



Cytec Cycom 5250-5 T650 Unitape Gr 145 32% RC Qualification Statistical Analysis Report

FAA Special Project Number SP4613WI-Q

NCAMP Test Report Number: NCP-RP-2010-068 N/C

Report Date: October 19, 2017

Elizabeth Clarkson, Ph.D.

National Center for Advanced Materials Performance (NCAMP)
National Institute for Aviation Research
Wichita State University
Wichita, KS 67260-0093

Testing Facility:

National Institute for Aviation Research
Wichita State University
1845 N. Fairmount
Wichita, KS 67260-0093

Test Panel Fabrication Facility:

Northrop Grumman Corporation
900 N. Douglas St., Bldg 902
El Segundo, CA 90245

Prepared by: _____
Elizabeth Clarkson, Ph.D

Reviewed by: _____
Evelyn Lian

Approved by: _____
Royal Lovingfoss

REVISIONS:

Rev	By	Date	Pages Revised or Added
N/C	Elizabeth Clarkson	10/19/2017	Document Initial Release

DISCONTINUED

Table of Contents

1. Introduction..... 9

1.1 Symbols and Abbreviations 10

1.2 Pooling Across Environments..... 11

1.3 Basis Value Computational Process..... 12

1.4 Modified Coefficient of Variation (CV) Method..... 12

2. Background 14

2.1 ASAP Statistical Formulas and Computations 14

 2.1.1 Basic Descriptive Statistics..... 14

 2.1.2 Statistics for Pooled Data..... 14

 2.1.3 Basis Value Computations..... 15

 2.1.4 Modified Coefficient of Variation 16

 2.1.5 Determination of Outliers 17

 2.1.6 The k-Sample Anderson Darling Test for Batch Equivalency 18

 2.1.7 The Anderson Darling Test for Normality..... 19

 2.1.8 Levene’s Test for Equality of Coefficient of Variation 20

2.2 STAT-17..... 20

 2.2.1 Distribution Tests..... 20

 2.2.2 Computing Normal Distribution Basis Values 21

 2.2.3 Non-parametric Basis Values 25

 2.2.4 Analysis of Variance (ANOVA) Basis Values..... 28

2.3 Single Batch and Two Batch Estimates using Modified CV..... 30

2.4 Lamina Variability Method (LVM) 30

2.5 0° Lamina Strength Derivation..... 32

 2.5.1 0° Lamina Strength Derivation (Alternate Formula) 32

3. Summary of Results..... 33

3.1 NCAMP Recommended B-basis Values 33

3.2 Lamina and Laminate Summary Tables 36

4. Test Results, Statistics, Basis Values and Graphs..... 38

4.1 Longitudinal (0°) Tension Properties (LT)..... 39

4.2 Transverse (90°) Tension Properties (TT) 42

4.3 Longitudinal (0°) Compression Properties (LC)..... 44

4.4 Transverse (90°) Compression Properties (TC)..... 46

4.5 In-Plane Shear Properties (IPS) 48

4.6 Short Beam Strength (SBS) Data 50

4.7 Unnotched Tension Properties (UNT0) 52

4.8 Unnotched Compression Properties (UNC0) 54

4.9 Quasi Isotropic Unnotched Tension Properties (UNT1) 56

4.10 “Soft” Unnotched Tension Properties (UNT2)..... 58

4.11 “Hard” Unnotched Tension Properties (UNT3) 60

4.12 Quasi Isotropic Unnotched Compression Properties (UNC1) 62

4.13 “Soft” Unnotched Compression Properties (UNC2) 64

4.14 “Hard” Unnotched Compression Properties (UNC3) 66

4.15 Quasi Isotropic Open Hole Tension Properties (OHT1)..... 68

4.16 “Soft” Open Hole Tension Properties (OHT2) 70

4.17 “Hard” Open Hole Tension Properties (OHT3) 72

4.18 Quasi Isotropic Filled Hole Tension Properties (FHT1) 74

4.19 "Soft" Filled Hole Tension Properties (FHT2) 76

4.20 "Hard" Filled Hole Tension Properties (FHT3) 78

4.21 Quasi Isotropic Open Hole Compression Properties (OHC1) 80

4.22 “Soft” Open Hole Compression Properties (OHC2) 82

4.23 “Hard” Open Hole Compression Properties (OHC3) 84

4.24 Quasi Isotropic Filled Hole Compression Properties (FHC1) 86

4.25 "Soft" Filled Hole Compression Properties (FHC2) 88

4.26 "Hard" Filled Hole Compression Properties (FHC3) 90

4.27 Laminate Short Beam Strength (SBS1) 92

4.28 Quasi Isotropic Single Shear Bearing Properties (SSB1)..... 94

4.29 "Soft" Single Shear Bearing Properties (SSB2)..... 96

4.30 "Hard" Single Shear Bearing Properties (SSB3) 98

4.31 Interlaminar Tension and Curved Beam Strength (ILT and CBS)..... 100

4.32 Compression After Impact (CAI)..... 101

5. Outliers..... 102

6. References 104

DISCONTINUED

List of Figures

Figure 4-1 Batch plot for LT strength computed from UNT0 specimens normalized 39

Figure 4-2 Batch plot for LT strength normalized 41

Figure 4-3: Batch Plot for TT strength as measured..... 42

Figure 4-4 Batch plot for LC strength normalized 44

Figure 4-5: Batch Plot for TC strength as measured..... 46

Figure 4-6: Batch plot for IPS strength as measured 48

Figure 4-7: Batch plot for SBS as measured 50

Figure 4-8: Batch Plot for UNT0 strength normalized..... 52

Figure 4-9: Batch Plot for UNC0 strength normalized 54

Figure 4-10: Batch Plot for UNT1 strength normalized..... 56

Figure 4-11: Batch Plot for UNT2 strength normalized..... 58

Figure 4-12: Batch Plot for UNT3 strength normalized..... 60

Figure 4-13: Batch plot for UNC1 strength normalized..... 62

Figure 4-14: Batch plot for UNC2 strength normalized..... 64

Figure 4-15: Batch plot for UNC3 strength normalized..... 66

Figure 4-16: Batch Plot for OHT1 strength normalized 68

Figure 4-17: Batch Plot for OHT2 strength normalized 70

Figure 4-18: Batch Plot for OHT3 strength normalized..... 72

Figure 4-19: Batch plot for FHT1 strength normalized 74

Figure 4-20: Batch plot for FHT2 strength normalized 76

Figure 4-21: Batch plot for FHT3 strength normalized 78

Figure 4-22: Batch plot for OHC1 strength normalized 80

Figure 4-23: Batch plot for OHC2 strength normalized 82

Figure 4-24: Batch plot for OHC3 strength normalized 84

Figure 4-25: Batch plot for FHC1 strength normalized..... 86

Figure 4-26: Batch plot for FHC2 strength normalized..... 88

Figure 4-27: Batch plot for FHC3 strength normalized..... 90

Figure 4-28: Batch plot for SBS1 strength as measured 92

Figure 4-29: Batch plot for SSB1 strength normalized 94

Figure 4-30: Batch plot for SSB2 strength normalized 97

Figure 4-31: Batch plot for SSB3 strength normalized 99

Figure 4-32: Plot for ILT and CBS as measured 100

Figure 4-33: Plot for Compression After Impact strength normalized 101

List of Tables

Table 1-1: Test Property Abbreviations 10

Table 1-2: Test Property Symbols 11

Table 1-3: Environmental Conditions Abbreviations 11

Table 2-1: K factors for normal distribution 21

Table 2-2: Weibull Distribution Basis Value Factors 24

Table 2-3: B-Basis Hanson-Koopmans Table 27

Table 2-4: A-Basis Hanson-Koopmans Table 28

Table 2-5: B-Basis factors for small datasets using variability of corresponding large dataset 31

Table 3-1 : NCAMP recommended B-basis values for lamina test data 34

Table 3-2 : NCAMP Recommended B-basis values for laminate test data 35

Table 3-3: Summary of Test Results for Lamina Data 36

Table 3-4: Summary of Test Results for Laminate Data 37

Table 4-1: Statistics and Basis values for LT strength from UNT0 40

Table 4-2: Statistics from LT modulus 40

Table 4-3: Statistics and Basis values for LT strength 41

Table 4-4: Statistics and Basis Values for TT Strength data as measured..... 43

Table 4-5: Statistics from TT Modulus data as measured 43

Table 4-6: Statistics and Basis Values for LC strength derived from UNC0 45

Table 4-7: Statistics from LC modulus 45

Table 4-8: Statistics and Basis Values for TC Strength data..... 47

Table 4-9: Statistics from TC Modulus data 47

Table 4-10: Statistics and Basis Values for IPS Strength data 49

Table 4-11: Statistics from IPS Modulus data 49

Table 4-12: Statistics and Basis Values for SBS data 51

Table 4-13: Statistics and Basis Values for UNT0 Strength data 53

Table 4-14: Statistics from UNT0 Modulus data 53

Table 4-15: Statistics and Basis Values for UNC0 Strength data..... 55

Table 4-16: Statistics from UNC0 Modulus data 55

Table 4-17: Statistics and Basis Values for UNT1 Strength data 57

Table 4-18: Statistics from UNT1 Modulus data 57

Table 4-19: Statistics and Basis Values for UNT2 Strength data 59

Table 4-20: Statistics from UNT2 Modulus data 59

Table 4-21: Statistics and Basis Values for UNT3 Strength data 61

Table 4-22: Statistics from UNT3 Modulus data 61

Table 4-23: Statistics and Basis Values for UNC1 Strength data..... 63

Table 4-24: Statistics from UNC1 Modulus data 63

Table 4-25: Statistics and Basis Values for UNC2 Strength data..... 65

Table 4-26: Statistics from UNC2 Modulus data 65

Table 4-27: Statistics and Basis Values for UNC3 Strength data..... 67

Table 4-28: Statistics from UNC3 Modulus data 67

Table 4-29: Statistics and Basis Values for OHT1 Strength data 69

Table 4-30: Statistics and Basis Values for OHT2 Strength data 71

Table 4-31: Statistics and Basis Values for OHT3 Strength data 73

Table 4-32: Statistics and Basis Values for FHT1 Strength data 75

Table 4-33: Statistics and Basis Values for FHT2 Strength data 77
Table 4-34: Statistics and Basis Values for FHT3 Strength data 79
Table 4-35: Statistics and Basis Values for OHC1 Strength data 81
Table 4-36: Statistics and Basis Values for OHC2 Strength data 83
Table 4-37: Statistics and Basis Values for OHC3 Strength data 85
Table 4-38: Statistics and Basis Values for FHC1 Strength data 87
Table 4-39: Statistics and Basis Values for FHC2 Strength data 89
Table 4-40: Statistics and Basis Values for FHC3 Strength data 91
Table 4-41: Statistics and Basis Values for SBS1 Strength data 93
Table 4-42: Statistics and Basis Values for SSB1 Strength data 95
Table 4-43: Statistics and Basis Values for SSB2 Strength data 97
Table 4-44: Statistics and Basis Values for SSB3 Strength data 99
Table 4-45: Statistics for ILT and CBS data 100
Table 4-46: Statistics for Compression After Impact Strength data 101
Table 5-1: List of outliers 103

DISCONTINUED

1. Introduction

This report contains statistical analysis of the Cytec 5250-5 12k T650 Unitape material property data published in NCAMP Test Report CAM-RP-2010-079 Rev C. The lamina and laminate material property data have been generated with FAA oversight through FAA Special Project Number SP4613WI-Q and also meet the requirements outlined in NCAMP Standard Operating Procedure NSP 100. The test panels, test specimens, and test setups have been conformed by the FAA and the testing has been witnessed by the FAA.

B-Basis values, A-estimates, and B-estimates were calculated using a variety of techniques that are detailed in section two. The qualification material was procured to NCAMP Material Specification NMS 226/1 Rev Initial Release dated July 17, 2007. The qualification test panels were cured in accordance with NCAMP Process Specification NPS 81226 Rev C dated July 23, 2008 "C" cure cycle. The panels were fabricated at Northrop Grumman, 900 N. Douglas St., Bldg 902, El Segundo, CA 90245. The NCAMP Test Plan NTP 2261Q1 Rev A was used for this qualification program. The testing was performed at the National Institute for Aviation Research (NIAR) in Wichita, Kansas.

Basis numbers are labeled as 'values' when the data meets all the requirements of CMH-17 Rev G. When those requirements are not met, they will be labeled as 'estimates.' When the data does not meet all requirements, the failure to meet these requirements is reported and the specific requirement(s) the data fails to meet is identified. The method used to compute the basis value is noted for each basis value provided. When appropriate, in addition to the traditional computational methods, values computed using the modified coefficient of variation method is also provided.

The material property data acquisition process is designed to generate basic material property data with sufficient pedigree for submission to Complete Documentation sections of the Composite Materials Handbook (CMH-17 Rev G).

The NCAMP shared material property database contains material property data of common usefulness to a wide range of aerospace projects. However, the data may not fulfill all the needs of a project. Specific properties, environments, laminate architecture, and loading situations that individual projects need may require additional testing.

The use of NCAMP material and process specifications do not guarantee material or structural performance. Material users should be actively involved in evaluating material performance and quality including, but not limited to, performing regular purchaser quality control tests, performing periodic equivalency/additional testing, participating in material change management activities, conducting statistical process control, and conducting regular supplier audits.

The applicability and accuracy of NCAMP material property data, material allowables, and specifications must be evaluated on case-by-case basis by aircraft companies and certifying agencies. NCAMP assumes no liability whatsoever, expressed or implied, related to the use of the material property data, material allowables, and specifications.

Part fabricators that wish to utilize the material property data, allowables, and specifications may be able to do so by demonstrating the capability to reproduce the original material properties; a process known as equivalency. More information about this equivalency process including the test statistics and its limitations can be found in Section 6 of DOT/FAA/AR-03/19 and Section 8.4.1 of CMH-17 Rev G. The applicability of equivalency process must be evaluated on program-by-program basis by the applicant and certifying agency. The applicant and certifying agency must agree that the equivalency test plan along with the equivalency process described in Section 6 of DOT/FAA/AR-03/19 and Section 8.4.1 of CMH-17 Rev G are adequate for the given program.

Aircraft companies should not use the data published in this report without specifying NCAMP Material Specification NMS 226/1. NMS 226/1 may have additional requirements that are listed in its prepreg process control document (PCD), fiber specification, fiber PCD, and other raw material specifications and PCDs which impose essential quality controls on the raw materials and raw material manufacturing equipment and processes. *Aircraft companies and certifying agencies should assume that the material property data published in this report is not applicable when the material is not procured to NMS 226/1. NMS 226/1 is a free, publicly available, non-proprietary aerospace industry material specification.*

This report is intended for general distribution to the public, either freely or at a price that does not exceed the cost of reproduction (e.g. printing) and distribution (e.g. postage).

1.1 Symbols and Abbreviations

Test Property	Abbreviation
Longitudinal Compression	LC
Longitudinal Tension	LT
Transverse Compression	TC
Transverse Tension	TT
In-Plane Shear	IPS
Short Beam Strength	SBS
Laminate Short Beam Strength	SBS1
Unnotched Tension	UNT
Unnotched Compression	UNC
Filled Hole Tension	FHT
Filled Hole Compression	FHC
Open Hole Tension	OHT
Open Hole Compression	OHC
Single Shear Bearing	SSB
Interlaminar Tension	ILT
Curved Beam Strength	CBS
Compression After Impact	CAI

Table 1-1: Test Property Abbreviations

Test Property	Symbol
Longitudinal Compression Strength	F_1^{cu}
Longitudinal Compression Modulus	E_1^c
Longitudinal Compression Poisson's Ratio	ν_{12}^c
Longitudinal Tension Strength	F_1^{tu}
Longitudinal Tension Modulus	E_1^t
Longitudinal Tension Poisson's Ratio	ν_{12}^t
Transverse Compression Strength	F_2^{cu}
Transverse Compression Modulus	E_2^c
Transverse Compression Poisson's Ratio	ν_{21}^c
Transverse Tension Strength	F_2^{tu}
Transverse Tension Modulus	E_2^t
In-Plane Shear Strength at 5% strain	$F_{12}^{s5\%}$
In-Plane Shear Strength at 0.2% offset	$F_{12}^{s0.2\%}$
In-Plane Shear Peak Strength before 5% strain	F_{12}^{smax}
In-Plane Shear Modulus	G_{12}^s

Table 1-2: Test Property Symbols

Environmental Condition	Temperature	Abbreviation
Cold Temperature Dry	-65°F	CTD
Room Temperature Dry	70°F	RTD
Elevated Temperature Dry	350°F	ETD
Elevated Temperature Wet	350°F	ETW

Table 1-3: Environmental Conditions Abbreviations

Tests with a number immediately after the abbreviation indicate the lay-up:

- 1 = "Quasi-Isotropic"
- 2 = "Soft"
- 3 = "Hard"

EX: OHT1 is an open hole tension test with a "Quasi-Isotropic" layup

Detailed information about the test methods and conditions used is given in NCAMP Test Report CAM-RP-2009-079 Rev C.

1.2 Pooling Across Environments

When pooling across environments was allowable, the pooled co-efficient of variation was used. ASAP (AGATE Statistical Analysis Program) 2008 version 1.0 was used to determine if pooling was allowable and to compute the pooled coefficient of variation for those tests. In these cases, the modified coefficient of variation based on the pooled data was used to compute the basis values.

When pooling across environments was not advisable because the data was not eligible for pooling and engineering judgment indicated there was no justification for overriding the result, then B-Basis values were computed for each environmental condition separately using Stat17 version 5.

1.3 Basis Value Computational Process

The general form to compute engineering basis values is: $\text{basis value} = \bar{X} - kS$ where k is a factor based on the sample size and the distribution of the sample data. There are many different methods to determine the value of k in this equation, depending on the sample size and the distribution of the data. In addition, the computational formula used for the standard deviation, S , may vary depending on the distribution of the data. The details of those different computations and when each should be used are in section 2.0.

1.4 Modified Coefficient of Variation (CV) Method

A common problem with new material qualifications is that the initial specimens produced and tested do not contain all of the variability that will be encountered when the material is being produced in larger amounts over a lengthy period of time. This can result in setting basis values that are unrealistically high. The variability as measured in the qualification program is often lower than the actual material variability because of several reasons. The materials used in the qualification programs are usually manufactured within a short period of time, typically 2-3 weeks only, which is not representative of the production material. Some raw ingredients that are used to manufacture the multi-batch qualification materials may actually be from the same production batches or manufactured within a short period of time so the qualification materials, although regarded as multiple batches, may not truly be multiple batches so they are not representative of the actual production material variability.

The modified Coefficient of Variation (CV) used in this report is in accordance with section 8.4.4 of CMH-17 Rev G. It is a method of adjusting the original basis values downward in anticipation of the expected additional variation. Composite materials are expected to have a CV of at least 6%. The modified coefficient of variation (CV) method increases the measured coefficient of variation when it is below 8% prior to computing basis values. A higher CV will result in lower or more conservative basis values and lower specification limits. The use of the modified CV method is intended for a temporary period of time when there is minimal data available. When a sufficient number of production batches (approximately 8 to 15) have been produced and tested, the as-measured CV may be used so that the basis values and specification limits may be adjusted higher.

The material allowables in this report are calculated using both the as-measured CV and modified CV, so users have the choice of using either one. When the measured CV is greater than 8%, the modified CV method does not change the basis value. NCAMP recommended values make use of the modified CV method when it is appropriate for the data.

When the data fails the Anderson-Darling K-sample test for batch to batch variability or when the data fails the normality test, the modified CV method is not appropriate and no modified CV basis value will be provided. When the ANOVA method is used, it may produce excessively

conservative basis values. When appropriate, a single batch or two batch estimate may be provided in addition to the ANOVA estimate.

In some cases a transformation of the data to fit the assumption of the modified CV resulted in the transformed data passing the ADK test and thus the data can be pooled only for the modified CV method.

NCAMP recommends that if a user decides to use the basis values that are calculated from as-measured CV, the specification limits and control limits be calculated with as-measured CV also. Similarly, if a user decides to use the basis values that are calculated from modified CV, the specification limits and control limits be calculated with modified CV also. This will ensure that the link between material allowables, specification limits, and control limits is maintained.

DISCONTINUED

2. Background

Statistical computations are performed with AGATE Statistical Analysis Program (ASAP) when pooling across environments is permissible according to CMH-17 Rev G guidelines. If pooling is not permissible, a single point analysis using STAT-17 is performed for each environmental condition with sufficient test results. If the data does not meet CMH-17 Rev G requirements for a single point analysis, estimates are created by a variety of methods depending on which is most appropriate for the dataset available. Specific procedures used are presented in the individual sections where the data is presented.

2.1 ASAP Statistical Formulas and Computations

This section contains the details of the specific formulas ASAP uses in its computations.

2.1.1 Basic Descriptive Statistics

The basic descriptive statistics shown are computed according to the usual formulas, which are shown below:

Mean:
$$\bar{X} = \sum_{i=1}^n \frac{X_i}{n}$$
 Equation 1

Std. Dev.:
$$S = \sqrt{\frac{1}{n-1} \sum_{i=1}^n (X_i - \bar{X})^2}$$
 Equation 2

% Co. Variation:
$$\frac{S}{\bar{X}} \times 100$$
 Equation 3

Where n refers to the number of specimens in the sample and X_i refers to the individual specimen measurements.

2.1.2 Statistics for Pooled Data

Prior to computing statistics for the pooled dataset, the data is normalized to a mean of one by dividing each value by the mean of all the data for that condition. This transformation does not affect the coefficients of variation for the individual conditions.

2.1.2.1 Pooled Standard Deviation

The formula to compute a pooled standard deviation is given below:

Pooled Std. Dev. S_p
$$S_p = \sqrt{\frac{\sum_{i=1}^k (n_i - 1) S_i^2}{\sum_{i=1}^k (n_i - 1)}}$$
 Equation 4

Where k refers to the number of batches and n_i refers to the number of specimens in the i^{th} sample.

2.1.2.2 Pooled Coefficient of Variation

Since the mean for the normalized data is 1.0 for each condition, the pooled normalized data also has a mean of one. The coefficient of variation for the pooled normalized data is the pooled standard deviation divided by the pooled mean, as in equation 3. Since the mean for the pooled normalized data is one, the pooled coefficient of variation is equal to the pooled standard deviation of the normalized data.

$$\text{Pooled Coefficient of Variation} = \frac{S_p}{1} = S_p \quad \text{Equation 5}$$

2.1.3 Basis Value Computations

Basis values are computed using the mean and standard deviation for that environment, as follows: The mean is always the mean for the environment, but if the data meets all requirements for pooling, S_p can be used in place of the standard deviation for the environment, S .

$$\begin{aligned} \text{Basis Values:} \quad A\text{-basis} &= \bar{X} - K_a S \\ B\text{-basis} &= \bar{X} - K_b S \end{aligned} \quad \text{Equation 6}$$

2.1.3.1 K-factor computations

K_a and K_b are computed according to the methodology documented in section 8.3.5 of CMH-17 Rev G. The approximation formulas are given below:

$$K_a = \frac{2.3263}{\sqrt{q(f)} + \sqrt{\frac{1}{c_A(f) \cdot n_j} + \left(\frac{b_A(f)}{2c_A(f)}\right)^2}} - \frac{b_A(f)}{2c_A(f)} \quad \text{Equation 7}$$

$$K_b = \frac{1.2816}{\sqrt{q(f)} + \sqrt{\frac{1}{c_B(f) \cdot n_j} + \left(\frac{b_B(f)}{2c_B(f)}\right)^2}} - \frac{b_B(f)}{2c_B(f)} \quad \text{Equation 8}$$

Where

r = the number of environments being pooled together

n_j = number of data values for environment j

$$N = \sum_{j=1}^r n_j$$

$$f = N - r$$

$$q(f) = 1 - \frac{2.323}{\sqrt{f}} + \frac{1.064}{f} + \frac{0.9157}{f\sqrt{f}} - \frac{0.6530}{f^2} \quad \text{Equation 9}$$

$$b_B(f) = \frac{1.1372}{\sqrt{f}} - \frac{0.49162}{f} + \frac{0.18612}{f\sqrt{f}} \quad \text{Equation 10}$$

$$c_B(f) = 0.36961 + \frac{0.0040342}{\sqrt{f}} - \frac{0.71750}{f} + \frac{0.19693}{f\sqrt{f}} \quad \text{Equation 11}$$

$$b_A(f) = \frac{2.0643}{\sqrt{f}} - \frac{0.95145}{f} + \frac{0.51251}{f\sqrt{f}} \quad \text{Equation 12}$$

$$c_A(f) = 0.36961 + \frac{0.0026958}{\sqrt{f}} - \frac{0.65201}{f} + \frac{0.011320}{f\sqrt{f}} \quad \text{Equation 13}$$

2.1.4 Modified Coefficient of Variation

The coefficient of variation is modified according to the following rules:

$$\text{Modified CV} = CV^* = \begin{cases} .06 & \text{if } CV < .04 \\ \frac{CV}{2} + .04 & \text{if } .04 \leq CV < .08 \\ CV & \text{if } CV \geq .08 \end{cases} \quad \text{Equation 14}$$

This is converted to percent by multiplying by 100%.

CV^* is used to compute a modified standard deviation S^* .

$$S^* = CV^* \cdot \bar{X} \quad \text{Equation 15}$$

To compute the pooled standard deviation based on the modified CV:

$$S_p^* = \sqrt{\frac{\sum_{i=1}^k ((n_i - 1)(CV_i^* \cdot \bar{X}_i)^2)}{\sum_{i=1}^k (n_i - 1)}} \quad \text{Equation 16}$$

The A-basis and B-basis values under the assumption of the modified CV method are computed by replacing S with S^* .

2.1.4.1 Transformation of data based on Modified CV

In order to determine if the data would pass the diagnostic tests under the assumption of the modified CV, the data must be transformed such that the batch means remain the same while the standard deviation of transformed data (all batches) matches the modified standard deviation.

To accomplish this requires a transformation in two steps:

Step 1: Apply the modified CV rules to each batch and compute the modified standard deviation $S_i^* = CV^* \cdot \bar{X}_i$ for each batch. Transform the data in each batch as follows:

$$X'_{ij} = C_i (X_{ij} - \bar{X}_i) + \bar{X}_i \quad \text{Equation 17}$$

$$C_i = \frac{S_i^*}{S_i} \quad \text{Equation 18}$$

Run the Anderson-Darling k-sample test for batch equivalence (see section 2.1.6) on the transformed data. If it passes, proceed to step 2. If not, stop. The data cannot be pooled.

Step 2: Another transformation is needed as applying the modified CV to each batch leads to a larger CV for the combined data than when applying the modified CV rules to the combined data (due to the addition of between batch variation when combining data from multiple batches). In order to alter the data to match S^* the transformed data is transformed again, this time setting using the same value of C' for all batches.

$$X''_{ij} = C' (X'_{ij} - \bar{X}_i) + \bar{X}_i \quad \text{Equation 19}$$

$$C' = \sqrt{\frac{SSE^*}{SSE'}} \quad \text{Equation 20}$$

$$SSE^* = (n-1)(CV^* \bar{X})^2 - \sum_{i=1}^k n_i (\bar{X}_i - \bar{X})^2 \quad \text{Equation 21}$$

$$SSE' = \sum_{i=1}^k \sum_{j=1}^{n_i} (X'_{ij} - \bar{X}_i)^2 \quad \text{Equation 22}$$

Once this second transformation has been completed, the k-sample Anderson Darling test for batch equivalence can be run on the transformed data to determine if the modified co-efficient of variation will permit pooling of the data.

2.1.5 Determination of Outliers

All outliers are identified in text and graphics. If an outlier is removed from the dataset, it will be specified and the reason why will be documented in the text. Outliers are identified using the Maximum Normed Residual Test for Outliers as specified in section 8.3.3 of CMH-17 Rev G.

$$MNR = \frac{\max_{all i} |X_i - \bar{X}|}{S}, i = 1 \dots n \quad \text{Equation 23}$$

$$C = \frac{n-1}{\sqrt{n}} \sqrt{\frac{t^2}{n-2+t^2}} \quad \text{Equation 24}$$

where t is the $1 - \frac{.05}{2n}$ quartile of a t distribution with n-2 degrees of freedom.

If $MNR > C$, then the X_i associated with the MNR is considered to be an outlier. If an outlier exists, then the X_i associated with the MNR is dropped from the dataset and the MNR procedure is applied again. This process is repeated until no outliers are detected. Additional information on this procedure can be found in references 1 and 2.

2.1.6 The k-Sample Anderson Darling Test for Batch Equivalency

The k-sample Anderson-Darling test is a nonparametric statistical procedure that tests the hypothesis that the populations from which two or more groups of data were drawn are identical. The distinct values in the combined data set are ordered from smallest to largest, denoted $z_{(1)}, z_{(2)}, \dots, z_{(L)}$, where L will be less than n if there are tied observations. These rankings are used to compute the test statistic.

The k-sample Anderson-Darling test statistic is:

$$ADK = \frac{n-1}{n^2(k-1)} \sum_{i=1}^k \left[\frac{1}{n_i} \sum_{j=1}^L h_j \frac{(nF_{ij} - n_i H_j)^2}{H_j(n - H_j) - \frac{nh_j}{4}} \right] \quad \text{Equation 25}$$

Where

n_i = the number of test specimens in each batch

$n = n_1 + n_2 + \dots + n_k$

h_j = the number of values in the combined samples equal to $z_{(j)}$

H_j = the number of values in the combined samples less than $z_{(j)}$ plus $\frac{1}{2}$ the number of values in the combined samples equal to $z_{(j)}$

F_{ij} = the number of values in the i^{th} group which are less than $z_{(j)}$ plus $\frac{1}{2}$ the number of values in this group which are equal to $z_{(j)}$.

The critical value for the test statistic at $1-\alpha$ level is computed:

$$ADC = 1 + \sigma_n \left[z_\alpha + \frac{0.678}{\sqrt{k-1}} - \frac{0.362}{k-1} \right]. \quad \text{Equation 26}$$

This formula is based on the formula in reference 3 at the end of section 5, using a Taylor's expansion to estimate the critical value via the normal distribution rather than using the t distribution with $k-1$ degrees of freedom.

$$\sigma_n^2 = \text{VAR}(ADK) = \frac{an^3 + bn^2 + cn + d}{(n-1)(n-2)(n-3)(k-1)^2} \quad \text{Equation 27}$$

With

$$\begin{aligned}
a &= (4g - 6)(k - 1) + (10 - 6g)S \\
b &= (2g - 4)k^2 + 8Tk + (2g - 14T - 4)S - 8T + 4g - 6 \\
c &= (6T + 2g - 2)k^2 + (4T - 4g + 6)k + (2T - 6)S + 4T \\
d &= (2T + 6)k^2 - 4Tk \\
S &= \sum_{i=1}^k \frac{1}{n_i} \\
T &= \sum_{i=1}^{n-1} \frac{1}{i} \\
g &= \sum_{i=1}^{n-2} \sum_{j=i+1}^{n-1} \frac{1}{(n-i)j}
\end{aligned}$$

The data is considered to have failed this test (i.e. the batches are not from the same population) when the test statistic is greater than the critical value. For more information on this procedure, see reference 3.

2.1.7 The Anderson Darling Test for Normality

Normal Distribution: A two parameter (μ, σ) family of probability distributions for which the probability that an observation will fall between a and b is given by the area under the curve between a and b :

$$F(x) = \int_a^b \frac{1}{\sigma\sqrt{2\pi}} e^{-\frac{(x-\mu)^2}{2\sigma^2}} dx \quad \text{Equation 28}$$

A normal distribution with parameters (μ, σ) has population mean μ and variance σ^2 .

The normal distribution is considered by comparing the cumulative normal distribution function that best fits the data with the cumulative distribution function of the data. Let

$$z_{(i)} = \frac{x_{(i)} - \bar{x}}{s}, \quad \text{for } i = 1, \dots, n \quad \text{Equation 29}$$

where $x_{(i)}$ is the smallest sample observation, \bar{x} is the sample average, and s is the sample standard deviation.

The Anderson Darling test statistic (AD) is:

$$AD = \sum_{i=1}^n \frac{1-2i}{n} \left\{ \ln [F_0(z_{(i)})] + \ln [1 - F_0(z_{(n+1-i)})] \right\} - n \quad \text{Equation 30}$$

Where F_0 is the standard normal distribution function. The observed significance level (OSL) is

$$OSL = \frac{1}{1 + e^{-0.48 + 0.78 \ln(AD^*) + 4.58 AD^*}}, \quad AD^* = \left(1 + \frac{0.2}{\sqrt{n}} \right) AD \quad \text{Equation 31}$$

This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if, in fact, the data are a sample from a normal population. If $OSL > 0.05$, the data is considered sufficiently close to a normal distribution.

2.1.8 Levene's Test for Equality of Coefficient of Variation

Levene's test performs an Analysis of Variance on the absolute deviations from their sample medians. The absolute value of the deviation from the median is computed for each data value. $w_{ij} = |y_{ij} - \tilde{y}_i|$. An F-test is then performed on the transformed data values as follows:

$$F = \frac{\sum_{i=1}^k n_i (\bar{w}_i - \bar{w})^2 / (k - 1)}{\sum_{i=1}^k \sum_{j=1}^{n_i} (w_{ij} - \bar{w}_i)^2 / (n - k)}$$

Equation 32

If this computed F statistic is less than the critical value for the F-distribution having k-1 numerator and n-k denominator degrees of freedom at the 1- α level of confidence, then the data is not rejected as being too different in terms of the co-efficient of variation. ASAP provides the appropriate critical values for F at α levels of 0.10, 0.05, 0.025, and 0.01. For more information on this procedure, see references 4 and 5.

2.2 STAT-17

This section contains the details of the specific formulas STAT-17 uses in its computations.

The basic descriptive statistics, the maximum normed residual (MNR) test for outliers, and the Anderson Darling K-sample test for batch variability are the same as with ASAP – see sections 2.1.1, 2.1.3.1, and 2.1.5.

Outliers must be dispositioned before checking any other test results. The results of the Anderson Darling k-Sample (ADK) Test for batch equivalency must be checked. If the data passes the ADK test, then the appropriate distribution is determined. If it does not pass the ADK test, then the ANOVA procedure is the only approach remaining that will result in basis values that meet the requirements of CMH-17 Rev G.

2.2.1 Distribution Tests

In addition to testing for normality using the Anderson-Darling test (see 2.1.7); Stat17 also tests to see if the Weibull or Lognormal distribution is a good fit for the data.

Each distribution is considered using the Anderson-Darling test statistic which is sensitive to discrepancies in the tail regions. The Anderson-Darling test compares the cumulative distribution function for the distribution of interest with the cumulative distribution function of the data.

An observed significance level (OSL) based on the Anderson-Darling test statistic is computed for each test. The OSL measures the probability of observing an Anderson-Darling test statistic at least as extreme as the value calculated if the distribution under consideration is in fact the underlying distribution of the data. In other words, the OSL is the probability of obtaining a value of the test statistic at least as large as that obtained if the hypothesis that the data are actually from the distribution being tested is true. If the OSL is less than or equal to 0.05, then the assumption that the data are from the distribution being tested is rejected with at most a five percent risk of being in error.

If the normal distribution has an OSL greater than 0.05, then the data is assumed to be from a population with a normal distribution. If not, then if either the Weibull or lognormal distributions has an OSL greater than 0.05, then one of those can be used. If neither of these distributions has an OSL greater than 0.05, a non-parametric approach is used.

In what follows, unless otherwise noted, the sample size is denoted by n , the sample observations by x_1, \dots, x_n , and the sample observations ordered from least to greatest by $x_{(1)}, \dots, x_{(n)}$.

2.2.2 Computing Normal Distribution Basis Values

Stat17 uses a table of values for the k-factors (shown in Table 2-1) when the sample size is less than 16 and a slightly different formula than ASAP to compute approximate k-values for the normal distribution when the sample size is 16 or larger.

Norm. Dist. k Factors for N<16		
N	B-basis	A-basis
2	20.581	37.094
3	6.157	10.553
4	4.163	7.042
5	3.408	5.741
6	3.007	5.062
7	2.756	4.642
8	2.583	4.354
9	2.454	4.143
10	2.355	3.981
11	2.276	3.852
12	2.211	3.747
13	2.156	3.659
14	2.109	3.585
15	2.069	3.520

Table 2-1: K factors for normal distribution

2.2.2.1 One-sided B-basis tolerance factors, k_B , for the normal distribution when sample size is greater than 15.

The exact computation of k_B values is $1/\sqrt{n}$ times the 0.95th quantile of the noncentral t-distribution with noncentrality parameter $1.282\sqrt{n}$ and $n - 1$ degrees of freedom. Since this is not a calculation that Excel can handle, the following approximation to the k_B values is used:

$$k_B \approx 1.282 + \exp\{0.958 - 0.520\ln(n) + 3.19/n\} \quad \text{Equation 33}$$

This approximation is accurate to within 0.2% of the tabulated values for sample sizes greater than or equal to 16.

2.2.2.2 One-sided A-basis tolerance factors, k_A , for the normal distribution

The exact computation of k_B values is $1/\sqrt{n}$ times the 0.95th quantile of the noncentral t-distribution with noncentrality parameter $2.326\sqrt{n}$ and $n - 1$ degrees of freedom (Reference 11). Since this is not a calculation that Excel can handle easily, the following approximation to the k_B values is used:

$$k_A \approx 2.326 + \exp\{1.34 - 0.522 \ln(n) + 3.87/n\} \quad \text{Equation 34}$$

This approximation is accurate to within 0.2% of the tabulated values for sample sizes greater than or equal to 16.

2.2.2.3 Two-parameter Weibull Distribution

A probability distribution for which the probability that a randomly selected observation from this population lies between a and b ($0 < a < b < \infty$) is given by

$$e^{-(a/\alpha)^\beta} - e^{-(b/\alpha)^\beta} \quad \text{Equation 35}$$

where α is called the scale parameter and β is called the shape parameter.

In order to compute a check of the fit of a data set to the Weibull distribution and compute basis values assuming Weibull, it is first necessary to obtain estimates of the population shape and scale parameters (Section 2.2.2.3.1). Calculations specific to the goodness-of-fit test for the Weibull distribution are provided in section 2.2.2.3.2.

2.2.2.3.1 Estimating Weibull Parameters

This section describes the *maximum likelihood* method for estimating the parameters of the two-parameter Weibull distribution. The maximum-likelihood estimates of the shape and scale parameters are denoted $\hat{\beta}$ and $\hat{\alpha}$. The estimates are the solution to the pair of equations:

$$\hat{\beta} \ln \hat{\beta} - \frac{\hat{\beta}}{\hat{\alpha}^{\hat{\beta}-1}} \sum_{i=1}^n x_i^{\hat{\beta}} = 0 \quad \text{Equation 36}$$

$$\frac{n}{\hat{\beta}} - n \ln \hat{\alpha} + \sum_{i=1}^n \ln x_i - \sum_{i=1}^n \left[\frac{x_i}{\hat{\alpha}} \right]^{\hat{\beta}} (\ln x_i - \ln \hat{\alpha}) = 0 \quad \text{Equation 37}$$

Stat17 solves these equations numerically for $\hat{\beta}$ and $\hat{\alpha}$ in order to compute basis values.

2.2.2.3.2 Goodness-of-fit test for the Weibull distribution

The two-parameter Weibull distribution is considered by comparing the cumulative Weibull distribution function that best fits the data with the cumulative distribution function of the data. Using the shape and scale parameter estimates from section 2.2.2.3.1, let

$$z_{(i)} = \left[x_{(i)} / \hat{\alpha} \right]^{\hat{\beta}}, \quad \text{for } i = 1, \dots, n \quad \text{Equation 38}$$

The Anderson-Darling test statistic is

$$AD = \sum_{i=1}^n \frac{1-2i}{n} \left[\ln \left[1 - \exp(-z_{(i)}) \right] - z_{(n+1-i)} \right] - n \quad \text{Equation 39}$$

and the observed significance level is

$$OSL = 1 / \{1 + \exp[-0.10 + 1.24 \ln(AD^*) + 4.48 AD^*]\} \quad \text{Equation 40}$$

where

$$AD^* = \left(1 + \frac{0.2}{\sqrt{n}} \right) AD \quad \text{Equation 41}$$

This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if in fact the data is a sample from a two-parameter Weibull distribution. If $OSL \leq 0.05$, one may conclude (at a five percent risk of being in error) that the population does not have a two-parameter Weibull distribution. Otherwise, the hypothesis that the population has a two-parameter Weibull distribution is not rejected. For further information on these procedures, see reference 6.

2.2.2.3.3 Basis value calculations for the Weibull distribution

For the two-parameter Weibull distribution, the B-basis value is

$$B = \hat{q} e^{\left(\frac{-V}{\hat{\beta} \sqrt{n}} \right)} \quad \text{Equation 42}$$

where

$$\hat{q} = \hat{\alpha} (0.10536)^{1/\hat{\beta}} \quad \text{Equation 43}$$

To calculate the A-basis value, substitute the equation below for the equation above.

$$\hat{q} = \hat{\alpha} (0.01005)^{1/\hat{\beta}} \quad \text{Equation 44}$$

V is the value in Table 2.2. when the sample size is less than 16. For sample sizes of 16 or larger, a numerical approximation to the V values is given in the two equations immediately below.

$$V_B \approx 3.803 + \exp \left[1.79 - 0.516 \ln(n) + \frac{5.1}{n-1} \right] \quad \text{Equation 45}$$

$$V_A \approx 6.649 + \exp \left[2.55 - 0.526 \ln(n) + \frac{4.76}{n} \right] \quad \text{Equation 46}$$

This approximation is accurate within 0.5% of the tabulated values for n greater than or equal to 16.

Weibull Dist. K Factors for N<16		
N	B-basis	A-basis
2	690.804	1284.895
3	47.318	88.011
4	19.836	36.895
5	13.145	24.45
6	10.392	19.329
7	8.937	16.623
8	8.047	14.967
9	7.449	13.855
10	6.711	12.573
11	6.477	12.093
12	6.286	11.701
13	6.127	11.375
14	5.992	11.098
15	5.875	10.861

Table 2-2: Weibull Distribution Basis Value Factors

2.2.2.4 Lognormal Distribution

A probability distribution for which the probability that an observation selected at random from this population falls between a and b ($0 < a < b < \infty$) is given by the area under the normal distribution between $\ln(a)$ and $\ln(b)$.

The lognormal distribution is a positively skewed distribution that is simply related to the normal distribution. If something is lognormally distributed, then its logarithm is normally distributed. The natural (base e) logarithm is used.

2.2.2.4.1 Goodness-of-fit test for the Lognormal distribution

In order to test the goodness-of-fit of the lognormal distribution, take the logarithm of the data and perform the Anderson-Darling test for normality from Section 2.1.7. Using the natural logarithm, replace the linked equation above with linked equation below:

$$z_{(i)} = \frac{\ln(x_{(i)}) - \bar{x}_L}{s_L}, \quad \text{for } i = 1, \dots, n \quad \text{Equation 47}$$

where $x_{(i)}$ is the i^{th} smallest sample observation, \bar{x}_L and s_L are the mean and standard deviation of the $\ln(x_i)$ values.

The Anderson-Darling statistic is then computed using the linked equation above and the observed significance level (OSL) is computed using the linked equation above. This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if in fact the data are a sample from a lognormal distribution. If $OSL \leq 0.05$, one may conclude (at a five percent risk of being in error) that the population is not lognormally distributed. Otherwise, the hypothesis that the population is lognormally distributed is not rejected. For further information on these procedures, see reference 6.

2.2.2.4.2 Basis value calculations for the Lognormal distribution

If the data set is assumed to be from a population with a lognormal distribution, basis values are calculated using the equation above in section 2.1.3. However, the calculations are performed using the logarithms of the data rather than the original observations. The computed basis values are then transformed back to the original units by applying the inverse of the log transformation.

2.2.3 Non-parametric Basis Values

Non-parametric techniques do not assume any particularly underlying distribution for the population the sample comes from. It does require that the batches be similar enough to be grouped together, so the ADK test must have a positive result. While it can be used instead of assuming the normal, lognormal or Weibull distribution, it typically results in lower basis values. One of following two methods should be used, depending on the sample size.

2.2.3.1 Non-parametric Basis Values for large samples

The required sample sizes for this ranking method differ for A and B basis values. A sample size of at least 29 is needed for the B-basis value while a sample size of 299 is required for the A-basis.

To calculate a B-basis value for $n > 28$, the value of r is determined with the following formulas:

For B-basis values:

$$r_B = \frac{n}{10} - 1.645 \sqrt{\frac{9n}{100}} + 0.23 \quad \text{Equation 48}$$

For A-Basis values:

$$r_A = \frac{n}{100} - 1.645 \sqrt{\frac{99n}{10,000}} + 0.29 + \frac{19.1}{n} \quad \text{Equation 49}$$

The formula for the A-basis values should be rounded to the nearest integer. This approximation is exact for most values and for a small percentage of values (less than 0.2%), the approximation errs by one rank on the conservative side.

The B-basis value is the r_B^{th} lowest observation in the data set, while the A-basis values are the r_A^{th} lowest observation in the data set. For example, in a sample of size $n = 30$, the lowest ($r = 1$) observation is the B-basis value. Further information on this procedure may be found in reference 7.

2.2.3.2 Non-parametric Basis Values for small samples

The Hanson-Koopmans method (references 8 and 9) is used for obtaining a B-basis value for sample sizes not exceeding 28 and A-basis values for sample sizes less than 299. This procedure requires the assumption that the observations are a random sample from a population for which the logarithm of the cumulative distribution function is concave, an assumption satisfied by a large class of probability distributions. There is substantial empirical evidence that suggests that composite strength data satisfies this assumption.

The Hanson-Koopmans B-basis value is:

$$B = x_{(r)} \left[\frac{x_{(1)}}{x_{(r)}} \right]^k \quad \text{Equation 50}$$

The A-basis value is:

$$A = x_{(n)} \left[\frac{x_{(1)}}{x_{(n)}} \right]^k \quad \text{Equation 51}$$

where $x_{(n)}$ is the largest data value, $x_{(1)}$ is the smallest, and $x_{(r)}$ is the r^{th} largest data value. The values of r and k depend on n and are listed in Table 2-3. This method is not used for the B-basis value when $x_{(r)} = x_{(1)}$.

The Hanson-Koopmans method can be used to calculate A-basis values for n less than 299. Find the value k_A corresponding to the sample size n in Table 2-4. For an A-basis value that meets all the requirements of CMH-17 Rev G, there must be at least five batches represented in the data and at least 55 data points. For a B-basis value, there must be at least three batches represented in the data and at least 18 data points.

B-Basis Hanson-Koopmans Table		
n	r	k
2	2	35.177
3	3	7.859
4	4	4.505
5	4	4.101
6	5	3.064
7	5	2.858
8	6	2.382
9	6	2.253
10	6	2.137
11	7	1.897
12	7	1.814
13	7	1.738
14	8	1.599
15	8	1.540
16	8	1.485
17	8	1.434
18	9	1.354
19	9	1.311
20	10	1.253
21	10	1.218
22	10	1.184
23	11	1.143
24	11	1.114
25	11	1.087
26	11	1.060
27	11	1.035
28	12	1.010

Table 2-3: B-Basis Hanson-Koopmans Table

DISCONTINUED

A-Basis Hanson-Koopmans Table					
n	k	n	k	n	k
2	80.00380	38	1.79301	96	1.32324
3	16.91220	39	1.77546	98	1.31553
4	9.49579	40	1.75868	100	1.30806
5	6.89049	41	1.74260	105	1.29036
6	5.57681	42	1.72718	110	1.27392
7	4.78352	43	1.71239	115	1.25859
8	4.25011	44	1.69817	120	1.24425
9	3.86502	45	1.68449	125	1.23080
10	3.57267	46	1.67132	130	1.21814
11	3.34227	47	1.65862	135	1.20620
12	3.15540	48	1.64638	140	1.19491
13	3.00033	49	1.63456	145	1.18421
14	2.86924	50	1.62313	150	1.17406
15	2.75672	52	1.60139	155	1.16440
16	2.65889	54	1.58101	160	1.15519
17	2.57290	56	1.56184	165	1.14640
18	2.49660	58	1.54377	170	1.13801
19	2.42833	60	1.52670	175	1.12997
20	2.36683	62	1.51053	180	1.12226
21	2.31106	64	1.49520	185	1.11486
22	2.26020	66	1.48063	190	1.10776
23	2.21359	68	1.46675	195	1.10092
24	2.17067	70	1.45352	200	1.09434
25	2.13100	72	1.44089	205	1.08799
26	2.09419	74	1.42881	210	1.08187
27	2.05991	76	1.41724	215	1.07595
28	2.02790	78	1.40614	220	1.07024
29	1.99791	80	1.39549	225	1.06471
30	1.96975	82	1.38525	230	1.05935
31	1.94324	84	1.37541	235	1.05417
32	1.91822	86	1.36592	240	1.04914
33	1.89457	88	1.35678	245	1.04426
34	1.87215	90	1.34796	250	1.03952
35	1.85088	92	1.33944	275	1.01773
36	1.83065	94	1.33120	299	1.00000
37	1.81139				

Table 2-4: A-Basis Hanson-Koopmans Table

2.2.4 Analysis of Variance (ANOVA) Basis Values

ANOVA is used to compute basis values when the batch to batch variability of the data does not pass the ADK test. Since ANOVA makes the assumption that the different batches have equal variances, the data is checked to make sure the assumption is valid. Levene's test for equality of variance is used (see section 2.1.8). If the dataset fails Levene's test, the basis values computed are likely to be conservative. Thus this method can still be used but the values produced will be listed as estimates.

2.2.4.1 Calculation of basis values using ANOVA

The following calculations address batch-to-batch variability. In other words, the only grouping is due to batches and the k-sample Anderson-Darling test (Section 2.1.6) indicates that the batch to batch variability is too large to pool the data. The method is based on the one-way analysis of variance random-effects model, and the procedure is documented in reference 10.

ANOVA separates the total variation (called the sum of squares) of the data into two sources: between batch variation and within batch variation.

First, statistics are computed for each batch, which are indicated with a subscript (n_i, \bar{x}_i, s_i^2) while statistics that were computed with the entire dataset do not have a subscript. Individual data values are represented with a double subscript, the first number indicated the batch and the second distinguishing between the individual data values within the batch. k stands for the number of batches in the analysis. With these statistics, the Sum of Squares Between batches (SSB) and the Total Sum of Squares (SST) are computed:

$$SSB = \sum_{i=1}^k n_i \bar{x}_i^2 - n \bar{x}^2 \quad \text{Equation 52}$$

$$SST = \sum_{i=1}^k \sum_{j=1}^{n_i} x_{ij}^2 - n \bar{x}^2 \quad \text{Equation 53}$$

The within-batch, or error, sum of squares (SSE) is computed by subtraction

$$SSE = SST - SSB \quad \text{Equation 54}$$

Next, the mean sums of squares are computed:

$$MSB = \frac{SSB}{k-1} \quad \text{Equation 55}$$

$$MSE = \frac{SSE}{n-k} \quad \text{Equation 56}$$

Since the batches need not have equal numbers of specimens, an ‘effective batch size,’ is defined as

$$n' = \frac{n - \frac{1}{n} \sum_{i=1}^k n_i^2}{k-1} \quad \text{Equation 57}$$

Using the two mean squares and the effective batch size, an estimate of the population standard deviation is computed:

$$S = \sqrt{\frac{MSB}{n'} + \left(\frac{n'-1}{n'}\right) MSE} \quad \text{Equation 58}$$

Two k-factors are computed using the methodology of section 2.2.2 using a sample size of n (denoted k_0) and a sample size of k (denoted k_1). Whether this value is an A- or B-basis value depends only on whether k_0 and k_1 are computed for A or B-basis values.

Denote the ratio of mean squares by

$$u = \frac{MSB}{MSE} \quad \text{Equation 59}$$

If u is less than one, it is set equal to one. The tolerance limit factor is

$$T = \frac{k_0 - \frac{k_1}{\sqrt{n'}} + (k_1 - k_0) \sqrt{\frac{u}{u + n' - 1}}}{1 - \frac{1}{\sqrt{n'}}} \quad \text{Equation 60}$$

The basis value is $\bar{x} - TS$.

The ANOVA method can produce extremely conservative basis values when a small number of batches are available. Therefore, when less than five (5) batches are available and the ANOVA method is used, the basis values produced will be listed as estimates.

2.3 Single Batch and Two Batch Estimates using Modified CV

This method has not been approved for use by the CMH-17 organization. Values computed in this manner are estimates only. It is used only when fewer than three batches are available and no valid B-basis value could be computed using any other method. The estimate is made using the mean of the data and setting the coefficient of variation to 8 percent if it was less than that. A modified standard deviation (S_{adj}) was computed by multiplying the mean by 0.08 and computing the A and B-basis values using this inflated value for the standard deviation.

$$\text{Estimated B-Basis} = \bar{X} - k_b S_{adj} = \bar{X} - k_b \cdot 0.08 \cdot \bar{X} \quad \text{Equation 61}$$

2.4 Lamina Variability Method (LVM)

This method has not been approved for use by the CMH-17 organization. Values computed in this manner are estimates only. It is used only when the sample size is less than 16 and no valid B-basis value could be computed using any other method. The prime assumption for applying the LVM is that the intrinsic strength variability of the laminate (small) dataset is no greater than the strength variability of the lamina (large) dataset. This assumption was tested and found to be reasonable for composite materials as documented by Tomblin and Seneviratne [12].

To compute the estimate, the coefficients of variation (CVs) of laminate data are paired with lamina CV's for the same loading condition and environmental condition. For example, the 0° compression lamina CV CTD condition is used with open hole compression CTD condition. Bearing and in-plane shear laminate CV's are paired with 0° compression lamina CV's.

However, if the laminate CV is larger than the corresponding lamina CV, the larger laminate CV value is used.

The LVM B-basis value is then computed as:

$$\text{LVM Estimated B-Basis} = \bar{X}_1 - K_{(N_1, N_2)} \cdot \bar{X}_1 \cdot \max(CV_1, CV_2) \quad \text{Equation 62}$$

When used in conjunction with the modified CV approach, a minimum value of 8% is used for the CV.

$$\text{Mod CV LVM Estimated B-Basis} = \bar{X}_1 - K_{(N_1, N_2)} \cdot \bar{X}_1 \cdot \text{Max}(8\%, CV_1, CV_2) \quad \text{Equation 63}$$

With:

\bar{X}_1 the mean of the laminate (small dataset)

N_1 the sample size of the laminate (small dataset)

N_2 the sample size of the lamina (large dataset)

CV_1 is the coefficient of variation of the laminate (small dataset)

CV_2 is the coefficient of variation of the lamina (large dataset)

$K_{(N_1, N_2)}$ is given in Table 2-5

	N1														
	2	3	4	5	6	7	8	9	10	11	12	13	14	15	
2	0	0	0	0	0	0	0	0	0	0	0	0	0	0	
3	4.508	0	0	0	0	0	0	0	0	0	0	0	0	0	
4	3.827	3.607	0	0	0	0	0	0	0	0	0	0	0	0	
5	3.481	3.263	3.141	0	0	0	0	0	0	0	0	0	0	0	
6	3.273	3.056	2.934	2.854	0	0	0	0	0	0	0	0	0	0	
7	3.134	2.918	2.796	2.715	2.658	0	0	0	0	0	0	0	0	0	
8	3.035	2.820	2.697	2.616	2.558	2.515	0	0	0	0	0	0	0	0	
9	2.960	2.746	2.623	2.541	2.483	2.440	2.405	0	0	0	0	0	0	0	
10	2.903	2.688	2.565	2.484	2.425	2.381	2.346	2.318	0	0	0	0	0	0	
11	2.856	2.643	2.519	2.437	2.378	2.334	2.299	2.270	2.247	0	0	0	0	0	
12	2.819	2.605	2.481	2.399	2.340	2.295	2.260	2.231	2.207	2.187	0	0	0	0	
13	2.787	2.571	2.450	2.367	2.308	2.263	2.227	2.198	2.174	2.154	2.137	0	0	0	
14	2.761	2.547	2.423	2.341	2.281	2.236	2.200	2.171	2.147	2.126	2.109	2.093	0	0	
15	2.738	2.525	2.401	2.318	2.258	2.212	2.176	2.147	2.123	2.102	2.084	2.069	2.056	0	
16	2.719	2.505	2.381	2.298	2.238	2.192	2.156	2.126	2.102	2.081	2.063	2.048	2.034	2.022	
17	2.701	2.488	2.364	2.280	2.220	2.174	2.138	2.108	2.083	2.062	2.045	2.029	2.015	2.003	
18	2.686	2.473	2.348	2.265	2.204	2.158	2.122	2.092	2.067	2.046	2.028	2.012	1.999	1.986	
19	2.673	2.459	2.335	2.251	2.191	2.144	2.108	2.078	2.053	2.032	2.013	1.998	1.984	1.971	
20	2.661	2.447	2.323	2.239	2.178	2.132	2.095	2.065	2.040	2.019	2.000	1.984	1.970	1.958	
N1+N2-2	2.650	2.437	2.312	2.228	2.167	2.121	2.084	2.053	2.028	2.007	1.988	1.972	1.958	1.946	
22	2.640	2.427	2.302	2.218	2.157	2.110	2.073	2.043	2.018	1.996	1.978	1.962	1.947	1.935	
23	2.631	2.418	2.293	2.209	2.148	2.101	2.064	2.033	2.008	1.987	1.968	1.952	1.938	1.925	
24	2.623	2.410	2.285	2.201	2.139	2.092	2.055	2.025	1.999	1.978	1.959	1.943	1.928	1.916	
25	2.616	2.402	2.277	2.193	2.132	2.085	2.047	2.017	1.991	1.969	1.951	1.934	1.920	1.907	
26	2.609	2.396	2.270	2.186	2.125	2.078	2.040	2.009	1.984	1.962	1.943	1.927	1.912	1.900	
27	2.602	2.389	2.264	2.180	2.118	2.071	2.033	2.003	1.977	1.955	1.936	1.920	1.905	1.892	
28	2.597	2.383	2.258	2.174	2.112	2.065	2.027	1.996	1.971	1.949	1.930	1.913	1.899	1.886	
29	2.591	2.378	2.252	2.168	2.106	2.059	2.021	1.990	1.965	1.943	1.924	1.907	1.893	1.880	
30	2.586	2.373	2.247	2.163	2.101	2.054	2.016	1.985	1.959	1.937	1.918	1.901	1.887	1.874	
40	2.550	2.337	2.211	2.126	2.063	2.015	1.977	1.946	1.919	1.897	1.877	1.860	1.845	1.832	
50	2.528	2.315	2.189	2.104	2.041	1.993	1.954	1.922	1.896	1.873	1.853	1.836	1.820	1.807	
60	2.514	2.301	2.175	2.089	2.026	1.978	1.939	1.907	1.880	1.857	1.837	1.819	1.804	1.790	
70	2.504	2.291	2.164	2.079	2.016	1.967	1.928	1.896	1.869	1.846	1.825	1.808	1.792	1.778	
80	2.496	2.283	2.157	2.071	2.008	1.959	1.920	1.887	1.860	1.837	1.817	1.799	1.783	1.769	
90	2.491	2.277	2.151	2.065	2.002	1.953	1.913	1.881	1.854	1.830	1.810	1.792	1.776	1.762	
100	2.486	2.273	2.146	2.060	1.997	1.948	1.908	1.876	1.849	1.825	1.805	1.787	1.771	1.757	
125	2.478	2.264	2.138	2.051	1.988	1.939	1.899	1.867	1.839	1.816	1.795	1.777	1.761	1.747	
150	2.472	2.259	2.132	2.046	1.982	1.933	1.893	1.861	1.833	1.809	1.789	1.770	1.754	1.740	
175	2.468	2.255	2.128	2.042	1.978	1.929	1.889	1.856	1.828	1.805	1.784	1.766	1.750	1.735	
200	2.465	2.252	2.125	2.039	1.975	1.925	1.886	1.853	1.825	1.801	1.781	1.762	1.746	1.732	

Table 2-5: B-Basis factors for small datasets using variability of corresponding large dataset

2.5 0° Lamina Strength Derivation

Lamina strength values in the 0° direction were not obtained directly for any conditions during compression tests. They are derived from the cross-ply lamina test results using a back out formula. Unless stated otherwise, the 0° lamina strength values were derived using the following formula:

$F_{0^\circ}^u = F_{0^\circ/90^\circ}^u \cdot BF$ where BF is the backout factor.

$F_{0^\circ/90^\circ}^u$ =UNC0 or UNT0 strength values

$$BF = \frac{E_1 [V_0 E_2 + (1 - V_0) E_1] - (\nu_{12} E_2)^2}{[V_0 E_1 + (1 - V_0) E_2] [V_0 E_2 + (1 - V_0) E_1] - (\nu_{12} E_2)^2} \quad \text{Equation 64}$$

V_0 = fraction of 0° plies in the cross-ply laminate (1/2 for UNT0 and 1/3 for UNC0)

E_1 = Average across of batches of modulus for LC and LT as appropriate

E_2 = Average across of batches of modulus for TC and TT as appropriate

ν_{12} = major Poisson's ratio of 0° plies from an average of all batches

This formula can also be found in section 2.4.2, equation 2.4.2.1(b) of CMH-17 Rev G.

In computing these strength values, the values for each environment are computed separately. The compression values are computed using only compression data, the tension values are computed using only tension data. Both normalized and as measured computations are done using the as measured and normalized strength values from the UNC0 and UNT0 strength values.

2.5.1 0° Lamina Strength Derivation (Alternate Formula)

In some cases, the previous formula cannot be used. For example, if there were no ETD tests run for transverse tension and compression, the value for E_2 would not be available. In that case, this alternative formula is used to compute the strength values for longitudinal tension and compression. It is similar to, but not quite the same as the formula detailed above. It requires the UNC0 and UNT0 strength and modulus data in addition to the LC and LT modulus data.

The 0° lamina strength values for the LC ETD condition were derived using the formula:

$$F_{0^\circ}^{cu} = F_{0^\circ/90^\circ}^{cu} \frac{E_1^c}{E_{0^\circ/90^\circ}^c}, \quad F_{0^\circ}^{tu} = F_{0^\circ/90^\circ}^{tu} \frac{E_1^t}{E_{0^\circ/90^\circ}^t} \quad \text{Equation 65}$$

with $F_{0^\circ}^{cu}$, $F_{0^\circ}^{tu}$ the derived mean lamina strength value for compression and tension respectively

$F_{0^\circ/90^\circ}^{cu}$, $F_{0^\circ/90^\circ}^{tu}$ are the mean strength values for UNC0 and UNT0 respectively

E_1^c , E_1^t are the modulus values for LC and LT respectively

$E_{0^\circ/90^\circ}^c$, $E_{0^\circ/90^\circ}^t$ are the modulus values for UNC0 and UNT0 respectively

This formula can also be found in section 2.4.2, equation 2.4.2.1(d) of CMH-17 Rev G.

3. Summary of Results

The basis values for all tests are summarized in the following tables. The NCAMP recommended B-basis values meet all requirements of CMH-17 Rev G. However, not all test data meets those requirements. The summary tables provide a complete listing of all computed basis values and estimates of basis values. Data that does not meet the requirements of CMH-17 Rev G are shown in shaded boxes and labeled as estimates. Basis values computed with the modified coefficient of variation (CV) are presented whenever possible. Basis values and estimates computed without that modification are presented for all tests.

3.1 NCAMP Recommended B-basis Values

The following rules are used in determining what B-basis value, if any, is included in tables Table 3-1 and Table 3-2 of recommended values.

1. Recommended values are NEVER estimates. Only B-basis values that meet all requirements of CMH-17 Rev G are recommended.
2. Modified CV basis values are preferred. Recommended values will be the modified CV basis value when available. The CV provided with the recommended basis value will be the one used in the computation of the basis value.
3. Only normalized basis values are given for properties that are normalized.
4. ANOVA B-basis values are not recommended since only three batches of material are available and CMH-17 Rev G recommends that no less than five batches be used when computing basis values with the ANOVA method.
5. Basis values of 90% or more of the mean value imply that the CV is unusually low and may not be conservative. Caution is recommended with B-Basis values calculated from STAT17 when the B-basis value is 90% or more of the average value. Such values will be indicated.
6. If the data appear questionable (e.g. when the CTD-RTD-ETW trend of the basis values are not consistent with the CTD-RTD-ETW trend of the average values), then the B-basis values will not be recommended.

**NCAMP Recommended B-basis Values for
CYTEC CYCOM 5250-5 T650 Unitape**

All B-basis values in this table meet the standards for publication in CMH-17G Handbook
Values are for normalized data unless otherwise noted

Lamina Strength Tests

Environment	Statistic	LT from UNT0	LC from UNC0	TT*	TC*	SBS*	IPS*		
							0.2% Offset	5% Strain	Peak before 5% strain
CTD (-65° F)	B-basis	244.58	182.02	8.82	43.14	16.29	9.87		14.30
	Mean	275.82	221.42	10.53	48.89	18.31	11.14		16.15
	CV	6.00	9.44	8.23	6.17	6.00	6.00		6.00
RTD (70° F)	B-basis	264.73	223.46	9.24	34.73	14.05	7.66		
	Mean	295.97	245.47	11.00	39.21	15.82	8.61		
	CV	6.27	6.00	8.22	6.00	6.00	6.00		
ETD (350° F)	B-basis		184.13			8.00**			
	Mean		206.14			8.23			
	CV		6.41			2.36			
ETW (350° F)	B-basis	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	
	Mean	304.66	152.80	2.91	17.54	5.73	2.03	4.05	
	CV	4.47	4.73	16.61	4.34	4.70	7.26	5.84	

Notes: The modified CV B-basis value is recommended when available.

The CV provided corresponds with the B-basis value given.

NA implies that tests were run but data did not meet NCAMP recommended requirements.

"NA: A" indicates ANOVA with 3 batches, "NA: I" indicates insufficient data,

NA (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Shaded empty boxes indicate that no test data is available for that property and condition.

* Data is as measured rather than normalized

** indicates the Stat17 B-basis value is greater than 90% of the mean value.



Table 3-1 NCAMP recommended B-basis values for lamina test data

**NCAMP Recommended B-basis Values for
CYTEC CYCOM 5250-5 T650 Unitape**

All B-basis values in this table meet the standards for publication in CMH-17G Handbook
Values are for normalized data unless otherwise noted

Laminate Strength Tests

Lay-up	ENV	Statistic	OHT	OHC	FHT	FHC	UNT	UNC	SSB 2% Offset	SSB Ultimate	SBS1*
25/50/25	CTD (-65° F)	B-basis	47.74		55.66		87.17				
		Mean	53.46		62.25		97.36				
		CV	6.00		6.33		6.00				
	RTD (70° F)	B-basis	50.06	44.14	55.92	67.89	90.26	84.91	104.44	132.74	10.25
		Mean	55.79	49.84	62.51	77.29	100.45	93.98	119.70	147.65	11.84
		CV	6.00	6.00	6.00	6.45	6.00	6.56	6.69	6.64	7.07
	ETW (350° F)	B-basis	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA:A	NA (1)	NA (1)
		Mean	56.30	36.04	59.79	51.12	96.92	56.10	81.71	101.20	5.74
		CV	3.46	3.68	2.91	3.35	2.68	6.75	6.20	5.31	1.81
10/80/10	CTD (-65° F)	B-basis	40.82		47.17		63.17				
		Mean	45.12		52.01		69.63				
		CV	6.00		6.00		6.00				
	RTD (70° F)	B-basis	39.29	40.04	44.33	53.55	59.95	65.90	101.05	146.84**	
		Mean	43.59	43.86	49.18	58.68	66.41	71.89	114.09	153.33	
		CV	6.00	6.00	6.00	6.00	6.00	6.00	6.00	2.82	
	ETW (350° F)	B-basis	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA:A	NA (1)	
		Mean	34.30	25.57	35.74	34.74	48.76	33.83	79.40	100.43	
		CV	2.19	2.49	4.01	3.94	2.17	4.69	10.18	3.74	
50/40/10	CTD (-65° F)	B-basis	68.58		73.64		145.19				
		Mean	77.39		82.66		162.57				
		CV	6.00		6.00		6.05				
	RTD (70° F)	B-basis	73.01	58.69	79.34	76.84	151.77	123.30	105.08	129.46	
		Mean	81.83	64.89	88.31	87.16	169.15	134.87	116.79	143.52	
		CV	6.00	6.00	6.00	6.00	6.00	6.00	6.56	6.34	
	ETW (350° F)	B-basis	NA (1)	NA (1)	NA (1)	NA:A	NA (1)	NA (1)	NA (1)	NA (1)	
		Mean	91.01	46.16	85.77	61.27	169.70	67.36	77.54	97.94	
		CV	3.30	4.34	4.08	6.42	1.95	6.05	5.77	5.39	

Notes: The modified CV B-basis value is recommended when available.

The CV provided corresponds with the B-basis value given.

NA implies that tests were run but data did not meet NCAMP recommended requirements.

"NA: A" indicates ANOVA with 3 batches, "NA: I" indicates insufficient data,

NA (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Shaded empty boxes indicate that no test data is available for that property and condition.

* Data is as measured rather than normalized

** indicates the Stat17 B-basis value is greater than 90% of the mean value.

Table 3-2 : NCAMP Recommended B-basis values for laminate test data

3.2 Lamina and Laminate Summary Tables

Material: Cytec Cycom® 5250-5 T650 Unitape NMS 226/1 Material Specification	Cytec Cycom® 5250-5 T650 Unitape Lamina Properties Summary		
Fiber: 12K T650 unitape	Resin: Cytec Cycom® 5250-5		
Tg(dry): 489.14°F	Tg(bone dry): 516.47°F	Tg(wet): 383.30°F	Tg METHOD: DMA (SRM 18-94)
PROCESSING: NCAMP Process Specification 81226 "C" Cure Cycle			

	BATCH 1	BATCH 2	BATCH 3		
Date of fiber manufacture	5/21/07	9/20/06	3/8/06	Date of testing	8/19/09 to 10/28/10
Date of resin manufacture	11/26/07	8/29/07	10/16/07	Date of data submittal	November 2010
Date of prepreg manufacture	11/26/07	8/29/07	10/16/07	Date of analysis	7/25/11 to 5/30/12
Date of composite manufacture	3/28/08				

LAMINA MECHANICAL PROPERTY B-BASIS SUMMARY												
Data reported: As measured followed by normalized values in parentheses, normalizing tply: 0.0055 in												
Values shown in shaded boxes do not meet CMH17 Rev G requirements and are estimates only												
These values may not be used for certification unless specifically allowed by the certifying agency												
	CTD			RTD			ETD			ETW ⁽¹⁾		
	B-Basis	Modified CV B-basis	Mean	B-Basis	Modified CV B-basis	Mean	B-Basis	Modified CV B-basis	Mean	B-Basis	Modified CV B-basis	Mean
F₁^{tu} (ksi)	224.89	249.59	281.33	277.37	269.78	301.53				286.81	279.22	310.96
from UNT0*	(230.53)	(244.58)	(275.82)	(270.37)	(264.73)	(295.97)				(241.57)	(273.43)	(304.66)
F₁^{tu} (ksi)	293.78	281.18	314.46	296.54	283.93	317.21				296.20	283.40	317.18
from LT	(289.60)	(278.42)	(311.53)	(292.41)	(281.23)	(314.34)				(292.22)	(280.88)	(314.48)
E₁^t (Msi)			20.49			20.48						20.90
V₁₂^t			0.308			0.304						0.388
F₂^{tu} (ksi)	8.82	NA	10.53	9.24	NA	11.00				2.01	NA	2.91
E₂^t (Msi)			1.44			1.35						0.59
F₁^{cu} (ksi)	183.41	NA	224.01	234.47	227.08	249.41	192.29	184.91	207.23	138.71	131.32	153.64
from UNCO*	(182.02)	NA	(221.42)	(230.73)	223.46	(245.47)	(191.40)	184.13	(206.14)	(138.06)	(130.79)	(152.80)
E₁^c (Msi)			18.10			18.48			18.26			18.68
(Msi)			(17.97)			(18.26)			(18.16)			(18.49)
F₂^{cu} (ksi)	44.85	43.14	48.89	36.51	34.73	39.21				16.09	15.47	17.54
E₂^c (Msi)			1.54			1.41						0.85
F₁₂^{s5%} (ksi)	NA	NA	NA	NA	NA	NA				3.58	3.50	4.05
F₁₂^{smax} (ksi)	15.48	14.30	16.15	NA	NA	NA				NA	NA	NA
F₁₂^{s0.2%} (ksi)	10.59	9.87	11.14	8.32	7.66	8.61				1.74	1.73	2.03
G₁₂^s (Msi)			0.83			0.72						0.20
SBS (ksi)	17.13	16.29	18.31	14.61	14.05	15.82	8.00	NA	8.23	5.22	5.04	5.73
UNT0 (ksi)	120.24	133.70	150.41	147.92	143.86	160.58				147.20	143.15	159.86
(ksi)	(123.33)	(131.11)	(147.56)	(144.07)	141.26	(157.71)				(124.22)	(140.22)	(156.67)
(Msi)			10.72			10.88						11.11
(Msi)			(10.51)			(10.68)						(10.89)
UNCO (ksi)	71.41	NA	87.22	90.05	87.23	95.65	72.65	69.83	78.25	50.22	47.40	55.83
(ksi)	(70.95)	NA	(86.30)	(88.74)	85.98	(94.29)	(72.21)	69.44	(77.75)	(50.02)	(47.26)	(55.57)
(Msi)			6.94			7.05			6.90			6.57
(Msi)			(6.87)			(6.95)			(6.85)			(6.51)

* Derived from cross-ply using back-out factor

Note (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Table 3-3: Summary of Test Results for Lamina Data

Material:	Cytec Cycom® 5250-5 T650 Unitape NMS 226/1 Material Specification	Cytec Cycom® 5250-5 T650 Unitape Laminate Properties Summary	
Fiber:	12K T650 unitape	Resin: Cytec Cycom® 5250-5	
Tg(dry):	489.14°F	Tg(bone dry): 516.47°F	Tg(wet): 383.30°F
PROCESSING:	NCAMP Process Specification 81226 "C" Cure Cycle		
Tg METHOD: DMA (SRM 18-94)			

	BATCH 1	BATCH 2	BATCH 3		
Date of fiber manufacture	5/21/07	9/20/06	3/8/06	Date of testing	8/19/09 to 10/28/10
Date of resin manufacture	11/26/07	8/29/07	10/16/07	Date of data submittal	November 2010
Date of prepreg manufacture	11/26/07	8/29/07	10/16/07	Date of analysis	7/25/11 to 5/30/12
Date of composite manufacture	3/28/08				

LAMINATE MECHANICAL PROPERTY B-BASIS SUMMARY													
Data reported: As measured followed by normalized values in parentheses, normalizing tply: 0.0055 in													
Values shown in shaded boxes do not meet CMH17 Rev G requirements and are estimates only													
These values may not be used for certification unless specifically allowed by the certifying agency													
Test	Property	Layup:			Quasi Isotropic 25/50/25			"Soft" 10/80/10			"Hard" 50/40/10		
		Test Condition	Unit	B-value	Mod. CV B-value	Mean	B-value	Mod. CV B-value	Mean	B-value	Mod. CV B-value	Mean	
OHT (normalized)	Strength	CTD	ksi	50.59	47.74	53.46	43.75	40.82	45.12	72.31	68.58	77.39	
		RTD	ksi	52.91	50.06	55.79	42.22	39.29	43.59	76.74	73.01	81.83	
		ETW ⁽¹⁾	ksi	53.42	50.57	56.30	30.73	30.06	34.30	85.97	82.28	91.01	
OHC (normalized)	Strength	RTD	ksi	48.33	44.14	49.84	42.38	40.04	43.86	55.96	58.69	64.89	
		ETW ⁽¹⁾	ksi	33.57	32.00	36.04	24.10	21.78	25.57	42.21	39.94	46.16	
UNT (normalized)	Strength Modulus	CTD	ksi	93.09	87.17	97.36	67.49	63.17	69.63	152.73	145.19	162.57	
		Msi	—	—	7.52	—	—	5.01	—	—	11.89		
	RTD	ksi	96.17	90.26	100.45	64.27	59.95	66.41	159.30	151.77	169.15		
Msi	—	—	7.50	—	—	4.85	—	—	—	11.85			
Strength Modulus	ETW ⁽¹⁾	ksi	92.64	86.72	96.92	46.61	42.30	48.76	159.89	152.39	169.70		
	Msi	—	—	7.21	—	—	3.80	—	—	11.46			
UNC (normalized)	Strength Modulus	RTD	ksi	86.46	84.91	93.98	66.86	65.90	71.89	126.14	123.30	134.87	
		Msi	—	—	7.05	—	—	4.66	—	—	10.85		
Strength Modulus	ETW ⁽¹⁾	ksi	48.66	47.12	56.10	26.76	27.87	33.83	50.57	55.93	67.36		
	Msi	—	—	6.39	—	—	3.55	—	—	10.34			
FHT (normalized)	Strength	CTD	ksi	56.60	55.66	62.25	48.96	47.17	52.01	76.96	73.64	82.66	
		RTD	ksi	59.33	55.92	62.51	46.12	44.33	49.18	82.64	79.34	88.31	
		ETW ⁽¹⁾	ksi	50.22	53.23	59.79	32.70	30.92	35.74	80.13	76.84	85.77	
FHC (normalized)	Strength	RTD	ksi	57.72	67.89	77.29	52.23	53.55	58.68	80.78	76.84	87.16	
		ETW ⁽¹⁾	ksi	47.86	45.28	51.12	32.13	29.61	34.74	37.41	52.93	61.27	
Single Shear Bearing (normalized)	2% Offset Strength	RTD	ksi	107.43	104.44	119.70	105.59	101.05	114.09	107.42	105.08	116.79	
		ETW ⁽¹⁾	ksi	57.64	70.65	81.71	45.20	64.01	79.40	68.17	65.83	77.54	
	Ultimate Strength	RTD	ksi	135.78	132.74	147.65	146.84	NA	153.33	132.81	129.46	143.52	
ETW	ksi	89.33	86.29	101.20	94.76	NA	100.43	87.24	83.88	97.94			
SBS1 (as measured)	Strength	RTD	ksi	10.46	10.25	11.84	—	—	—	—	—	—	
		ETW ⁽¹⁾	ksi	5.54	5.09	5.74	—	—	—	—	—	—	
ILT (as measured)	Strength	CTD	ksi	—	—	16.00	—	—	—	—	—	—	
		RTD	ksi	—	—	16.11	—	—	—	—	—	—	
		ETW	ksi	—	—	3.56	—	—	—	—	—	—	
CBS (as measured)	Strength	CTD	lb	—	—	524.13	—	—	—	—	—	—	
		RTD	lb	—	—	526.59	—	—	—	—	—	—	
		ETW	lb	—	—	119.61	—	—	—	—	—	—	
CAI (normalized)	Strength	RTD	ksi	—	—	21.10	—	—	—	—	—		

Note (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Table 3-4: Summary of Test Results for Laminate Data

4. Test Results, Statistics, Basis Values and Graphs

Test data for fiber dominated properties was normalized according to nominal cured ply thickness. Both normalized and as measured statistics were included in the tables, but only the normalized data values were graphed. Test failures, outliers and explanations regarding computational choices were noted in the accompanying text for each test.

For organic matrix composites, the typical rule of thumb is to maintain a 50 degree margin between the materials maximum operating limit (MOL) and its wet glass transition temperature. Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

All individual specimen results are graphed for each test by batch and environmental condition with a line indicating the recommended basis values for each environmental condition. The data is jittered (moved slightly to the left or right) in order for all specimen values to be clearly visible. The strength values are always graphed on the vertical axis with the scale adjusted to include all data values and their corresponding basis values. The vertical axis may not include zero. The horizontal axis values will vary depending on the data and how much overlapping of there was of the data within and between batches. When there was little variation, the batches were graphed from left to right and the environmental conditions were identified by the shape and color of the symbol used to plot the data. Otherwise, the environmental conditions were graphed from left to right and the batches were identified by the shape and color of the symbol.

When a dataset fails the Anderson-Darling k-sample (ADK) test for batch-to-batch variation an ANOVA analysis is required. In order for B-basis values computed using the ANOVA method, data from five batches is required. Since this qualification dataset has only three batches, the basis values computed using ANOVA are considered estimates only. However, the basis values resulting from the ANOVA method using only three batches may be overly conservative. The ADK test is performed again after a transformation of the data according to the assumptions of the modified CV method (see section 2.1.4 for details). If the dataset still passes the ADK test at this point, modified CV basis values are provided. If the dataset does not pass the ADK test after the transformation, estimates may be computed using the modified CV method per the guidelines in CMH-17 Rev G Vol 1 Chapter 8 section 8.3.10.

4.1 Longitudinal (0°) Tension Properties (LT)

The Longitudinal Tension data was normalized so both normalized and as measured statistics are provided. The longitudinal tension strengths are computed two different ways; directly from LT specimens and indirectly (derived) from UNT0 specimens via equation 64 specified in section 2.5. The results of both are presented here.

For the datasets computed from the UNT0 specimens, the as measured CTD dataset and the normalized CTD and ETW datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable for the normalized data. The RTD and ETW conditions could be pooled for the as measured data.

CMH-17 Rev G guidelines required using the ANOVA analysis when a dataset fails the ADK test. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, all three passed the ADK test and so modified CV basis values are provided. There were no other test failures so pooling was acceptable to compute the modified CV basis values.

There were no outliers. Statistics and basis values are given for strength data in Table 4-1 and for the modulus data in Table 4-2. The data and the B-basis values are shown graphically in Figure 4-1.

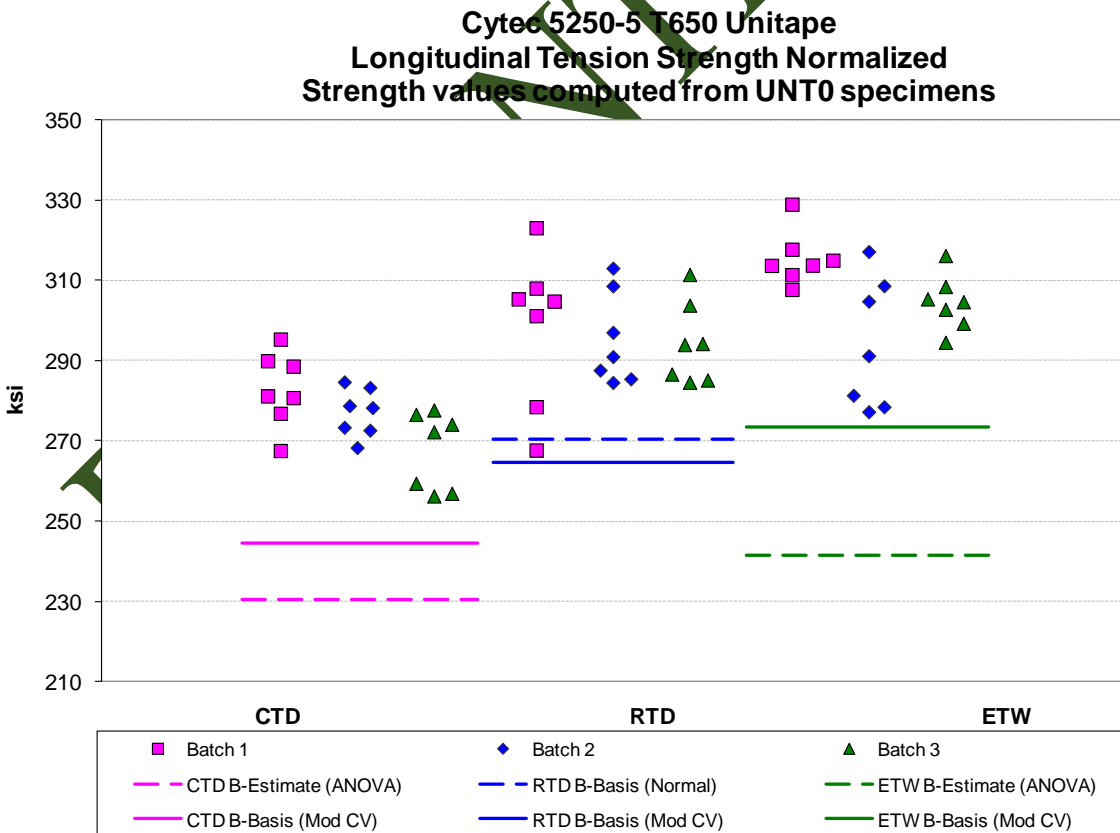


Figure 4-1 Batch plot for LT strength computed from UNT0 specimens normalized

Computed from UNT0 specimens using back-out formula						
Normalized			As Measured			
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	275.82	295.97	304.66	281.33	301.53	310.96
Stdev	10.29	13.44	13.62	11.12	14.15	13.07
CV	3.73	4.54	4.47	3.95	4.69	4.20
Mod CV	6.00	6.27	6.23	6.00	6.35	6.10
Min	256.23	267.67	277.21	258.34	272.85	286.02
Max	295.32	323.07	328.95	304.26	324.25	335.82
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21
Basis Values and Estimates						
B-basis Value		270.37			277.37	286.81
B-Estimate	230.53		241.57	224.89		
A-estimate	198.20	252.13	196.54	184.61	260.76	270.20
Method	ANOVA	Normal	ANOVA	ANOVA	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	244.58	264.73	273.43	249.59	269.78	279.22
A-estimate	223.48	243.63	252.33	228.15	248.34	257.77
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-1: Statistics and Basis values for LT strength from UNT0

Longitudinal Tension Modulus Statistics						
Normalized			As Measured			
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	20.30	20.30	20.72	20.49	20.48	20.90
Stdev	0.56	0.39	0.89	0.56	0.25	0.96
CV	2.77	1.93	4.32	2.75	1.21	4.59
Mod CV	6.00	6.00	6.16	6.00	6.00	6.30
Min	18.90	19.35	19.66	18.96	20.09	19.74
Max	21.20	21.20	23.21	21.26	20.96	23.68
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	19	21	21	19

Table 4-2: Statistics from LT modulus

For completeness and for comparison purposes, the LT strength values are given in Table 4-3. The data and the B-basis values are shown graphically in Figure 4-2. The ETW strength values from the LT specimens, both normalized and as measured, failed the test for normality, but the pooled datasets were sufficiently close to normal that pooling was acceptable. There was one outlier. The lowest value in the ETW condition was an outlier for both batch two and the ETW condition. It was an outlier for both the as measured and the normalized datasets.

**Cytec 5250-5 T650 Unitape
Longitudinal Tension Strength Normalized
Strength values from LT specimens**

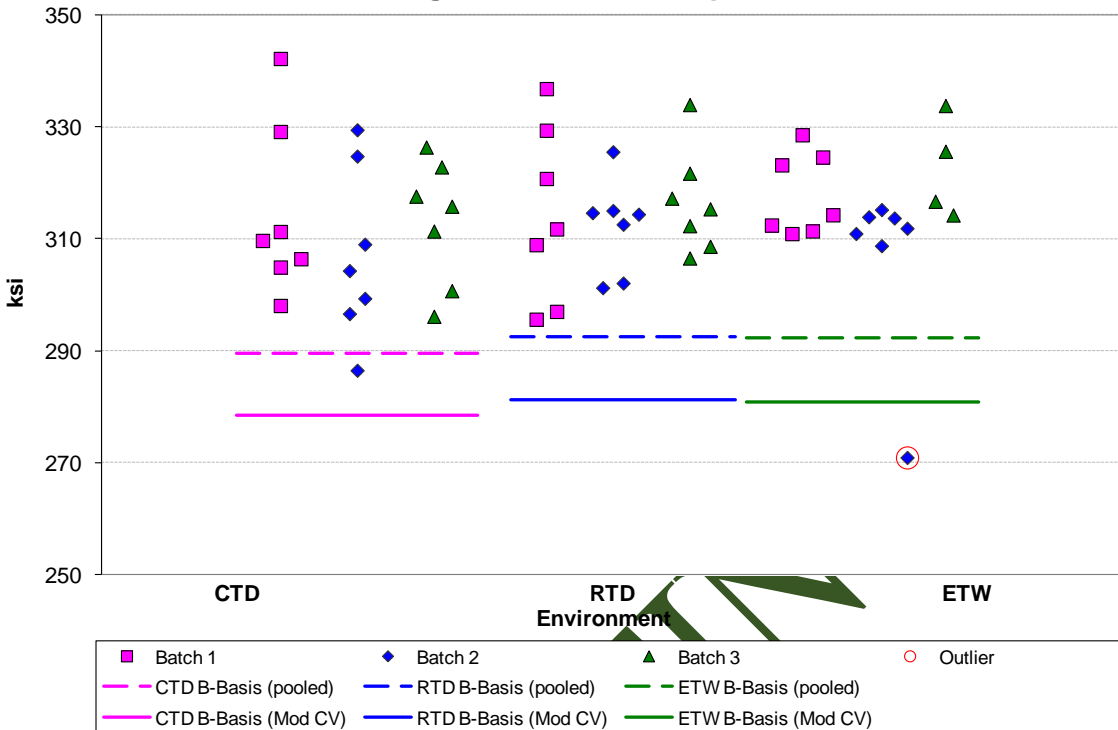


Figure 4-2 Batch plot for LT strength normalized

Longitudinal Tension Strength Basis Values and Statistics Computed from LT specimens						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	311.53	314.34	314.48	314.46	317.21	317.18
Stdev	13.81	11.08	12.96	13.84	9.42	12.13
CV	4.43	3.52	4.12	4.40	2.97	3.82
Mod CV	6.22	6.00	6.06	6.20	6.00	6.00
Min	286.48	295.60	270.92	291.11	299.23	276.47
Max	342.17	336.79	333.77	343.87	332.56	333.90
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	18	21	21	18
Basis Values and Estimates						
B-basis Value	289.60	292.41	292.22	293.78	296.54	296.20
A-estimate	274.75	277.56	277.43	279.79	282.54	282.26
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	278.42	281.23	280.88	281.18	283.93	283.40
A-estimate	256.01	258.82	258.55	258.65	261.40	260.96
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-3: Statistics and Basis values for LT strength

4.2 Transverse (90°) Tension Properties (TT)

Transverse Tension data is not normalized for unidirectional tape. Pooling was not acceptable due to a failure of Levene's test for equality of variance. Modified CV basis value as are not provided because the CV for all conditions was above 8%, so the modified CV approach would not result in any changes.

There were no outliers. Statistics, basis values and estimates are given for strength data as measured in Table 4-4 and for the modulus data as measured in Table 4-5. The data and the B-basis values and B-estimates are shown graphically in Figure 4-3.

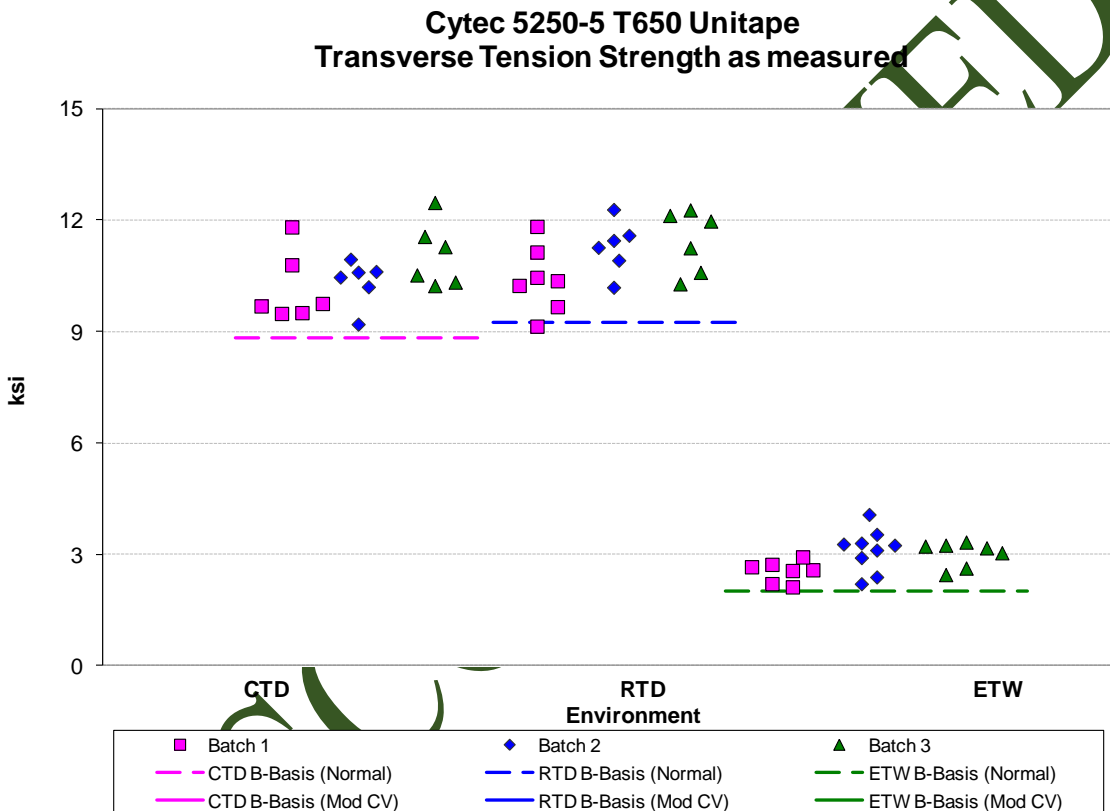


Figure 4-3: Batch Plot for TT strength as measured

Transverse Tension Strength Basis Values and Statistics			
Env	CTD	RTD	ETW
Mean	10.53	11.00	2.91
Stdev	0.87	0.90	0.48
CV	8.23	8.22	16.61
Mod CV	8.23	8.22	16.61
Min	9.20	9.14	2.12
Max	12.48	12.29	4.07
No. Batches	3	3	3
No. Spec.	18	19	23
Basis Values and Estimates			
B-basis Value	8.82	9.24	2.01
A-estimate	7.60	7.99	1.36
Method	Normal	Normal	Normal

Table 4-4: Statistics and Basis Values for TT Strength data as measured

Transverse Tension Modulus Statistics			
Env	CTD	RTD	ETW
Mean	1.44	1.35	0.59
Stdev	0.02	0.02	0.05
CV	1.58	1.54	8.19
Mod CV	6.00	6.00	8.19
Min	1.40	1.32	0.51
Max	1.47	1.39	0.73
No. Batches	3	3	3
No. Spec.	21	20	23

Table 4-5: Statistics from TT Modulus data as measured

4.3 Longitudinal (0°) Compression Properties (LC)

The Longitudinal Compression data was normalized so both normalized and as measured statistics are provided. The strength values for 0° properties are computed via the formulas specified in section 2.5. For the CTD, RTD and ETW condition, equation 64 was used. For the ETD values, a different formula was required because there were no specimens tested in the ETD condition for the transverse compression and the mean modulus value from the ETD condition for transverse compression is required by the formula that was used for the CTD, RTD and ETW conditions. Therefore, the ETD strength values were computed using equation 65.

This data could not be pooled across all four environments because the pooled dataset failed both the normality test and Levene's test for equality of variance. When the CTD data was removed from the pooled dataset, the RTD, ETD and ETW datasets met all requirements for pooling.

Modified CV basis values could not be provided for the CTD dataset due to the CV being above 8%.

There was one outlier. The highest value from batch one of the normalized ETD dataset was an outlier for that condition. It was an outlier only for the normalized dataset and only for the ETD condition. It was not an outlier for batch one. It was retained for this analysis.

Statistics and B-estimates are given for strength data in Table 4-6 and for the modulus data in Table 4-7. The normalized data and the B-estimates are shown graphically in Figure 4-4.

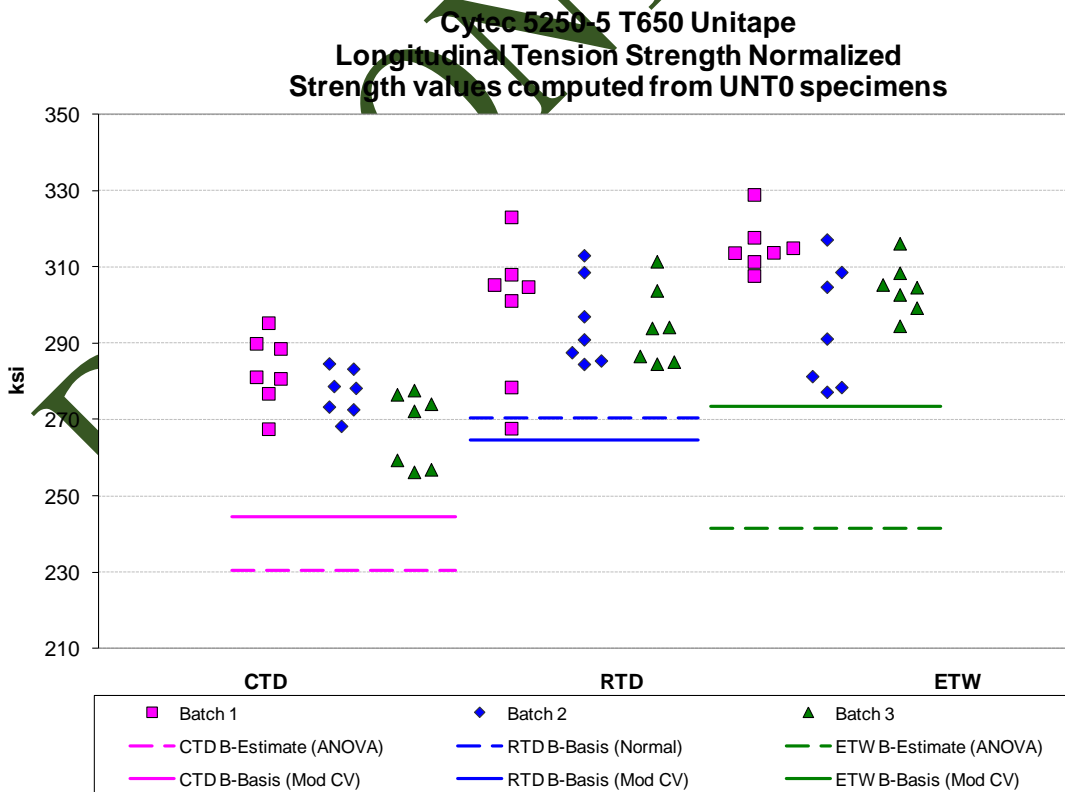


Figure 4-4 Batch plot for LC strength normalized

Longitudinal Compression Strength Basis Values and Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	221.42	245.47	206.14	152.80	224.01	249.41	207.23	153.64
Stdev	20.89	8.20	9.93	7.22	21.53	8.05	9.71	8.05
CV	9.44	3.34	4.82	4.73	9.61	3.23	4.68	5.24
Mod CV	9.44	6.00	6.41	6.36	9.61	6.00	6.34	6.62
Min	185.92	226.03	194.82	139.95	187.14	230.00	194.50	139.20
Max	257.20	260.50	233.66	167.78	261.01	262.65	233.34	170.82
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	22	21	21	21	22	21	21	21
Basis Value Estimates								
B-basis Value	182.02	230.73	191.40	138.06	183.41	234.47	192.29	138.71
A-Estimate	153.87	220.77	181.44	128.10	154.40	224.38	182.20	128.62
Method	Normal	pooled	pooled	pooled	Normal	pooled	pooled	pooled
Modified CV Basis Value Estimates								
B-basis Value	NA	223.46	184.13	130.79	NA	227.08	184.91	131.32
A-Estimate	NA	208.60	169.26	115.93	NA	212.00	169.83	116.24
Method	NA	pooled	pooled	pooled	NA	pooled	pooled	pooled

Table 4-6: Statistics and Basis Values for LC strength derived from UNCO

Longitudinal Compression Modulus Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	17.97	18.26	16.16	18.49	18.10	18.48	18.26	18.68
Stdev	0.91	0.27	0.42	0.52	0.89	0.40	0.39	0.65
CV	5.07	1.48	2.30	2.79	4.89	2.19	2.14	3.46
Mod CV	6.53	6.00	6.00	6.00	6.45	6.00	6.00	6.00
Min	15.12	17.65	17.53	17.69	15.40	17.87	17.65	17.74
Max	19.70	18.74	18.89	19.48	20.21	19.35	18.77	20.13
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21	21	21

Table 4-7: Statistics from LC modulus

4.4 Transverse (90°) Compression Properties (TC)

Transverse Compression data is not normalized for unidirectional tape. Pooling was not acceptable due to a failure of Levene's test for equality of variance.

There were no outliers. Statistics, basis values and estimates are given for strength data in Table 4-8 and for the modulus data in Table 4-9. The data, B-estimates, and B-basis values are shown graphically in Figure 4-5.

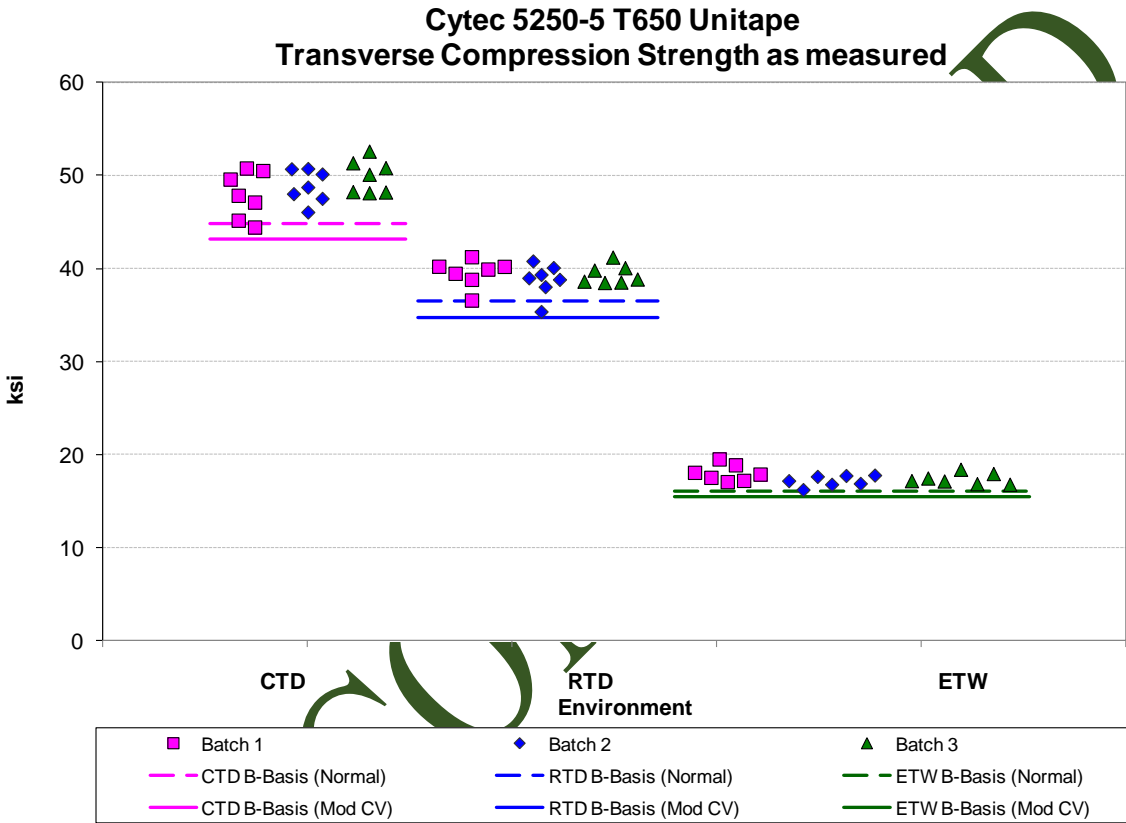


Figure 4-5: Batch Plot for TC strength as measured

Transverse Compression Strength Basis Values and Statistics			
Env	CTD	RTD	ETW
Mean	48.89	39.21	17.54
Stdev	2.12	1.41	0.76
CV	4.33	3.61	4.34
Mod CV	6.17	6.00	6.17
Min	44.44	35.36	16.22
Max	52.59	41.24	19.51
No. Batches	3	3	3
No. Spec.	21	21	21
Basis Values and Estimates			
B-basis Value	44.85	36.51	16.09
A-estimate	41.98	34.59	15.05
Method	Normal	Normal	Normal
Modified CV Basis Values and Estimates			
B-basis Value	43.14	34.73	15.47
A-estimate	39.05	31.53	14.00
Method	Normal	Normal	Normal

Table 4-8: Statistics and Basis Values for TC Strength data

Transverse Compression Modulus Statistics			
Env	CTD	RTD	ETW
Mean	1.54	1.41	0.85
Stdev	0.05	0.06	0.07
CV	3.37	4.02	8.48
Mod CV	6.90	6.01	8.48
Min	1.46	1.28	0.74
Max	1.69	1.54	1.03
No. Batches	3	3	3
No. Spec.	21	23	20

Table 4-9: Statistics from TC Modulus data

4.5 In-Plane Shear Properties (IPS)

In-Plane Shear data is not normalized. Maximum strength data refers to the peak shear strength before 5% strain and is available only for the CTD condition. Strength at 5% strain data is available only for the ETW condition.

The 0.2% offset strength CTD dataset failed the Anderson Darling k-sample test (ADK test) for batch to batch variability. CMH-17 Rev G guidelines required using the ANOVA analysis when a dataset fails the ADK test. With fewer than 5 batches, this is considered an estimate.

When this dataset was transformed according to the assumptions of the modified CV method, it passed the ADK test and so modified CV basis values are provided. The pooled dataset for 0.2% offset strength did not pass the normality test or Levene's test, so pooling was not appropriate.

There were three outliers, all in the ETW condition datasets. The highest value in the 0.2% offset strength ETW dataset was an outlier and the highest values in both batch one and batch three strength at 5% strain ETW dataset were outliers. All three outliers were outliers only for their respective batches, not the ETW condition. All three outliers were retained for this analysis.

Statistics, estimates and basis values are given for the strength data in Table 4-10 and modulus data in Table 4-11. The data, B-estimates and B-basis values are shown graphically in Figure 4-6.

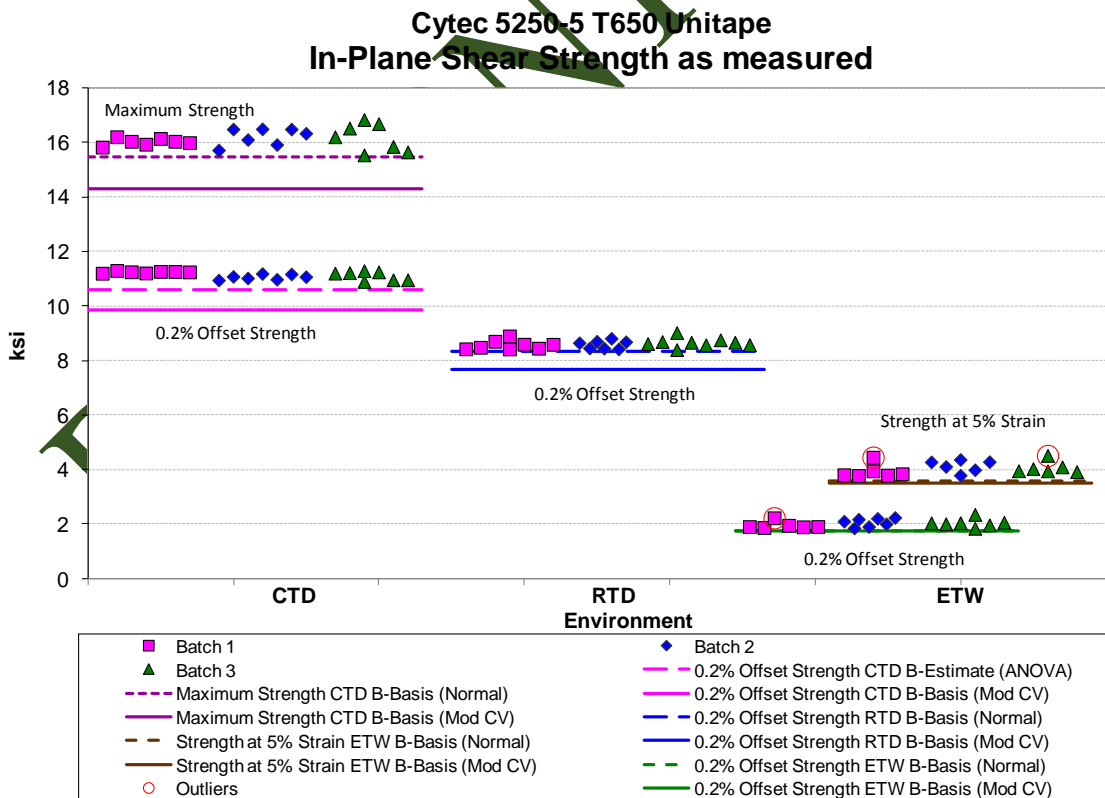


Figure 4-6: Batch plot for IPS strength as measured

In-Plane Shear Strength Basis Values and Statistics					
	Maximum Strength	Strength at 5%	0.2% Offset Strength		
Env	CTD	ETW	CTD	RTD	ETW
Mean	16.15	4.05	11.14	8.61	2.03
Stdev	0.35	0.24	0.13	0.16	0.15
CV	2.16	5.84	1.18	1.87	7.26
Mod CV	6.00	6.92	6.00	6.00	7.63
Min	15.54	3.78	10.90	8.40	1.84
Max	16.84	4.52	11.30	9.02	2.35
No. Batches	3	3	3	3	3
No. Spec.	21	18	21	24	20
Basis Values and Estimates					
B-basis Value	15.48	3.58		8.32	1.74
B-estimate			10.59		
A-estimate	15.01	3.25	10.19	8.19	1.54
Method	Normal	Normal	ANOVA	Normal	Normal
Modified CV Basis Values and Estimates					
B-basis Value	14.30	3.50	9.87	7.66	1.73
A-estimate	12.99	3.11	8.96	6.97	1.52
Method	Normal	Normal	Normal	Normal	Normal

Table 4-10: Statistics and Basis Values for IPS Strength data

In Plane Shear Modulus Statistics			
Env	CTD	RTD	ETW
Mean	0.83	0.72	0.20
Stdev	0.01	0.01	0.02
CV	1.78	1.49	8.19
Mod CV	6.00	6.00	8.19
Min	0.80	0.70	0.18
Max	0.85	0.75	0.24
No. Batches	3	3	3
No. Spec.	21	24	20

Table 4-11: Statistics from IPS Modulus data

4.6 Short Beam Strength (SBS)

The Short Beam Strength data is not normalized. The RTD data failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When the RTD data was transformed according to the assumptions of the modified CV method, it did pass the ADK test and so the modified CV B-basis value is provided.

The pooled dataset did not pass either the normality test or Levene's test for equality of variation, so pooling across environments remained unacceptable for the modified CV basis values. The ETD dataset did not fit any of the three tested distributions sufficiently well, so the non-parametric approach was required.

There were four outliers in the SBS data, one in each condition. The lowest value in batch one of the CTD dataset was an outlier for batch one only, not for the CTD condition. The highest value in batch two of the RTD data was an outlier for batch two but not for the RTD condition. The highest value in batch one of the ETD data was an outlier for both batch one and for the ETD condition. The highest value in batch two of the ETW data was an outlier for both batch two and for the ETW condition. All four outliers were retained for this analysis.

Statistics and basis values are given for SBS data in Table 4-12. The data and the B-basis values are shown graphically in Figure 4-7.

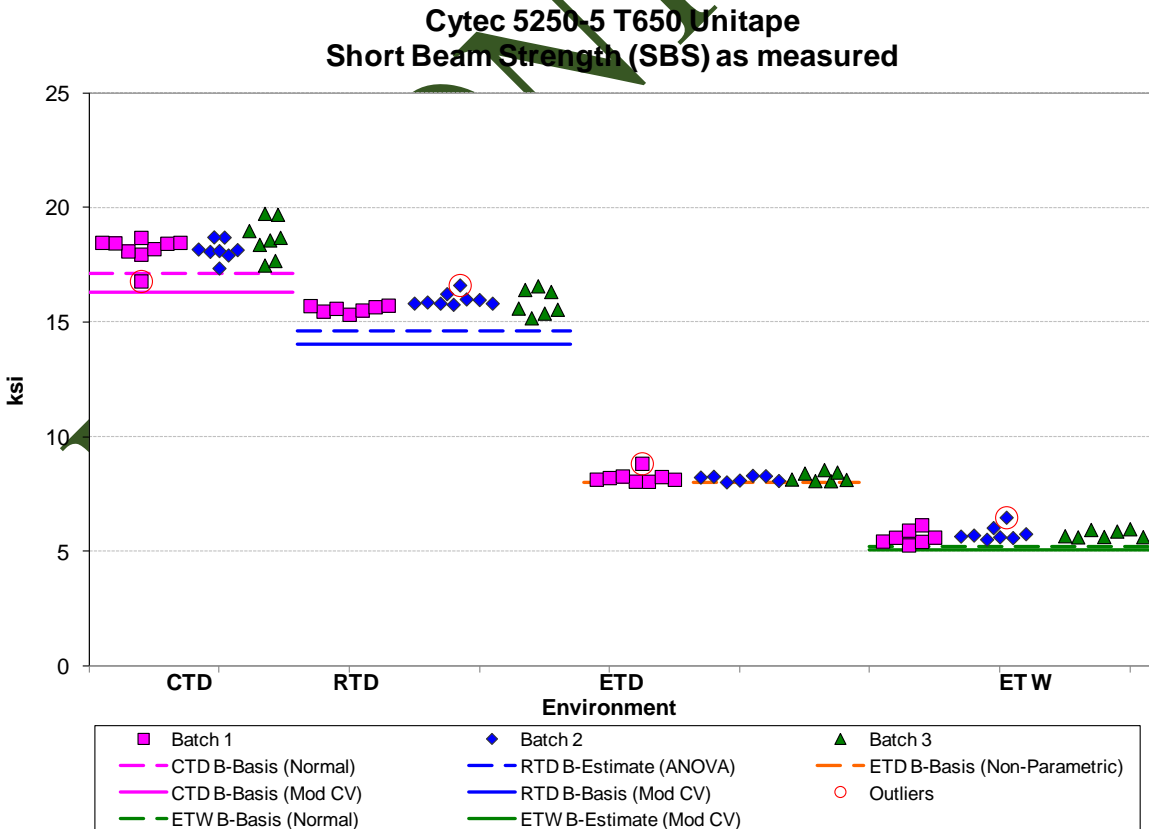


Figure 4-7: Batch plot for SBS as measured

Short Beam Strength (ksi)				
Env	CTD	RTD	ETD	ETW
Mean	18.31	15.82	8.23	5.73
Stdev	0.64	0.39	0.19	0.27
CV	3.52	2.45	2.36	4.70
Mod CV	6.00	6.00	6.00	6.35
Min	16.78	15.18	8.02	5.27
Max	19.73	16.61	8.83	6.48
No. Batches	3	3	3	3
No. Spec.	25	23	22	22
Basis Values and Estimates				
B-basis Value	17.13		8.00	5.22
B-Estimate		14.61		
A-estimate	16.28	13.74	7.10	4.86
Method	Normal	ANOVA	Non-Parametric	Normal
Modified CV Basis Values and Estimates				
B-basis Value	16.29	14.05	NA	5.04
A-estimate	14.84	12.78	NA	4.55
Method	Normal	Normal	NA	Normal

Table 4-12: Statistics and Basis Values for SBS data

DISCONTINUED

4.7 Unnotched Tension Properties (UNT0)

The UNT0 data was normalized so both normalized and as measured statistics are provided. The as measured CTD dataset and the normalized CTD and ETW datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, all three passed the ADK test and so modified CV basis values are provided. There were no other test failures so pooling was acceptable for the as measured RTD and ETW datasets and for all three datasets, both normalized and as measured, to compute the modified CV basis values.

There were no outliers. Statistics and basis values are given for strength data in Table 4-13 and for the modulus data in Table 4-14. The normalized data and the B-basis values are shown graphically in Figure 4-8.

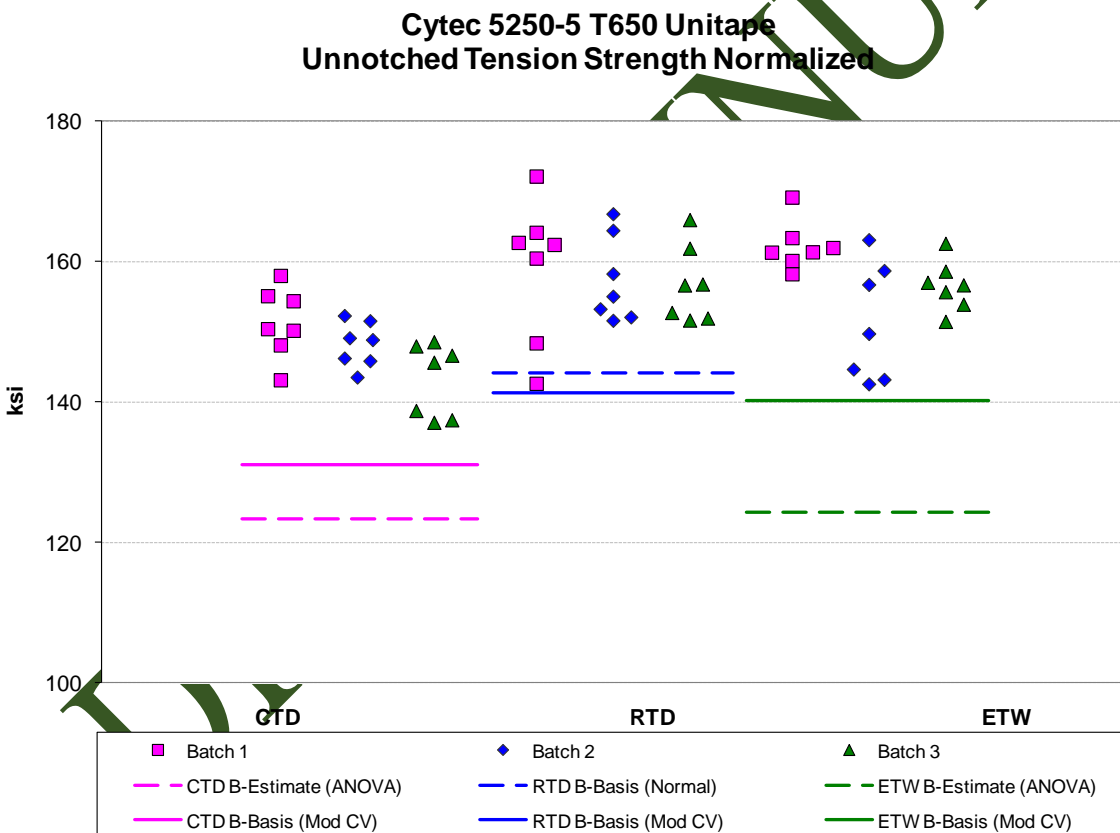


Figure 4-8: Batch Plot for UNT0 strength normalized

Unnotched Tension (UNT0) Strength Basis Values and Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	147.56	157.71	156.67	150.41	160.58	159.86
Stdev	5.51	7.16	7.00	5.95	7.54	6.72
CV	3.73	4.54	4.47	3.95	4.69	4.20
Modified CV	6.00	6.27	6.23	6.00	6.35	6.10
Min	137.08	142.63	142.55	138.12	145.31	147.04
Max	157.99	172.15	169.15	162.68	172.68	172.64
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21
Basis Values and Estimates						
B-basis Value		144.07			147.92	147.20
B-estimate	123.33		124.22	120.24		
A-estimate	106.04	134.35	101.07	98.70	139.21	138.50
Method	ANOVA	Normal	ANOVA	ANOVA	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	131.11	141.26	140.22	133.70	143.86	143.15
A-estimate	119.99	130.14	129.10	122.40	132.57	131.85
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-13: Statistics and Basis Values for UNT0 Strength data

Unnotched Tension (UNT0) Modulus Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	10.51	10.68	10.89	10.72	10.88	11.11
Stdev	0.21	0.21	0.38	0.26	0.28	0.44
CV	2.03	1.94	3.52	2.38	2.59	3.94
Mod CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	10.05	10.42	10.03	10.14	10.38	10.32
Max	10.84	11.09	11.81	11.13	11.48	12.15
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21

Table 4-14: Statistics from UNT0 Modulus data

4.8 Unnotched Compression Properties (UNC0)

The UNC0 data was normalized so both normalized and as measured statistics are provided. This data could not be pooled across all four environments because the pooled dataset failed both the normality test and Levene's test for equality of variance. When the CTD data was removed from the pooled dataset, the RTD, ETD and ETW datasets met all requirements for pooling.

Modified CV basis values could not be provided for the CTD datasets due to the CV being above 8% or for the RTD and ETD datasets due to non-normality.

There was one outlier. The highest value from batch one of the normalized ETD dataset was an outlier for that condition. It was an outlier only for the normalized dataset and only for the ETD condition. It was not an outlier for batch one. It was retained for this analysis.

Statistics and estimates of basis values are given for strength data in Table 4-15 and for the modulus data in Table 4-16. The normalized data and the B-estimates are shown graphically in Figure 4-9.

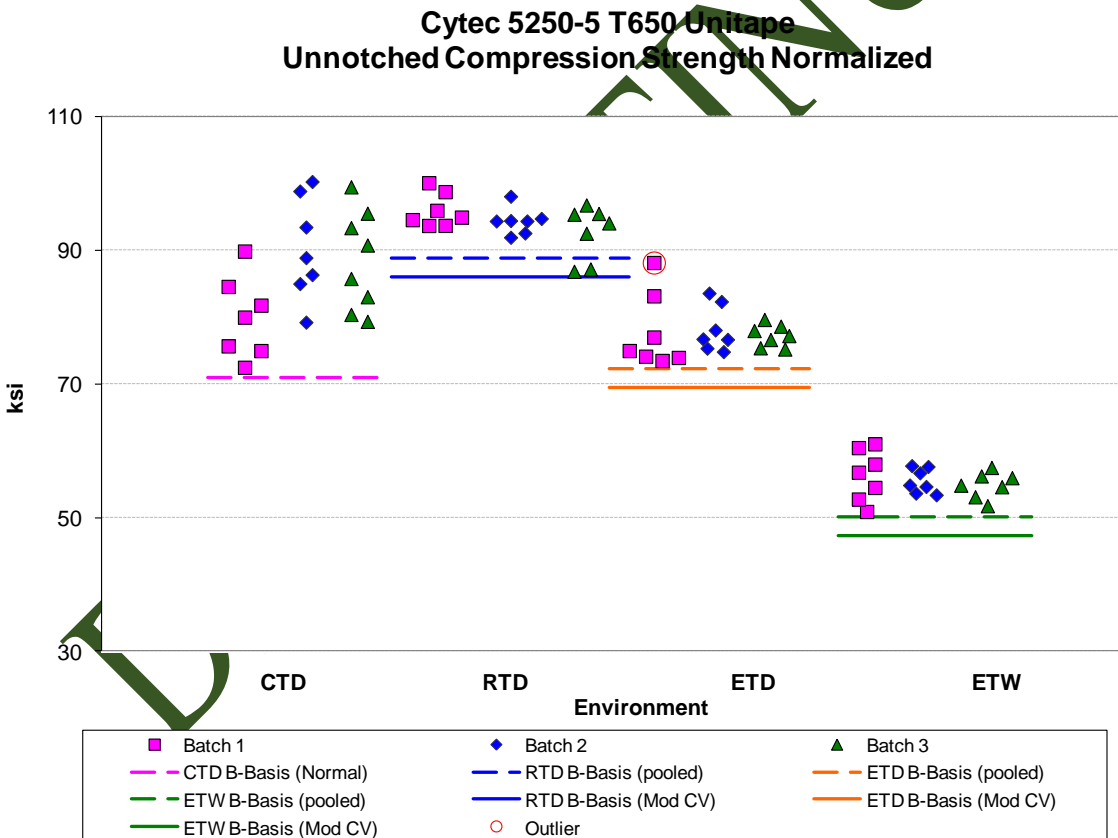


Figure 4-9: Batch Plot for UNC0 strength normalized

Unnotched Compression (UNC0) Strength Basis Values and Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	86.30	94.29	77.75	55.57	87.22	95.65	78.25	55.83
Stdev	8.14	3.15	3.75	2.63	8.38	3.09	3.67	2.93
CV	9.44	3.34	4.82	4.73	9.61	3.23	4.68	5.24
Modified CV	9.44	6.00	6.41	6.36	9.61	6.00	6.34	6.62
Min	72.47	86.82	73.48	50.90	72.86	88.21	73.44	50.58
Max	100.25	100.06	88.13	61.01	101.63	100.73	88.11	62.07
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	22	21	21	21	22	21	21	21
Basis Values and Estimates								
B-basis Value	70.95	88.74	72.21	50.02	71.41	90.05	72.65	50.22
A-estimate	59.98	85.00	68.46	46.28	60.12	86.26	68.86	46.44
Method	Normal	pooled	pooled	pooled	Normal	pooled	pooled	pooled
Modified CV Basis Values and Estimates								
B-basis Value	NA	85.98	69.44	47.26	NA	87.23	69.83	47.40
A-estimate	NA	80.36	63.82	41.64	NA	81.51	64.13	41.71
Method	NA	pooled	pooled	pooled	NA	pooled	pooled	pooled

Table 4-15: Statistics and Basis Values for UNC0 Strength data

Unnotched Compression (UNC0) Modulus Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	6.87	6.95	6.85	6.51	6.94	7.05	6.90	6.57
Stdev	0.26	0.15	0.17	0.14	0.26	0.15	0.16	0.18
CV	3.81	2.12	2.44	2.09	3.77	2.14	2.36	2.80
Mod CV	6.00	6.00	6.00	6.00	6.00	6.00	6.00	6.00
Min	6.38	6.63	6.61	6.28	6.43	6.75	6.60	6.27
Max	7.32	7.18	7.19	6.76	7.44	7.28	7.27	6.87
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	21	21	21	20	21	21	21	20

Table 4-16: Statistics from UNC0 Modulus data

4.9 Quasi Isotropic Unnotched Tension Properties (UNT1)

The UNT1 data was normalized so both normalized and as measured statistics are provided. The as measured ETW dataset failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When this dataset was transformed according to the assumptions of the modified CV method, it passed the ADK test.

The normalized RTD dataset failed the test for normality, but the pooled dataset was sufficiently close to normal and pooling was acceptable. There were no other test failures so pooling was acceptable to compute the normalized basis values and both the normalized and as measured modified CV basis values.

There were two outliers. The lowest value in batch one and the highest value in batch three of the CTD as measured dataset were both outliers for their respective batches, but not for the CTD condition. Both outliers were retained for this analysis.

Statistics, basis values and estimates are given for UNT1 strength data in Table 4-17 and for the modulus data in Table 4-18. The normalized data, B estimates and B -basis values are shown graphically in Figure 4-10

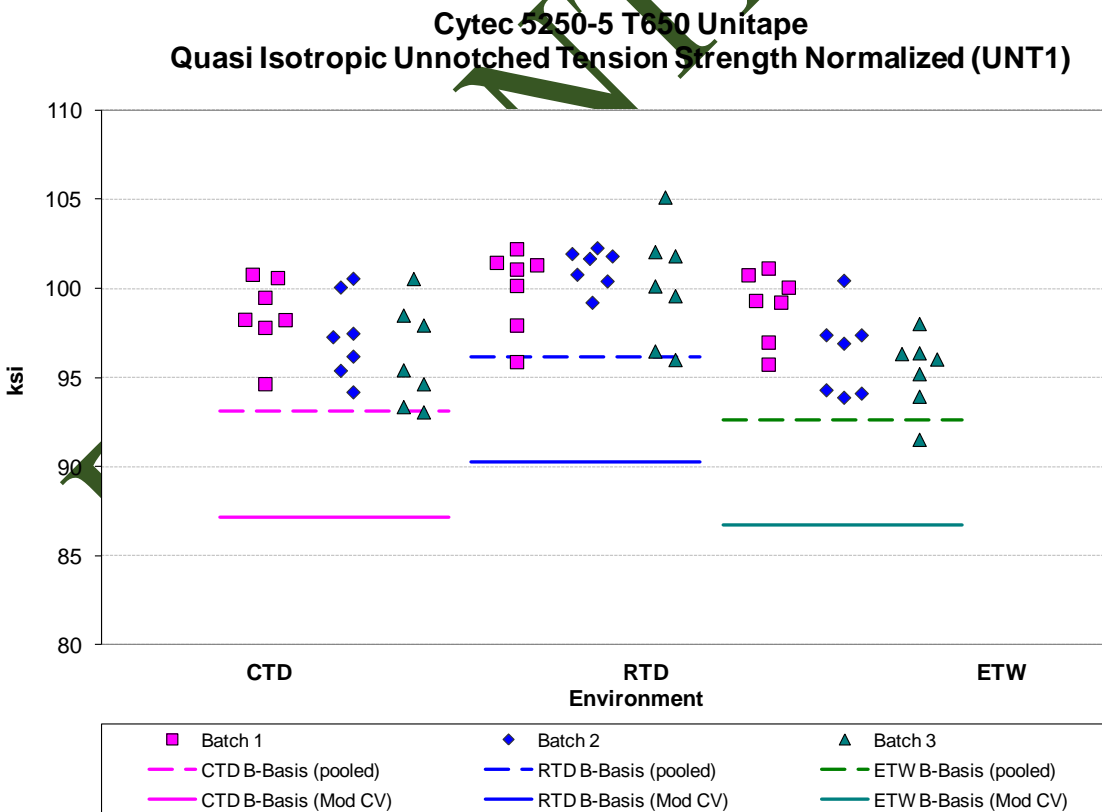


Figure 4-10: Batch Plot for UNT1 strength normalized

Unnotched Tension (UNT1) Strength Basis Values and Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	97.36	100.45	96.92	97.69	101.31	97.96
Stdev	2.51	2.30	2.60	2.95	3.07	2.47
CV	2.58	2.29	2.68	3.02	3.03	2.52
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	93.07	95.89	91.53	93.79	95.43	93.01
Max	100.79	105.12	101.14	104.86	108.92	101.93
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21
Basis Values and Estimates						
B-basis Value	93.09	96.17	92.64	92.35	95.97	
B-estimate						86.14
A-estimate	90.20	93.29	89.75	88.68	92.30	77.70
Method	pooled	pooled	pooled	pooled	pooled	ANOVA
Modified CV Basis Values and Estimates						
B-basis Value	87.17	90.26	86.72	87.42	91.04	87.69
A-estimate	80.28	83.37	79.84	80.49	84.11	80.75
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-17: Statistics and Basis Values for UNT1 Strength data

Unnotched Tension (UNT1) Modulus Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	7.52	7.50	7.21	7.55	7.57	7.28
Stdev	0.10	0.19	0.20	0.14	0.20	0.18
CV	1.38	2.50	2.75	1.85	2.65	2.41
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	7.30	6.86	6.79	7.28	6.91	6.91
Max	7.67	7.81	7.64	7.80	7.92	7.70
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21

Table 4-18: Statistics from UNT1 Modulus data

4.10 "Soft" Unnotched Tension Properties (UNT2)

The UNT2 data was normalized so both normalized and as measured statistics are provided. The normalized RTD dataset failed the test for normality, but the pooled dataset was sufficiently close to normal and pooling was acceptable. There were no other test failures so pooling was acceptable to compute the basis values.

There were three outliers. The smallest value in batch three of the CTD normalized dataset was an outlier for batch three but not for the CTD condition. The largest value in batch three of the RTD normalized dataset was an outlier for the RTD condition, but not for batch three. The smallest value in batch two of the ETW as measured dataset was an outlier for batch two, but not for the ETW condition. All three outliers were retained for this analysis.

Statistics, basis values and estimates are given for UNT2 strength data in Table 4-19 and for the modulus data in Table 4-20. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-11

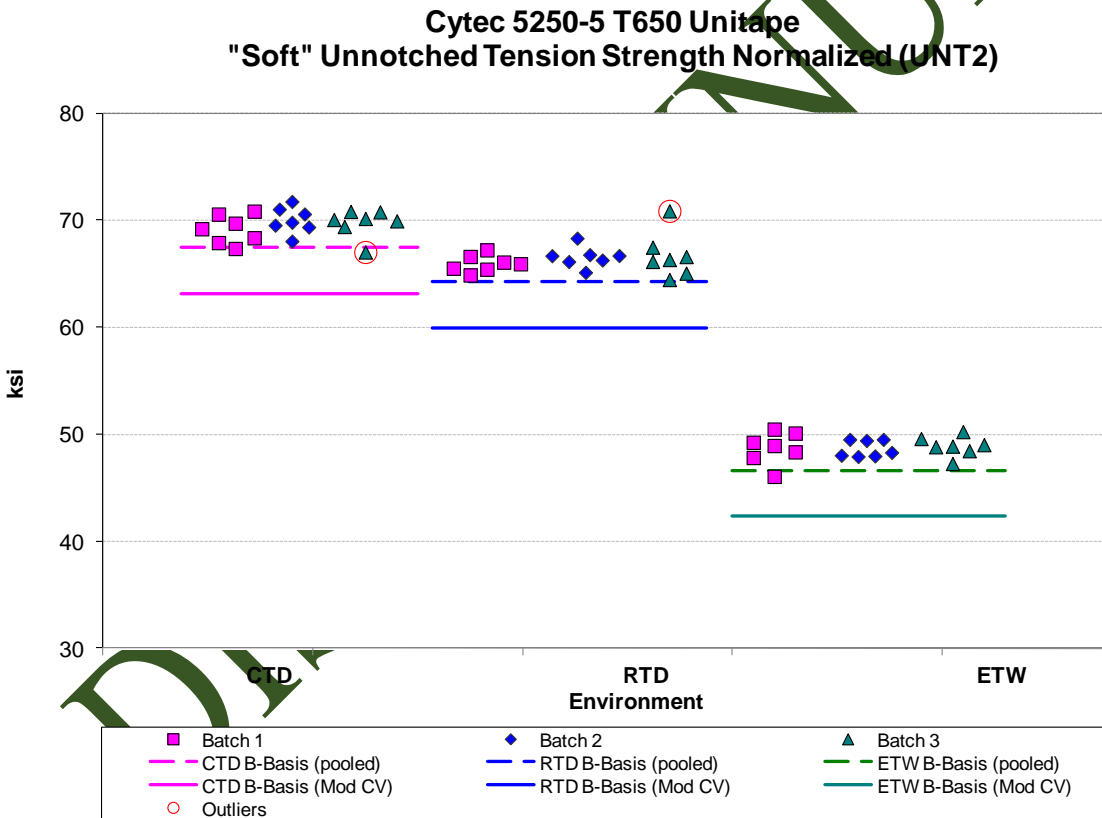


Figure 4-11: Batch Plot for UNT2 strength normalized

Unnotched Tension (UNT2) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	69.63	66.41	48.76	70.26	67.81	49.09
Stdev	1.27	1.37	1.06	1.34	1.78	1.24
CV	1.83	2.07	2.17	1.91	2.62	2.52
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	67.03	64.46	46.06	67.44	64.55	46.14
Max	71.75	70.88	50.47	72.76	71.56	51.32
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21
Basis Values and Estimates						
B-basis Value	67.49	64.27	46.61	67.72	65.26	46.54
A-estimate	66.04	62.82	45.16	66.00	63.54	44.82
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	63.17	59.95	42.30	63.71	61.26	42.54
A-estimate	58.81	55.59	37.93	59.29	56.84	38.12
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-19: Statistics and Basis Values for UNT2 Strength data

Unnotched Tension (UNT2) Modulus Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	5.01	4.85	3.80	5.05	4.95	3.82
Stdev	0.10	0.10	0.12	0.14	0.15	0.14
CV	1.98	2.03	3.19	2.74	3.04	3.76
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	4.87	4.67	3.60	4.87	4.71	3.62
Max	5.18	5.07	4.02	5.32	5.19	4.07
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21

Table 4-20: Statistics from UNT2 Modulus data

Unnotched Tension (UNT3) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	162.57	169.15	169.70	163.60	170.77	171.43
Stdev	6.68	6.56	3.30	6.46	6.96	4.16
CV	4.11	3.88	1.95	3.95	4.07	2.43
Modified CV	6.05	6.00	6.00	6.00	6.04	6.00
Min	154.97	155.66	162.30	152.98	158.47	163.34
Max	176.69	178.93	175.42	177.44	183.82	178.55
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	22	21	21	22
Basis Values and Estimates						
B-basis Value	152.73	159.30	159.89	153.31	160.48	160.18
A-estimate	146.08	152.66	153.24	146.36	153.53	154.25
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	145.19	151.77	152.39	146.08	153.25	153.99
A-estimate	133.46	140.04	140.65	134.25	141.43	142.15
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-21: Statistics and Basis Values for UNT3 Strength data

Unnotched Tension (UNT3) Modulus Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	11.89	11.85	11.46	11.96	11.96	11.58
Stdev	0.36	0.29	0.31	0.31	0.24	0.26
CV	2.99	2.47	2.67	2.57	1.98	2.22
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	11.26	11.37	10.97	11.46	11.64	11.17
Max	12.74	12.71	12.07	12.85	12.71	12.11
No. Batches	3	3	3	3	3	3
No. Spec.	21	22	22	21	22	22

Table 4-22: Statistics from UNT3 Modulus data

4.12 Quasi Isotropic Unnotched Compression Properties (UNC1)

The UNC1 data was normalized so both normalized and as measured statistics are provided. There were no test failures so pooling was acceptable to compute the basis values.

There was one outlier. It was the highest value in batch two of the as measured ETW dataset. It was an outlier only for batch two, not for the ETW condition. It was retained for this analysis.

Statistics, basis values and estimates are given for UNC1 strength data in Table 4-23 and for the modulus data in Table 4-24. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-13.

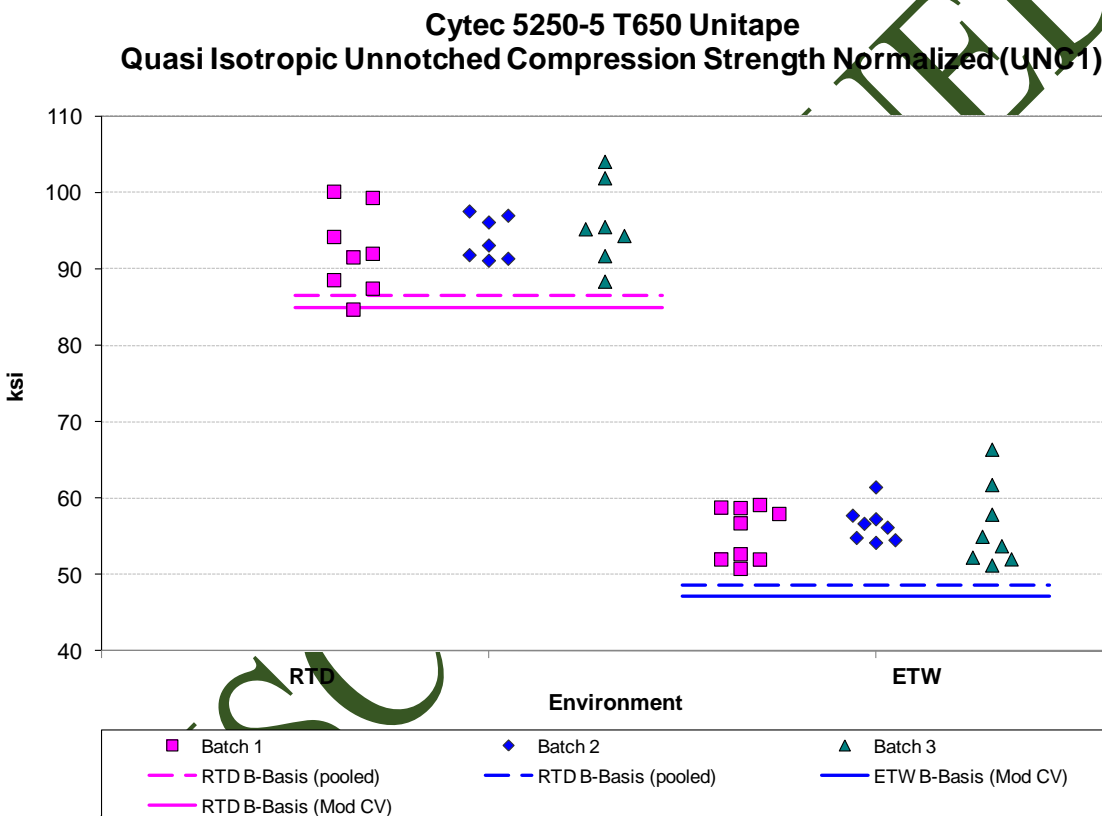


Figure 4-13: Batch plot for UNC1 strength normalized

Unnotched Compression (UNC1) Strength Basis Values and				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	93.98	56.10	95.48	56.61
Stdev	4.81	3.79	5.03	3.77
CV	5.12	6.75	5.27	6.66
Modified CV	6.56	7.37	6.64	7.33
Min	84.74	50.81	86.29	51.41
Max	104.07	66.40	105.53	66.53
No. Batches	3	3	3	3
No. Spec.	22	25	22	25
Basis Values and Estimates				
B-basis Value	86.46	48.66	87.76	48.97
A-estimate	81.29	43.47	82.46	43.65
Method	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates				
B-basis Value	84.91	47.12	86.23	47.45
A-estimate	78.67	40.86	79.86	41.07
Method	pooled	pooled	pooled	pooled

Table 4-23: Statistics and Basis Values for UNC1 Strength data

Unnotched Compression (UNC1) Modulus Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	7.05	6.39	7.16	6.46
Stdev	0.18	0.16	0.19	0.17
CV	2.58	2.49	2.65	2.64
Modified CV	6.00	6.00	6.00	6.00
Min	6.74	6.03	6.85	6.05
Max	7.43	6.62	7.56	6.74
No. Batches	3	3	3	3
No. Spec	23	21	23	21

Table 4-24: Statistics from UNC1 Modulus data

4.13 “Soft” Unnotched Compression Properties (UNC2)

The UNC2 data was normalized so both normalized and as measured statistics are provided. The normalized ETW dataset failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When this dataset was transformed according to the assumptions of the modified CV method, it passed the ADK test. There were no other test failures so pooling was acceptable to compute the as measured basis values and both the normalized and as measured modified CV basis values.

There was one outlier. It was the lowest value in batch one of the RTD datasets, both normalized and as measured. It was an outlier both for batch one and for the RTD condition in the as measured dataset. It was an outlier only for the RTD condition, not for batch one in the normalized dataset. It was retained for this analysis.

Statistics and basis values are given for UNC2 strength data in Table 4-25 and for the modulus data in Table 4-26. The normalized data and the B-basis values are shown graphically in Figure 4-14.

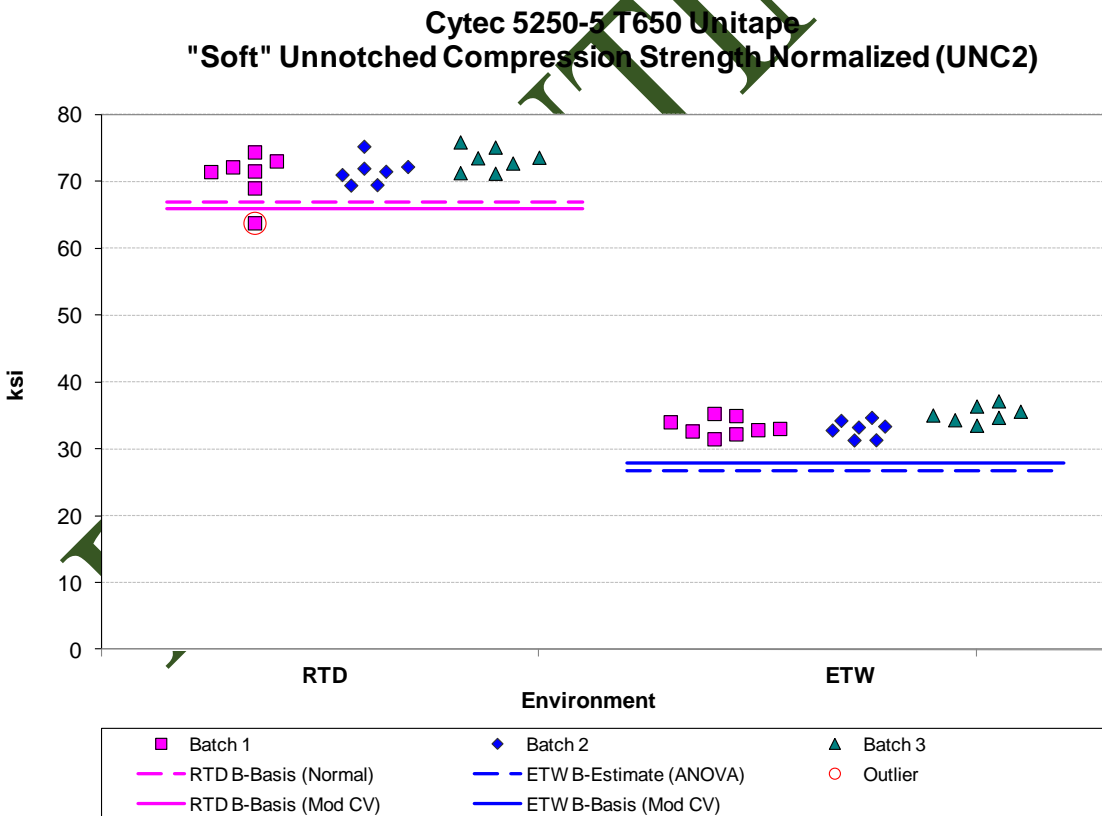


Figure 4-14: Batch plot for UNC2 strength normalized

Unnotched Compression (UNC2) Strength Basis Values and Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	71.89	33.83	74.06	34.32
Stdev	2.64	1.59	2.98	1.73
CV	3.67	4.69	4.02	5.05
Modified CV	6.00	6.35	6.01	6.52
Min	63.79	31.32	64.62	31.24
Max	75.89	37.16	78.07	38.18
No. Batches	3	3	3	3
No. Spec.	21	22	21	22
Basis Values and Estimates				
B-basis Value	66.86		69.77	80.04
B-estimate		26.76		
A-estimate	63.27	21.71	66.83	27.09
Method	Normal	ANOVA	pooled	pooled
Modified CV Basis Values and Estimates				
B-basis Value	65.90	27.87	67.87	28.75
A-estimate	61.79	23.75	63.62	23.89
Method	pooled	pooled	pooled	pooled

Table 4-25: Statistics and Basis Values for UNC2 Strength data

Unnotched Compression (UNC2) Modulus Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	4.66	3.55	4.80	3.60
Stdev	0.06	0.11	0.09	0.11
CV	1.38	3.19	1.85	3.14
Modified CV	6.00	6.00	6.00	6.00
Min	4.46	3.41	4.62	3.42
Max	4.76	3.84	4.98	3.83
No. Batches	3	3	3	3
No. Spec.	21	21	21	21

Table 4-26: Statistics from UNC2 Modulus data

Unnotched Compression (UNC3) Strength Basis Values and Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	134.87	67.36	136.47	67.76
Stdev	4.53	4.07	4.14	3.96
CV	3.36	6.05	3.03	5.84
Modified CV	6.00	7.02	6.00	6.92
Min	125.30	62.03	128.78	62.31
Max	144.60	74.48	146.91	75.23
No. Batches	3	3	3	3
No. Spec.	20	23	20	23
Basis Values and Estimates				
B-basis Value	126.14		129.28	60.66
B-estimate		50.57		
A-estimate	119.94	38.58	124.37	55.73
Method	Normal	ANOVA	pooled	pooled
Modified CV Basis Values and Estimates				
B-basis Value	123.30	55.93	124.83	56.26
A-estimate	115.39	48.00	116.88	49.28
Method	pooled	pooled	pooled	pooled

Table 4-27: Statistics and Basis Values for UNC3 Strength data

Unnotched Compression (UNC3) Modulus Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	10.85	10.34	10.99	10.47
Stdev	0.22	0.33	0.24	0.34
CV	2.03	3.18	2.19	3.28
Modified CV	6.00	6.00	6.00	6.00
Min	10.35	9.72	10.53	9.86
Max	11.30	10.96	11.31	11.25
No. Batches	3	3	3	3
No. Spec.	21	20	21	20

Table 4-28: Statistics from UNC3 Modulus data

4.15 Quasi Isotropic Open Hole Tension Properties (OHT1)

The OHT1 data was normalized so both normalized and as measured statistics are provided. There were no test failures so pooling across the environments was acceptable. There were no outliers.

Statistics, basis values and estimates are given for OHT1 strength data in Table 4-29. The normalized data, B-basis values and B-estimates are shown graphically in Figure 4-16.

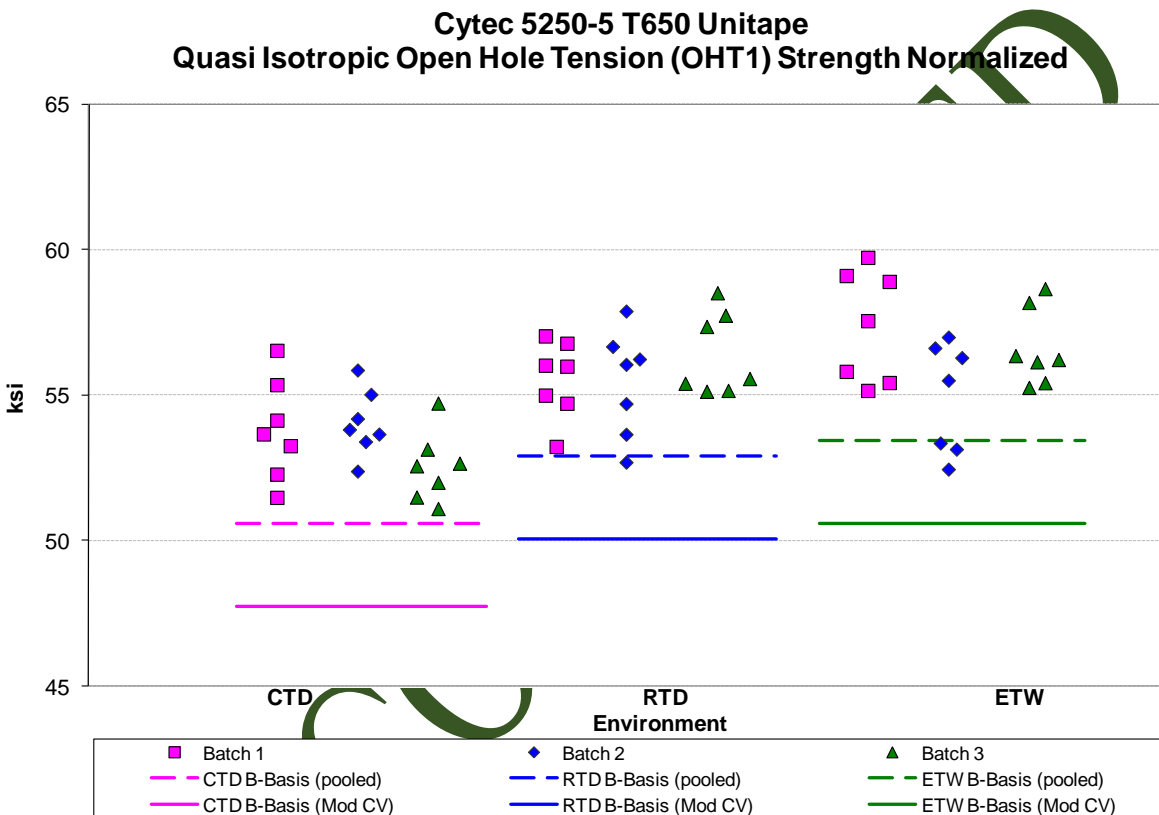


Figure 4-16: Batch Plot for OHT1 strength normalized

Open Hole Tension (OHT1) Strength Basis Values and Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	53.46	55.79	56.30	53.88	56.02	56.53
Stdev	1.48	1.52	1.95	1.80	1.89	1.94
CV	2.76	2.73	3.46	3.33	3.37	3.42
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	51.10	52.69	52.45	50.56	52.22	52.62
Max	56.54	58.52	59.73	57.76	58.86	60.36
No. Batches	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21
Basis Values and Estimates						
B-basis Value	50.59	52.91	53.42	50.64	52.78	53.29
A-estimate	48.64	50.97	51.48	48.45	50.59	51.10
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	47.74	50.06	50.57	48.12	50.26	50.77
A-estimate	43.87	46.19	46.71	44.23	46.38	46.88
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-29: Statistics and Basis Values for OHT1 Strength data

DISCONTINUED

4.16 "Soft" Open Hole Tension Properties (OHT2)

The OHT2 data was normalized so both normalized and as measured statistics are provided. The as measured CTD dataset and the normalized ETW dataset failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, both passed the ADK test. There were no other test failures. The as measured RTD and ETW datasets could be pooled and the normalized CTD and RTD dataset could be pooled. All three conditions could be pooled to compute the modified CV basis values.

There were no outliers. Statistics, basis values and estimates are given for OHT2 strength data in Table 4-30. The normalized data, B-estimates and the B-basis values are shown graphically in Figure 4-17.

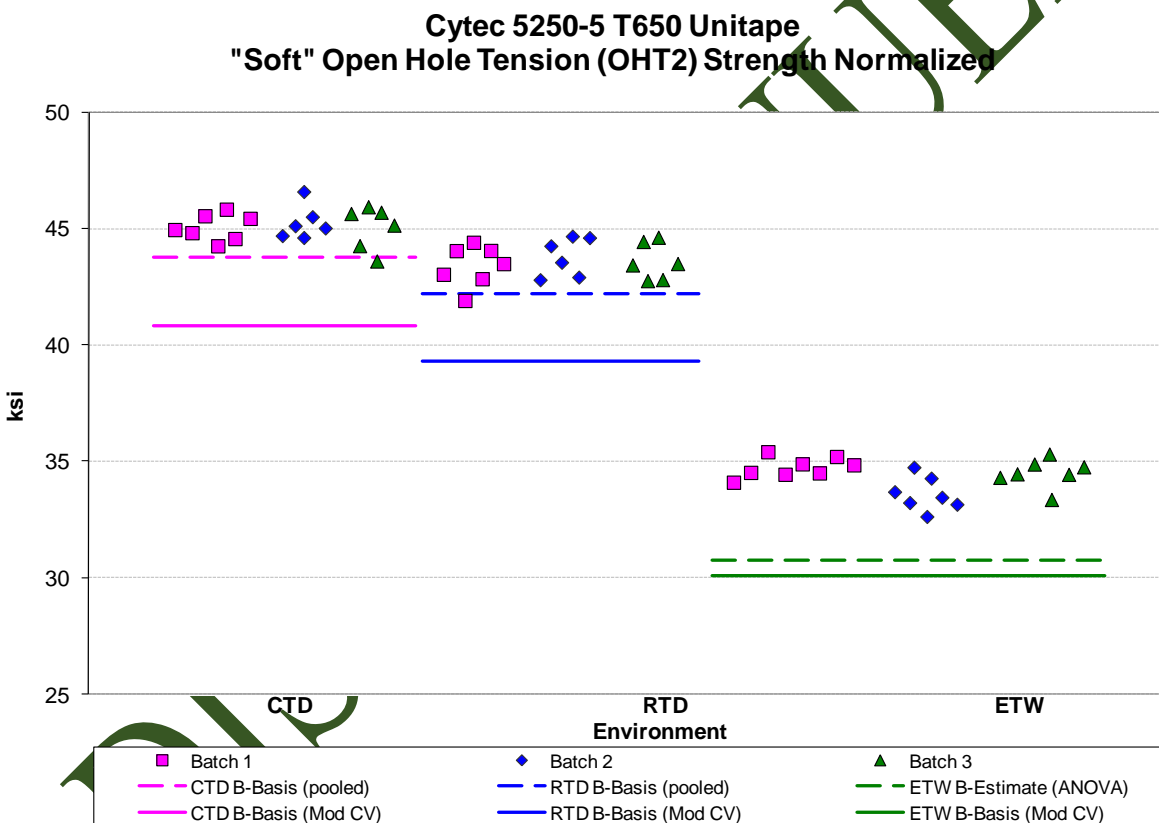


Figure 4-17: Batch Plot for OHT2 strength normalized

Open Hole Tension (OHT2) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	45.12	43.59	34.30	45.49	43.95	34.27
Stdev	0.71	0.81	0.75	0.86	0.81	1.21
CV	1.57	1.85	2.19	1.89	1.85	3.54
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	43.60	41.91	32.63	43.44	42.63	31.90
Max	46.59	44.67	35.41	46.70	45.37	36.48
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	22	19	19	22
Basis Values and Estimates						
B-basis Value	43.75	42.22			42.07	32.42
B-estimate			30.73	41.65		
A-estimate	42.82	41.29	28.18	38.92	40.79	31.13
Method	pooled	pooled	ANOVA	ANOVA	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	40.82	39.29	30.06	41.16	39.62	30.01
A-estimate	37.94	36.41	27.17	38.27	36.73	27.10
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-30: Statistics and Basis Values for OHT2 Strength data

DISCONTINUED

4.17 "Hard" Open Hole Tension Properties (OHT3)

The OHT3 data was normalized so both normalized and as measured statistics are provided. There were no test failures. Pooling across environmental conditions was acceptable.

There was one outlier. It was the lowest value from batch two in the RTD condition. It was an outlier for the RTD condition but not for batch 2. It was retained for this analysis.

Statistics, basis values and estimates are given for OHT3 strength data in Table 4-31. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-18.

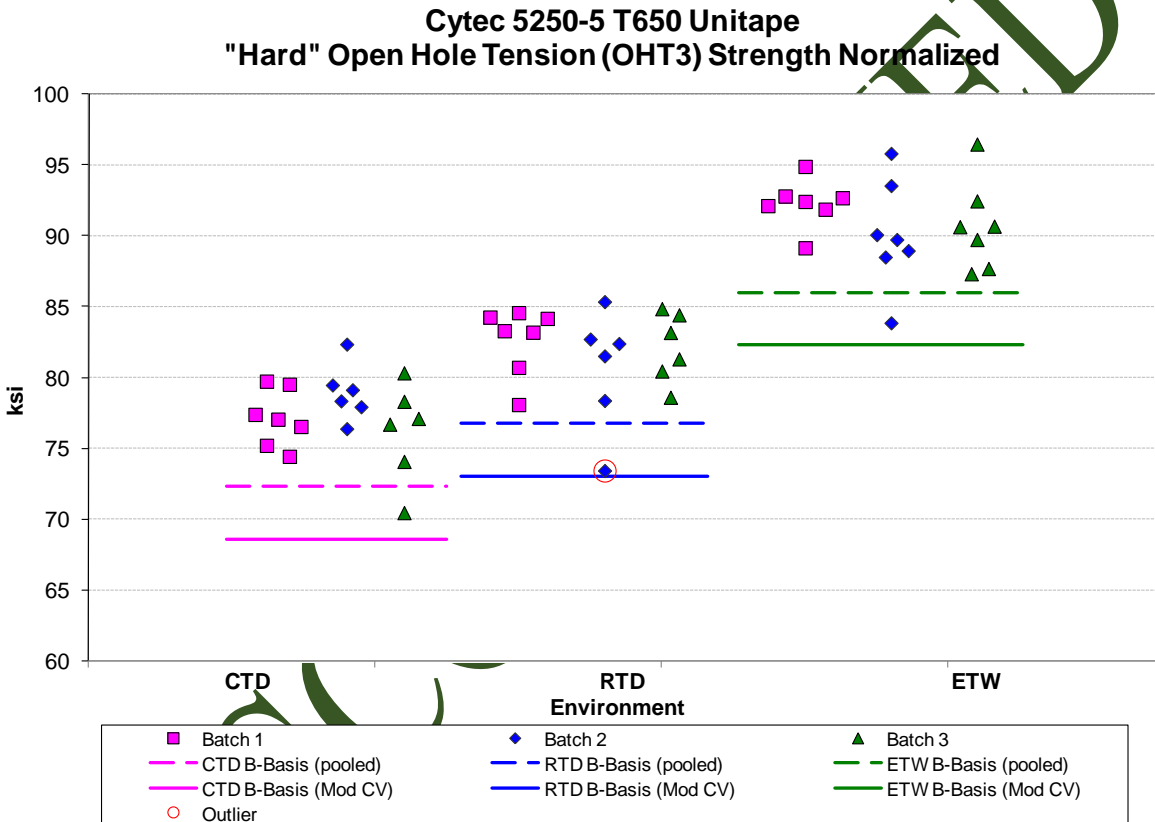


Figure 4-18: Batch Plot for OHT3 strength normalized

Open Hole Tension (OHT3) Strength (ksi) Basis Values and Statistics						
Normalized			As Measured			
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	77.39	81.83	91.01	77.80	82.34	91.83
Stdev	2.66	3.02	3.00	2.77	2.96	2.97
CV	3.44	3.69	3.30	3.56	3.60	3.24
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	70.46	73.43	83.85	70.96	74.31	85.03
Max	82.34	85.34	96.46	83.09	86.35	97.32
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	21	19	19	21
Basis Value Estimates						
B-basis Value	72.31	76.74	85.97	72.71	77.25	86.78
A-estimate	68.90	73.34	82.56	69.30	73.84	83.36
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	68.58	73.01	82.28	68.92	73.46	83.03
A-estimate	62.67	67.11	76.36	62.98	67.52	77.07
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-31: Statistics and Basis Values for OHT3 Strength data

DISCONTINUED

4.18 Quasi Isotropic Filled Hole Tension Properties (FHT1)

The FHT1 data was normalized so both normalized and as measured statistics are provided. The ETW datasets, both as measured and normalized, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, both passed the ADK test, so modified CV basis values are provided.

The normalized RTD dataset failed the normality test. The lognormal distribution was the best fit. The normalized CTD and RTD data could not be pooled due to non-normality of the pooled dataset. The as measured CTD and RTDs dataset could be pooled and all three conditions could be pooled to compute the modified CV basis values for both normalized and as measured data.

There were no outliers. Statistics, estimates and basis values are given for FHT1 strength data in Table 4-32. The normalized data, B-estimates and the B-basis values are shown graphically in Figure 4-19 .

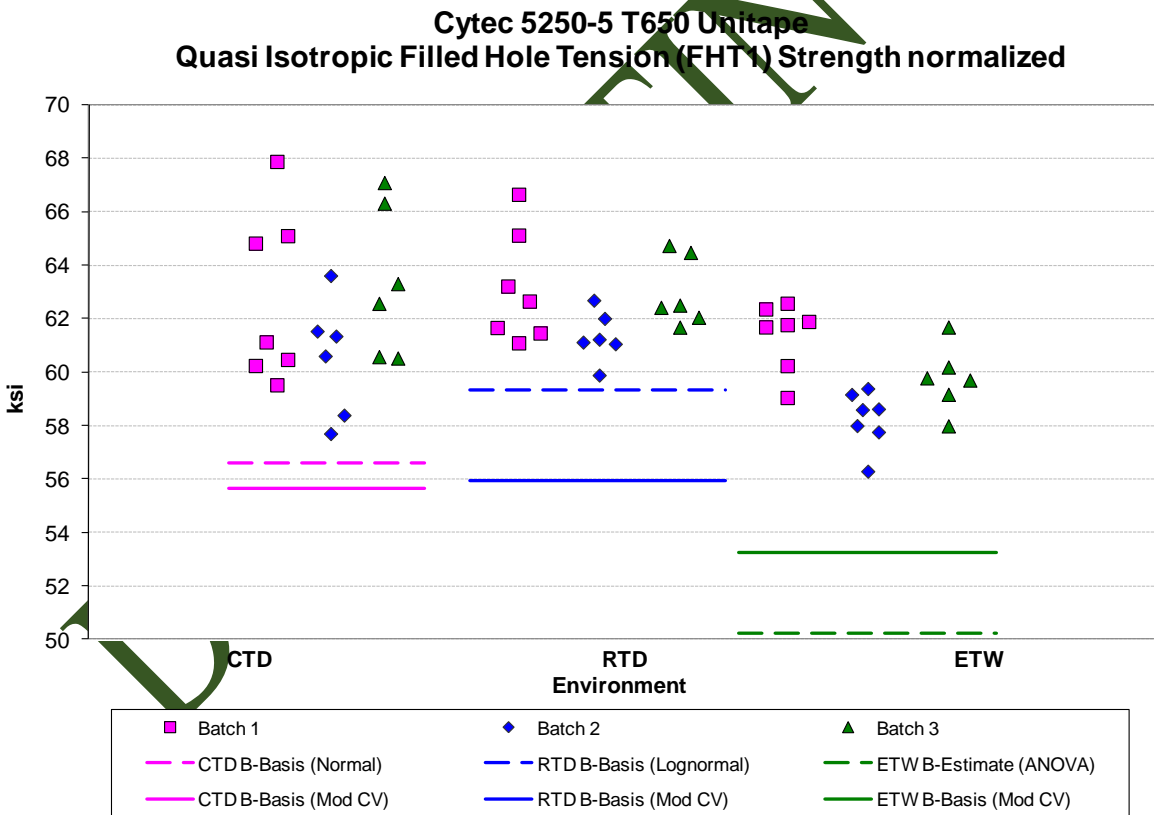


Figure 4-19: Batch plot for FHT1 strength normalized

Filled-Hole Tension (FHT1) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	62.25	62.51	59.79	62.72	63.13	59.80
Stdev	2.90	1.68	1.74	2.47	1.63	1.54
CV	4.65	2.69	2.91	3.93	2.59	2.58
Modified CV	6.33	6.00	6.00	6.00	6.00	6.00
Min	57.69	59.88	56.28	59.43	60.73	56.68
Max	67.88	66.65	62.57	68.30	66.98	62.77
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	20	19	19	20
Basis Values and Estimates						
B-basis Value	56.60	59.33		58.95	59.36	
B-estimate			50.22			53.10
A-estimate	52.60	57.18	43.38	56.37	56.78	48.32
Method	Normal	Lognormal	ANOVA	pooled	pooled	ANOVA
Modified CV Basis Values and Estimates						
B-basis Value	55.66	55.92	53.23	56.21	56.62	53.32
A-estimate	51.24	51.50	48.81	51.85	52.26	48.95
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-32: Statistics and Basis Values for FHT1 Strength data

DISCONTINUED

4.19 "Soft" Filled Hole Tension Properties (FHT2)

The FHT2 data was normalized so both normalized and as measured statistics are provided. There were no test failures. Pooling across the environmental conditions was acceptable.

There was one outlier. It was the highest value in batch two of the ETW normalized dataset. It was an outlier only for normalized data from batch two, not for the ETW condition or for the as measured data from batch two. It was retained for this analysis.

Statistics and basis values are given for FHT2 strength data in Table 4-33. The normalized data and the B-basis values are shown graphically in Figure 4-20.

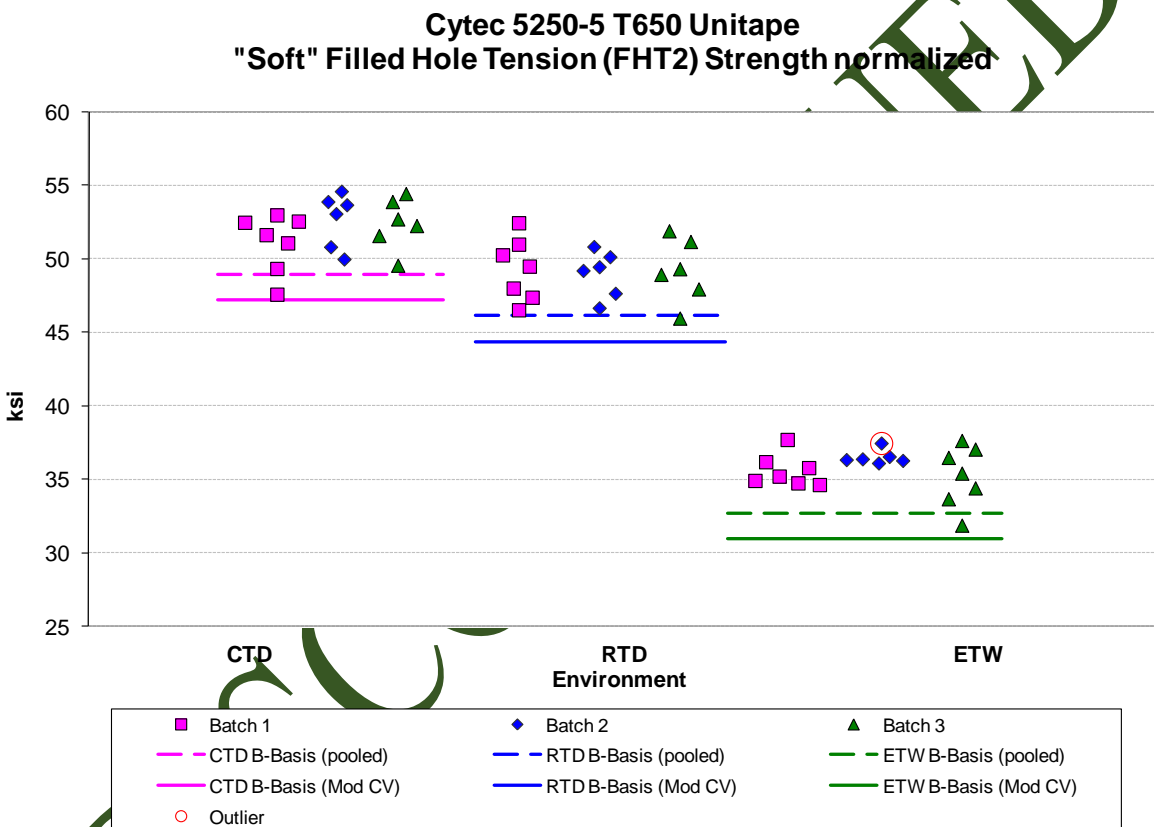


Figure 4-20: Batch plot for FHT2 strength normalized

Filled-Hole Tension (FHT2) Strength Basis Values and Statistics						
Normalized			As Measured			
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	52.01	49.18	35.74	52.61	49.48	35.97
Stdev	1.90	1.87	1.43	1.99	1.75	1.54
CV	3.66	3.80	4.01	3.77	3.53	4.29
Modified CV	6.00	6.00	6.01	6.00	6.00	6.14
Min	47.59	45.96	31.87	47.72	45.96	32.40
Max	54.60	52.45	37.70	55.63	52.81	38.18
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	20	19	19	20
Basis Values and Estimates						
B-basis Value	48.96	46.12	32.70	49.52	46.39	32.89
A-estimate	46.91	44.08	30.65	47.44	44.02	30.81
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	47.17	44.33	30.92	47.70	44.57	31.08
A-estimate	43.93	41.09	27.67	44.41	41.29	27.79
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-33: Statistics and Basis Values for FHT2 Strength data

DISCONTINUED

4.20 "Hard" Filled Hole Tension Properties (FHT3)

The FHT3 data was normalized so both normalized and as measured statistics are provided. There were no test failures. Pooling across the environmental conditions was acceptable.

There were no outliers. Statistics, estimates and basis values are given for FHT3 strength data in Table 4-34. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-21.

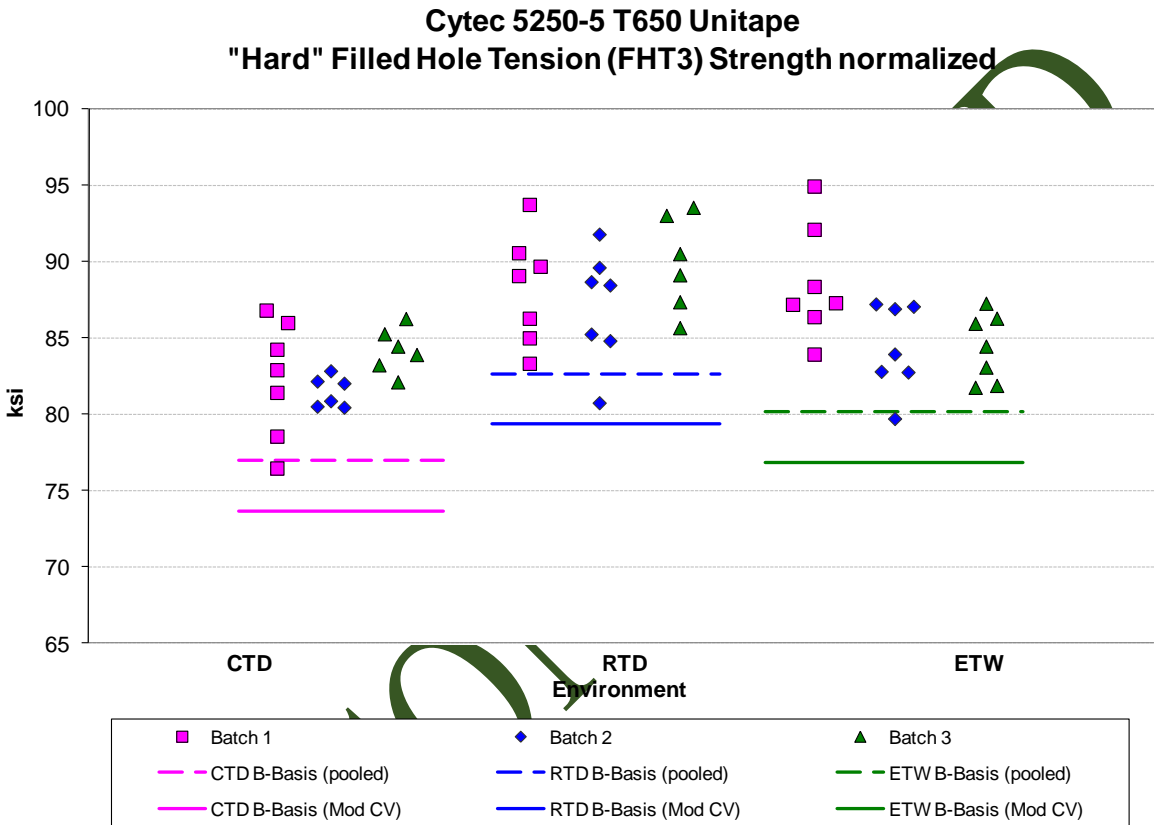


Figure 4-21: Batch plot for FHT3 strength normalized

Filled-Hole Tension (FHT3) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	82.66	88.31	85.77	83.57	88.86	85.97
Stdev	2.65	3.50	3.50	2.71	3.00	3.69
CV	3.20	3.96	4.08	3.25	3.38	4.29
Modified CV	6.00	6.00	6.04	6.00	6.00	6.15
Min	76.47	80.75	79.71	77.16	82.91	79.54
Max	86.81	93.73	94.94	87.42	93.86	95.10
No. Batches	3	3	3	3	3	3
No. Spec.	19	20	21	19	20	21
Basis Values and Estimates						
B-basis Value	76.96	82.64	80.13	78.01	83.32	80.46
A-estimate	73.15	78.83	76.31	74.29	79.60	76.73
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	73.64	79.34	76.84	74.44	79.77	76.93
A-estimate	67.61	73.30	70.80	68.33	73.66	70.81
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-34: Statistics and Basis Values for FHT3 Strength data

DISCONTINUED

4.21 Quasi Isotropic Open Hole Compression Properties (OHC1)

The OHC1 data was normalized so both normalized and as measured statistics are provided. The as measured RTD and ETW datasets failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, both passed the ADK test, so modified CV basis values are provided.

Both the normalized and as measured datasets failed Levene's test for equality of variance, so pooling the two conditions together was not acceptable.

There were a total of four outliers for the OHC1 data, three in the normalized data and one in the as measured data. The lowest value in batch two of the as measured RTD data was an outlier for batch two, but not for the RTD condition. The lowest value in batch one of the normalized RTD data was an outlier for batch one, but not for the RTD condition. The highest value in batch three of the normalized RTD data was an outlier for both batch three and the RTD condition. The highest value in batch one of the normalized ETW data was an outlier for batch one but not for the ETW condition. All four outliers were retained for this analysis.

Statistics, estimates and basis values are given for OHC1 strength data in Table 4-35. The normalized data and the B-basis values are shown graphically in Figure 4-22.

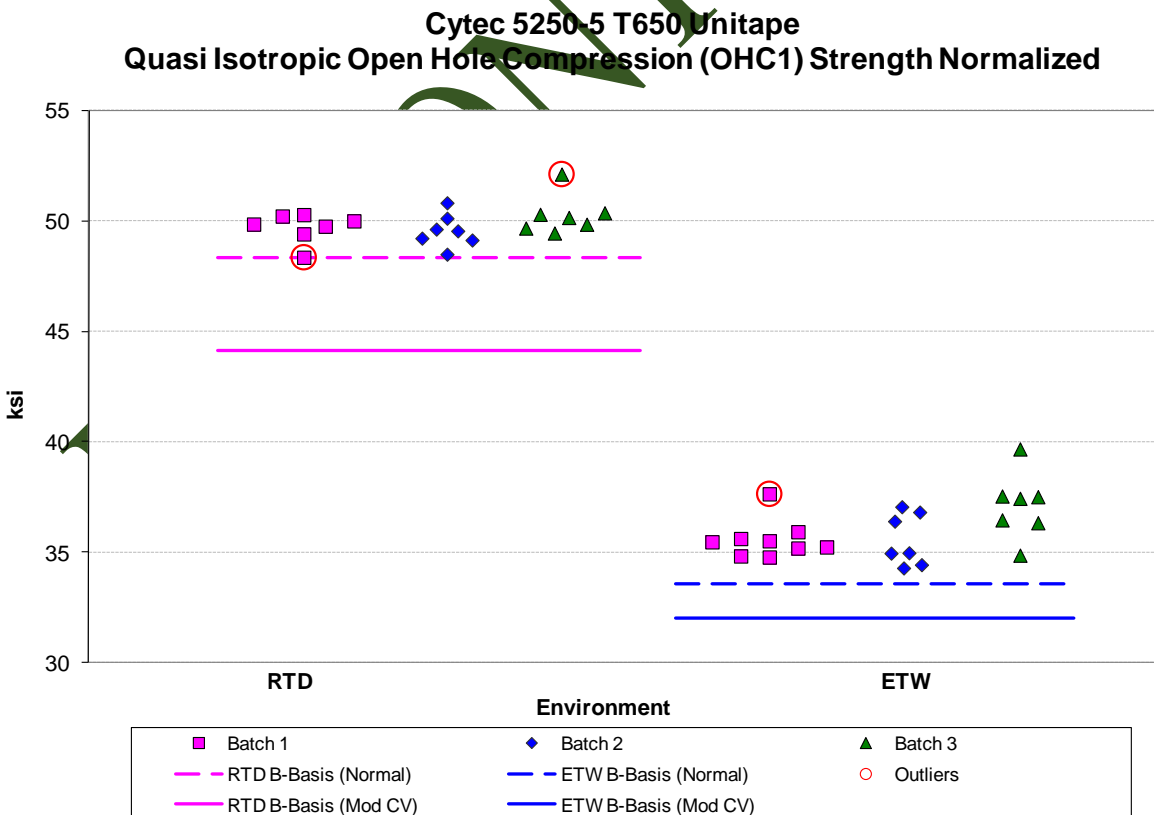


Figure 4-22: Batch plot for OHC1 strength normalized

Open Hole Compression (OHC1) Strength Basis Values and Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	49.84	36.04	50.31	36.50
Stdev	0.79	1.33	0.83	1.61
CV	1.59	3.68	1.65	4.42
Modified CV	6.00	6.00	6.00	6.21
Min	48.35	34.29	48.31	34.02
Max	52.12	39.68	52.21	39.97
No. Batches	3	3	3	3
No. Spec.	21	23	21	23
Basis Values and Estimates				
B-basis Value	48.33	33.57		
B-estimate			47.06	30.51
A-estimate	47.25	31.79	44.74	26.24
Method	Normal	Normal	ANOVA	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	44.14	32.00	44.56	32.28
A-estimate	40.08	29.11	40.46	28.23
Method	Normal	Normal	Normal	Normal

Table 4-35: Statistics and Basis Values for OHC1 Strength data

DISCONTINUED

4.22 “Soft” Open Hole Compression Properties (OHC2)

The OHC2 data was normalized so both normalized and as measured statistics are provided. . The as measured RTD dataset failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When this dataset was transformed according to the assumptions of the modified CV method, it passed the ADK test, so modified CV basis values are provided.

Pooling across the two conditions was acceptable for the normalized datasets and for the modified CV basis values for the as measured datasets.

There was one outlier. It was the lowest value in batch one of the as measured ETW dataset. It was an outlier only for batch one, not for the ETW condition and not for the normalized batch one data. It was retained for this analysis.

Statistics, estimates and basis values are given for OHC2 strength data in Table 4-36. The normalized data and the B-basis values are shown graphically in Figure 4-23.

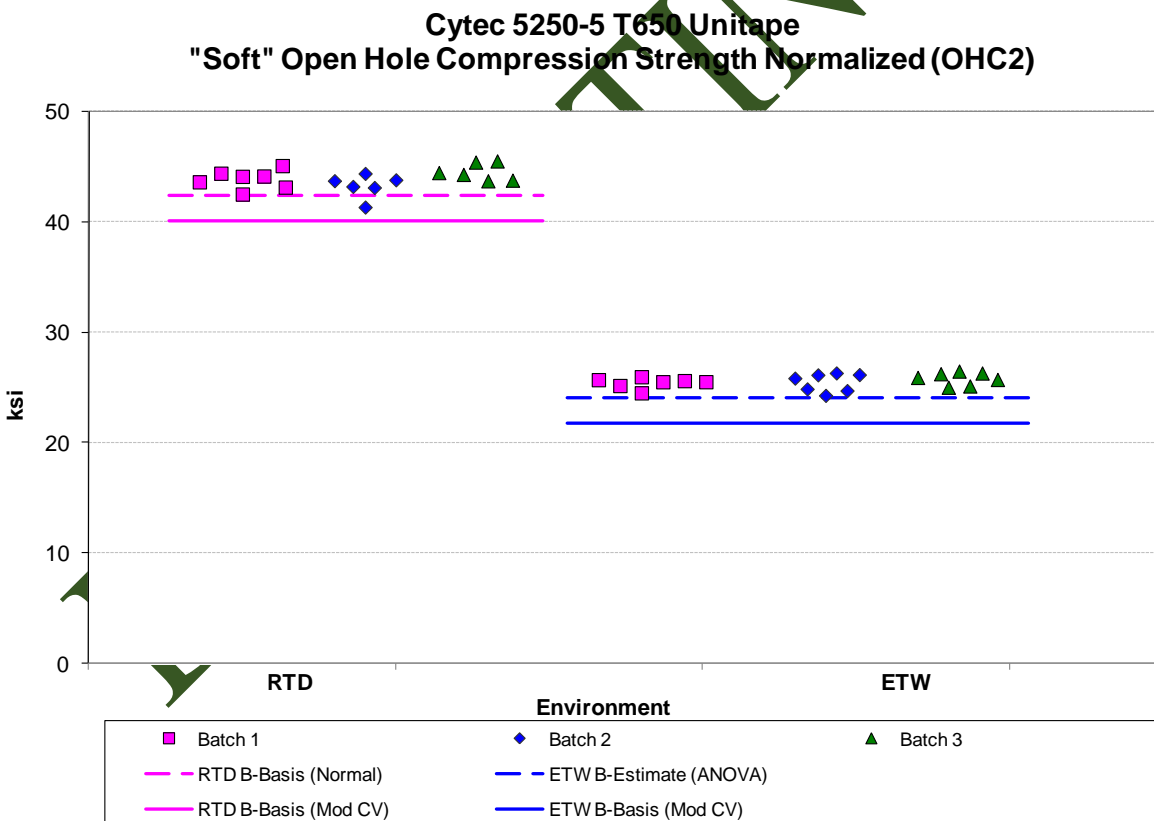


Figure 4-23: Batch plot for OHC2 strength normalized

Open-Hole Compression (OHC2) Strength Basis Values and Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	43.86	25.57	44.19	25.80
Stdev	0.99	0.64	1.02	0.82
CV	2.26	2.49	2.30	3.18
Modified CV	6.00	6.00	6.00	6.00
Min	41.32	24.27	42.30	24.07
Max	45.49	26.47	45.63	27.23
No. Batches	3	3	3	3
No. Spec.	19	21	19	21
Basis Values and Estimates				
B-basis Value	42.38	24.10		24.23
B-estimate			40.16	
A-estimate	41.37	23.09	37.29	23.12
Method	pooled	pooled	ANOVA	Normal
Modified CV Basis Values and Estimates				
B-basis Value	40.04	21.78	40.84	21.98
A-estimate	37.44	19.17	37.72	18.35
Method	pooled	pooled	pooled	pooled

Table 4-36: Statistics and Basis Values for OHC2 Strength data

DISCONTINUED

4.23 “Hard” Open Hole Compression Properties (OHC3)

The OHC3 data was normalized so both normalized and as measured statistics are provided. Batch one of the OHC3 data had specimens available from only one cure cycle. The material from the second cure cycle was excluded due to bad layup.

The RTD datasets, both as measured and normalized, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, it passed the ADK test, so modified CV basis values are provided. Pooling across the two conditions was acceptable for the modified CV basis values.

There was one outlier. It was the highest value in batch two of the as measured RTD dataset. It was an outlier only for batch two, not for the RTD condition and not for the normalized batch two data. It was retained for this analysis.

Statistics, estimates and basis values are given for OHC3 strength data in Table 4-37. The normalized data and the B-basis values are shown graphically in Figure 4-24.

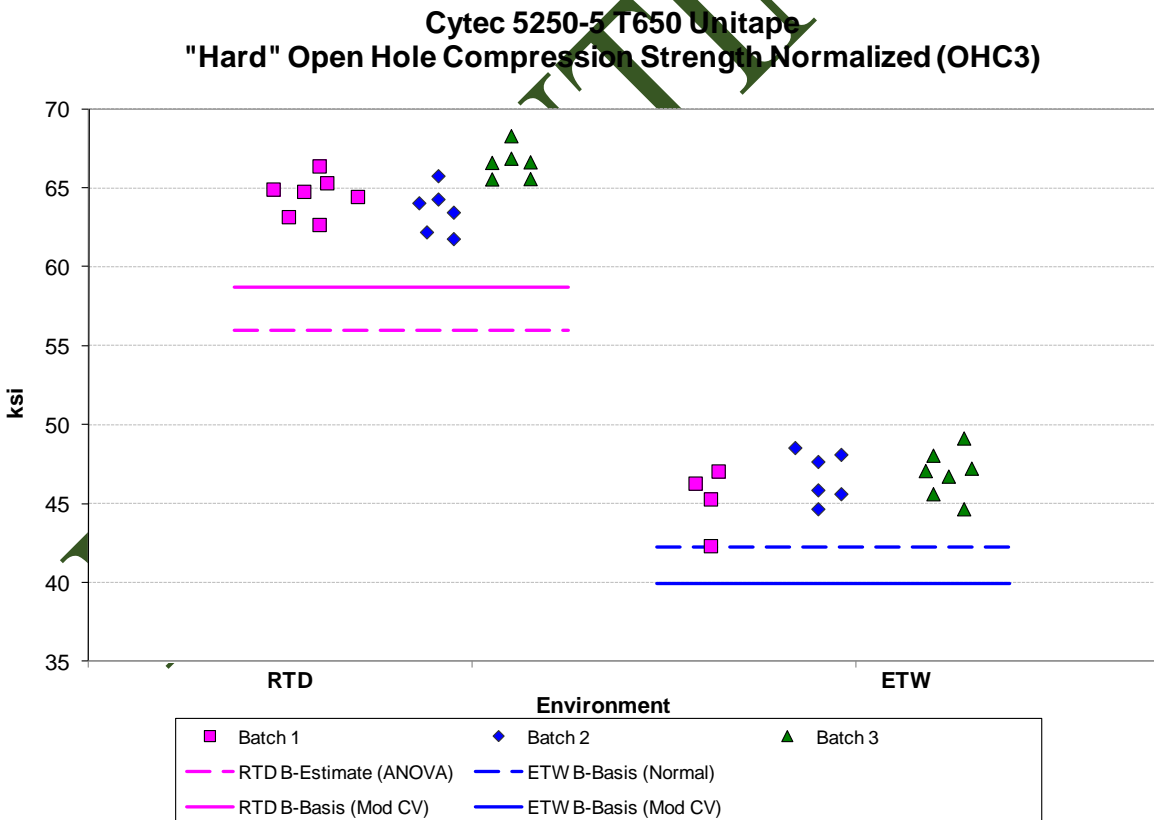


Figure 4-24: Batch plot for OHC3 strength normalized

Open-Hole Compression (OHC3) Strength Basis Values and Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	64.89	46.16	65.75	46.81
Stdev	1.73	2.00	1.79	2.37
CV	2.66	4.34	2.72	5.06
Modified CV	6.00	6.17	6.00	6.53
Min	61.78	42.02	62.56	42.03
Max	68.30	49.15	69.23	50.48
No. Batches	3	3	3	3
No. Spec.	19	18	19	18
Basis Values and Estimates				
B-basis Value		42.21		42.13
B-estimate	55.96		55.05	
A-estimate	49.60	39.41	47.41	38.82
Method	ANOVA	Normal	ANOVA	Normal
Modified CV Basis Values and Estimates				
B-basis Value	58.69	39.94	59.85	40.38
A-estimate	54.46	35.71	54.97	36.00
Method	pooled	pooled	pooled	pooled

Table 4-37: Statistics and Basis Values for OHC3 Strength data

DISCONTINUED

4.24 Quasi Isotropic Filled Hole Compression Properties (FHC1)

The FHC1 data was normalized so both normalized and as measured statistics are provided. The RTD datasets, both as measured and normalized, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate.

When these datasets were transformed according to the assumptions of the modified CV method, it passed the ADK test, so modified CV basis values are provided. Pooling across the two conditions was not acceptable for the modified CV basis values due to a failure of Levene's test for equality of variance.

There were no outliers. Statistics, estimates and basis values are given for FHC1 strength data in Table 4-38. The normalized data, B-estimates and the B-basis values are shown graphically in Figure 4-25.

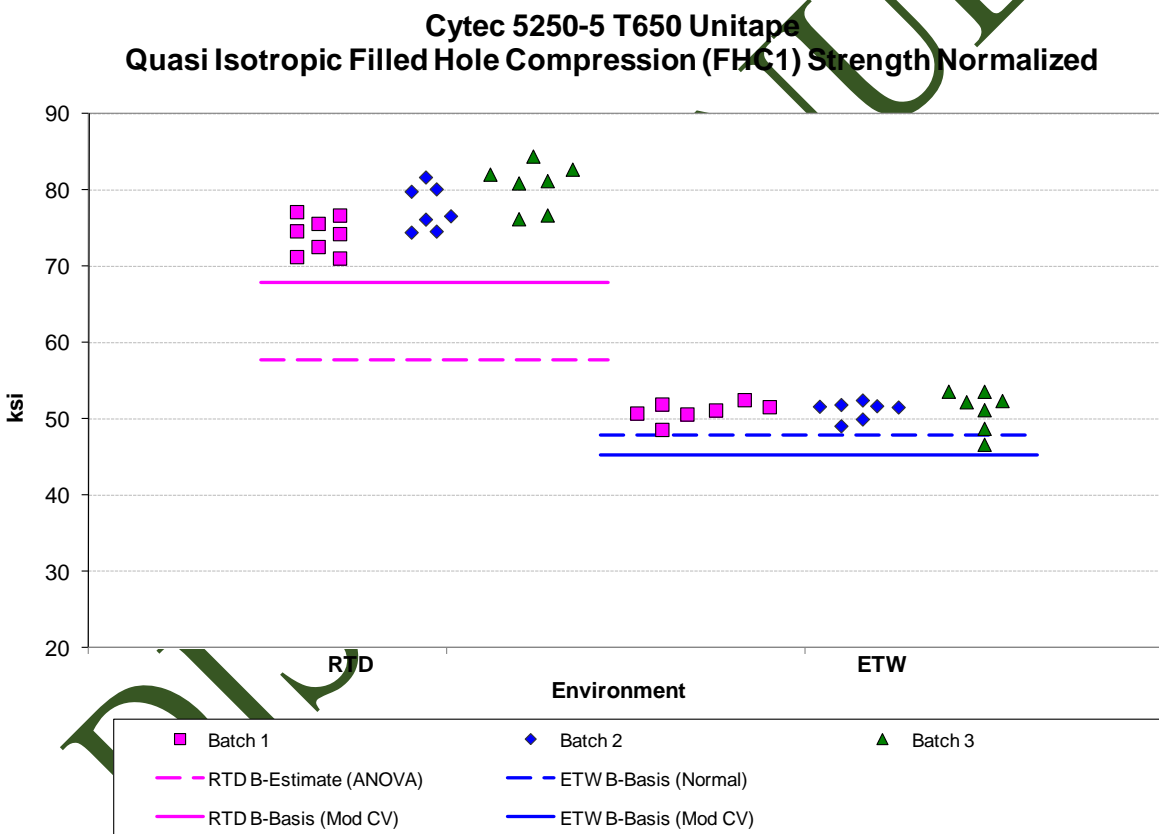


Figure 4-25: Batch plot for FHC1 strength normalized

Filled-Hole Compression (FHC1) Strength Basis Values and Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	77.29	51.12	78.55	52.07
Stdev	3.78	1.71	4.09	2.03
CV	4.89	3.35	5.21	3.90
Modified CV	6.45	6.00	6.61	6.00
Min	71.04	46.65	70.85	47.31
Max	84.40	53.60	87.42	54.97
No. Batches	3	3	3	3
No. Spec.	22	21	22	21
Basis Values and Estimates				
B-basis Value		47.86		48.20
B-estimate	57.72		58.73	
A-estimate	43.74	45.53	44.57	45.44
Method	ANOVA	Normal	ANOVA	Normal
Modified CV Basis Values and Estimates				
B-basis Value	67.89	45.28	68.76	46.12
A-estimate	61.18	41.11	61.77	41.88
Method	Normal	Normal	Normal	Normal

Table 4-38: Statistics and Basis Values for FHC1 Strength data

DISCONTINUED

4.25 "Soft" Filled Hole Compression Properties (FHC2)

The FHC2 data was normalized so both normalized and as measured statistics are provided.

The RTD datasets, both as measured and normalized, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, it passed the ADK test, so modified CV basis values are provided. Pooling across the two conditions was acceptable for the modified CV basis values.

There were no outliers. Statistics, estimates and basis values are given for FHC2 strength data in Table 4-39. The normalized data, B-estimates and the B-basis values are shown graphically in Figure 4-26.

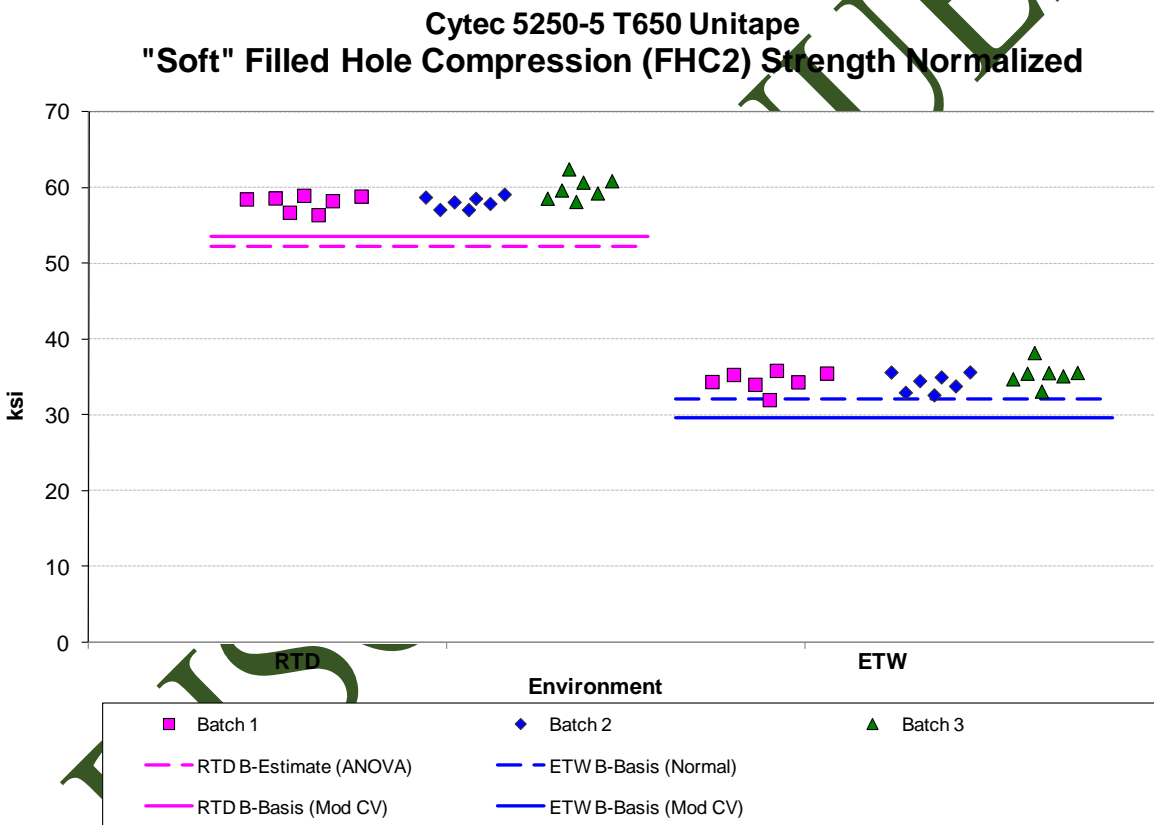


Figure 4-26: Batch plot for FHC2 strength normalized

Filled-Hole Compression (FHC2) Strength Basis Values and Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	58.68	34.74	59.27	35.08
Stdev	1.42	1.37	1.68	1.49
CV	2.42	3.94	2.84	4.26
Modified CV	6.00	6.00	6.00	6.13
Min	56.39	32.00	55.42	31.96
Max	62.43	38.21	62.75	38.84
No. Batches	3	3	3	3
No. Spec.	21	21	21	21
Basis Values and Estimates				
B-basis Value		32.13		32.24
B-estimate	52.23		50.78	
A-estimate	47.62	30.27	44.72	30.21
Method	ANOVA	Normal	ANOVA	Normal
Modified CV Basis Values and Estimates				
B-basis Value	53.55	29.61	54.06	29.87
A-estimate	50.02	26.08	50.48	26.29
Method	pooled	pooled	pooled	pooled

Table 4-39: Statistics and Basis Values for FHC2 Strength data

DISCONTINUED

4.26 "Hard" Filled Hole Compression Properties (FHC3)

The FHC3 data was normalized so both normalized and as measured statistics are provided. Batch one of the FHC3 data had specimens available from only one cure cycle. The material from the second cure cycle was excluded due to bad layup.

The ETW datasets, both as measured and normalized, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, they still did not pass the ADK test, so only estimates are available for the ETW condition.

There was one outlier. It was the lowest value in batch two of the normalized RTD data. It was an outlier only for batch two, not for the RTD condition and not for the as measured batch three RTD data. It was retained for this analysis.

Statistics, estimates and basis values are given for FHC3 strength data in Table 4-40. The normalized data and the B-basis values are shown graphically in Figure 4-27.

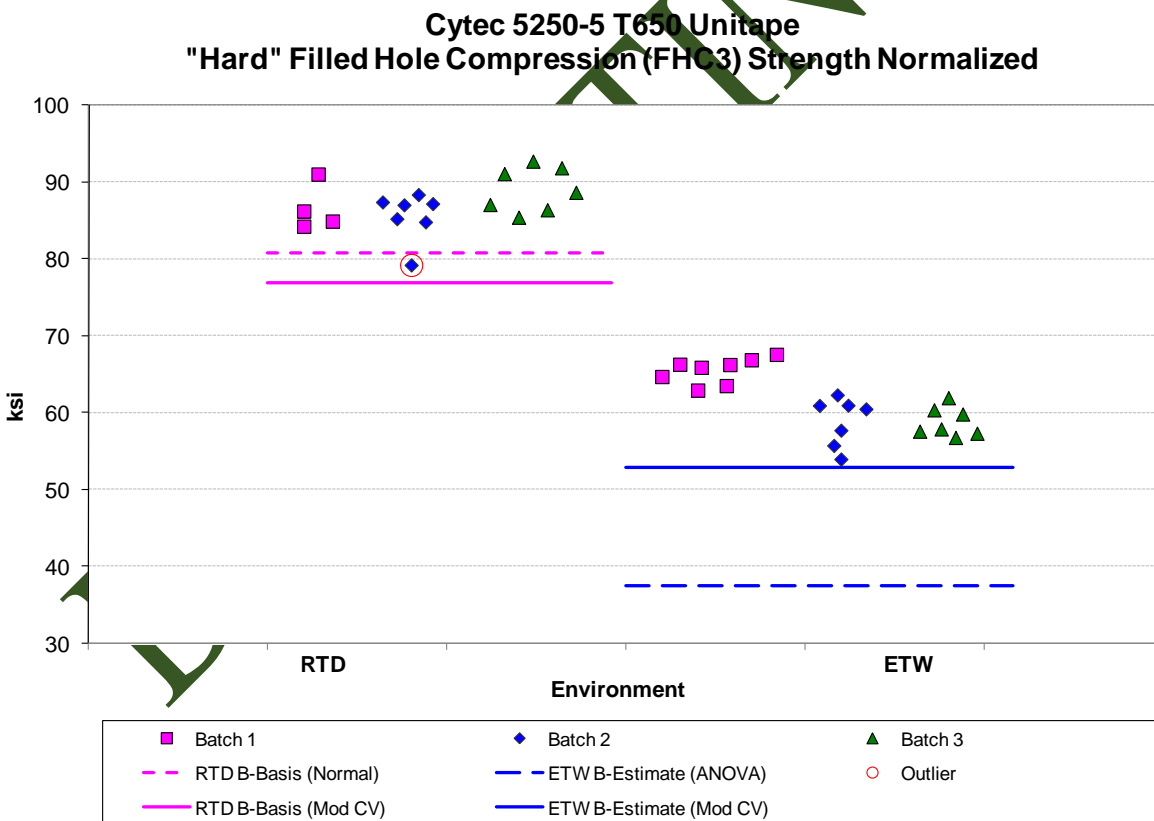


Figure 4-27: Batch plot for FHC3 strength normalized

Filled-Hole Compression (FHC3) Strength Basis Values and Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	87.16	61.27	88.06	61.65
Stdev	3.23	3.93	2.85	3.58
CV	3.71	6.42	3.24	5.80
Modified CV	6.00	7.21	6.00	6.90
Min	79.21	53.96	81.34	54.64
Max	92.72	67.58	92.51	67.15
No. Batches	3	3	3	3
No. Spec.	18	22	18	22
Basis Values and Estimates				
B-basis Value	80.78		82.42	
B-estimate		37.41		41.71
A-estimate	76.26	20.38	78.43	27.47
Method	Normal	ANOVA	Normal	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	76.84		77.62	
B-estimate		52.93		53.62
A-estimate	69.53	46.98	70.25	47.89
Method	Normal	Normal	Normal	Normal

Table 4-40: Statistics and Basis Values for FHC3 Strength data

DISCONTINUED

4.27 Laminate Short Beam Strength (SBS1)

The Laminate Short Beam Strength data is not normalized. The pooled data failed the normality test, so pooling across environments was not acceptable. There were no outliers. Statistics, estimates and basis values are given for SBS1 strength data in Table 4-41. The data and the B-basis values are shown graphically in Figure 4-28.

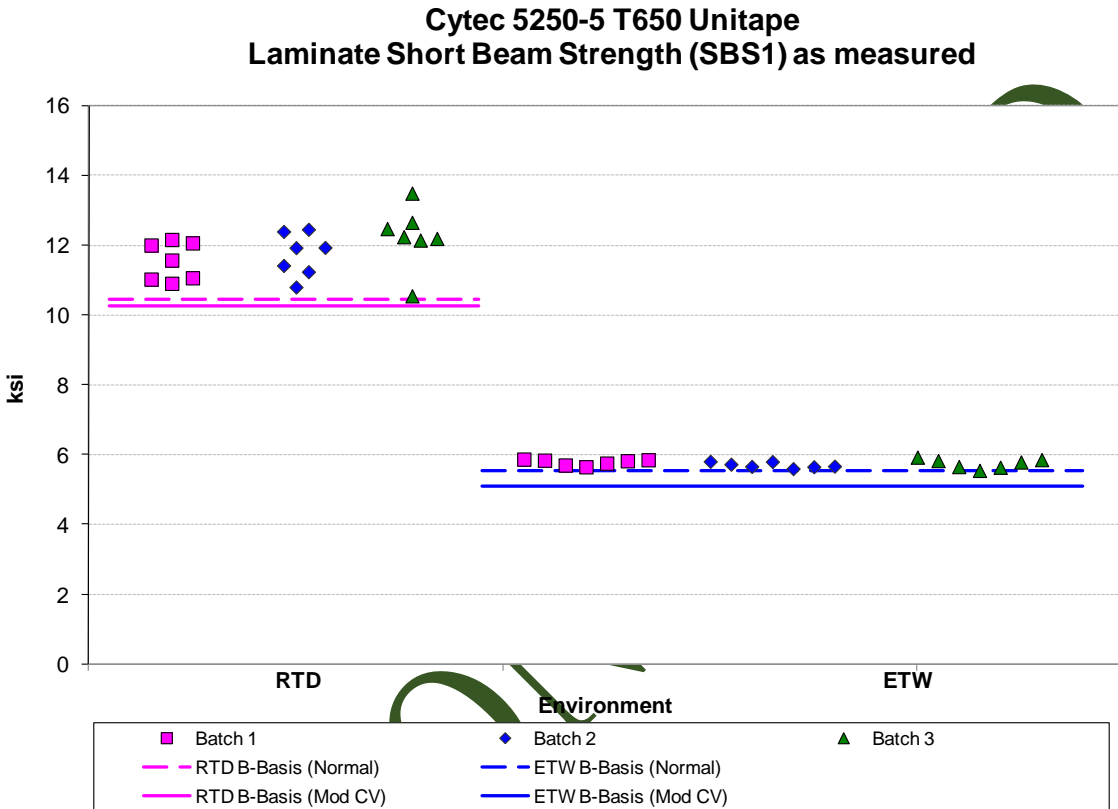


Figure 4-28: Batch plot for SBS1 strength as measured

Laminate Short Beam Strength (SBS1) Basis Values and Statistics		
Env	RTD	ETW
Mean	11.84	5.74
Stdev	0.73	0.10
CV	6.13	1.81
Modified CV	7.07	6.00
Min	10.55	5.55
Max	13.49	5.93
No. Batches	3	3
No. Spec.	21	21
Basis Values and Estimates		
B-basis Value	10.46	5.54
A-estimate	9.47	5.40
Method	Normal	Normal
Modified CV Basis Values and		
B-basis Value	10.25	5.09
A-estimate	9.11	4.62
Method	Normal	Normal

Table 4-41: Statistics and Basis Values for SBS1 Strength data

DISCONTINUED

4.28 Quasi Isotropic Single Shear Bearing Properties (SSB1)

The SSB1 data was normalized so both normalized and as measured statistics are provided. The 2% offset strength ETW datasets, both normalized and as measured, and the Ultimate Strength as measured ETW dataset, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate.

When these datasets were transformed according to the assumptions of the modified CV method, the ETW ultimate strength dataset was the only one that passed the ADK test. Modified CV basis values are provided for that dataset, but only estimates are available for the 2% offset strength ETW condition.

There were two outliers. One outlier was the largest value in batch two of the RTD ultimate strength dataset. It was an outlier only for batch two, not for the RTD condition. It was an outlier in both the normalized and the as measured dataset. The second outlier was the largest value in batch three of the ETW condition. It was an outlier only for batch three, not for the ETW condition. It was an outlier in both the normalized and the as measured dataset. Both outliers were retained for this analysis.

Statistics, estimates and basis values are given for the SSB1 strength data in Table 4-42. The normalized data and the B-basis values are shown graphically in Figure 4-29.

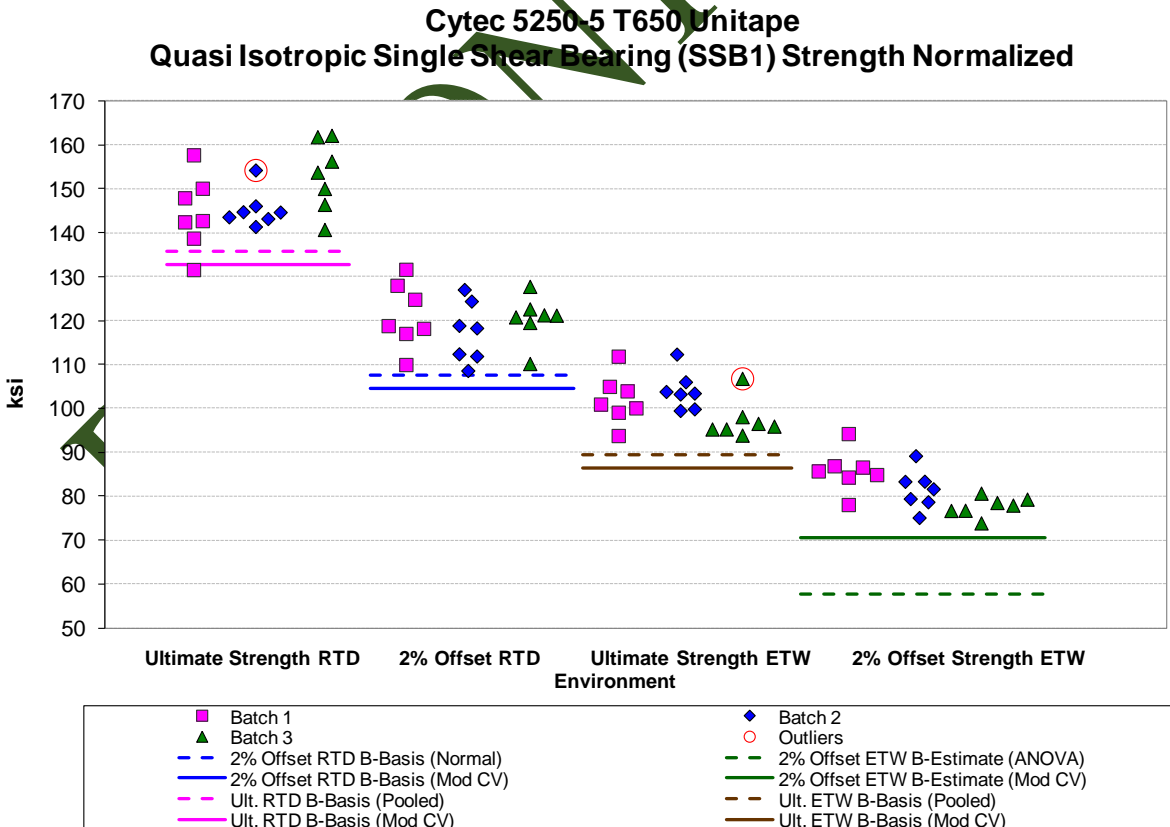


Figure 4-29: Batch plot for SSB1 strength normalized

Single Shear Bearing (SSB1) Strength Basis Values and Statistics								
2% Offset Strength					Ultimate Strength			
Env	Normalized		As measured		Normalized		As measured	
	RTD	ETW	RTD	ETW	RTD	ETW	RTD	ETW
Mean	119.70	81.71	121.17	83.38	147.65	101.20	149.42	103.29
Stdev	6.44	5.07	6.79	5.31	7.79	5.38	7.23	6.18
CV	5.38	6.20	5.60	6.36	5.28	5.31	4.84	5.99
Modified CV	6.69	7.10	6.80	7.18	6.64	6.66	6.42	6.99
Min	108.62	73.92	110.75	75.41	131.59	93.81	134.16	95.17
Max	131.65	94.25	135.10	93.75	162.16	112.34	164.27	117.25
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21	21	21
Basis Values and Estimates								
B-basis Value	107.43		108.24		135.78	89.33	135.65	
B-estimate		57.64		56.01				81.45
A-estimate	98.69	40.45	99.02	36.47	127.62	81.17	125.84	65.86
Method	Normal	ANOVA	Normal	ANOVA	pooled	pooled	Normal	ANOVA
Modified CV Basis Values and Estimates								
B-basis Value	104.44		105.47		132.74	86.29	134.37	88.24
B-estimate		70.65		71.97				
A-estimate	93.57	62.77	94.28	63.84	122.48	76.03	124.01	77.89
Method	Normal	Normal	Normal	Normal	pooled	pooled	pooled	pooled

Table 4-42: Statistics and Basis Values for SSB1 Strength data

4.29 "Soft" Single Shear Bearing Properties (SSB2)

The SSB2 data was normalized so both normalized and as measured statistics are provided. The 2% offset strength ETW datasets, both normalized and as measured failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate.

When these datasets were transformed according to the assumptions of the modified CV method, only the as measured dataset passed the ADK test. Modified CV basis values are provided for the as measured dataset, but only estimates are available for the normalized 2% offset strength ETW condition.

The normalized ultimate strength data did not have a good fit to any of the three distributions that were checked, so the non-parametric method was used to compute those basis values and the modified CV method could not be applied due to non-normality.

There were two outliers. The largest value in batch two of the ultimate strength RTD normalized data and the largest value in batch two of the ultimate strength ETW normalized data were both outliers for batch two, but not for their respective conditions. They were both outliers only for the normalized datasets, not for the as measured datasets. Both outliers were retained for this analysis.

Statistics, estimates and basis values are given for the SSB2 strength data in Table 4-43. The normalized data and the B-basis values are shown graphically in Figure 4-30.

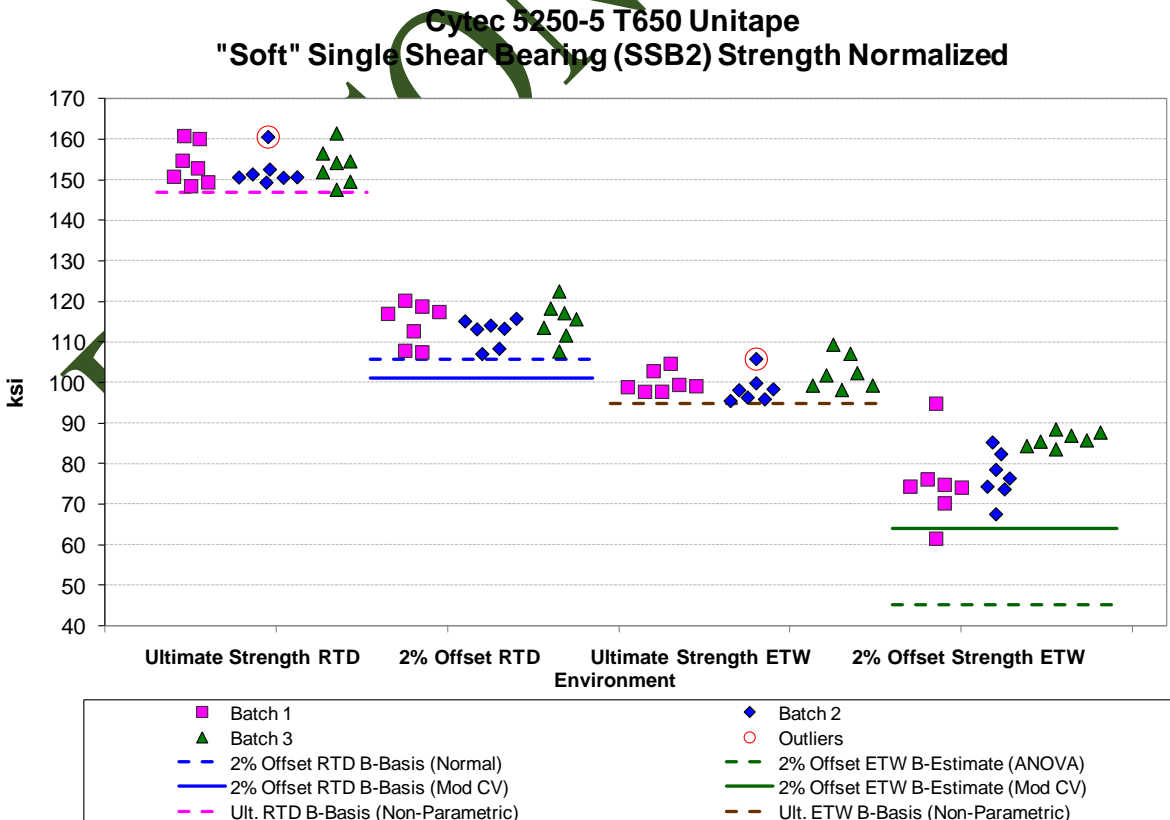


Figure 4-30: Batch plot for SSB2 strength normalized

Single Shear Bearing (SSB2) Strength Basis Values and Statistics								
2% Offset Strength					Ultimate Strength			
	Normalized		As measured		Normalized		As measured	
Env	RTD	ETW	RTD	ETW	RTD	ETW	RTD	ETW
Mean	114.09	79.40	116.01	80.93	153.33	100.43	155.91	102.25
Stdev	4.46	8.08	4.49	8.96	4.32	3.75	4.16	3.84
CV	3.91	10.18	3.87	11.07	2.82	3.74	2.67	3.75
Modified CV	6.00	10.18	6.00	11.07	6.00	6.00	6.00	6.00
Min	107.11	61.58	106.99	61.44	147.65	95.54	149.25	97.57
Max	122.57	94.89	126.63	94.53	161.54	109.43	165.36	112.48
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21	21	21
Basis Values and Estimates								
B-basis Value	105.59		107.46		146.84	94.76	147.98	94.94
B-estimate		45.20		44.16				
A-estimate	99.52	20.79	101.37	17.92	131.24	79.96	142.33	89.72
Method	Normal	ANOVA	Normal	ANOVA	Non-Parametric	Non-Parametric	Normal	Normal
Modified CV Basis Values and Estimates								
B-basis Value	101.05		102.75	63.86	NA	NA	138.08	90.56
B-estimate		64.01						
A-estimate	91.75	53.04	93.30	51.70	NA	NA	125.38	82.23
Method	Normal	Normal	Normal	Normal	NA	NA	Normal	Normal

Table 4-43: Statistics and Basis Values for SSB2 Strength data

4.30 "Hard" Single Shear Bearing Properties (SSB3)

The SSB3 data was normalized so both normalized and as measured statistics are provided. The as measured 2% offset strength ETW failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate.

When this dataset was transformed according to the assumptions of the modified CV method, it still did not pass the ADK test, so only estimates are available for the as measured 2% offset strength ETW condition.

The ultimate strength ETW datasets, both normalized and as measured, failed the normality test, but when pooled with the RTD datasets, the resulting dataset had an adequate fit to the normal distribution and pooling the two environmental conditions together was acceptable.

There were two outliers. The largest value in batch two of the as measured ultimate strength RTD data was an outlier for batch two, but not for the normalized data and not for the RTD condition. Specimen CNA3B119J from batch two in the ETW condition was an outlier for both normalized and as measured datasets and for the 2% offset strength as well as the ultimate strength datasets. In three of those four datasets, it was an outlier only for batch two, not the condition. It was an outlier for the condition in the normalized 2% offset strength dataset. Interestingly, it was the lowest value in batch two for the 2% offset strength data and the highest value for batch two for the ultimate strength data. Both outliers were retained for this analysis.

Statistics, estimates and basis values are given for the SSB3 strength data in Table 4-44. The normalized data and the B-basis values are shown graphically in Figure 4-31.

**Cytec 5250-5 T650 Unitape
"Hard" Single Shear Bearing (SSB3) Strength Normalized**

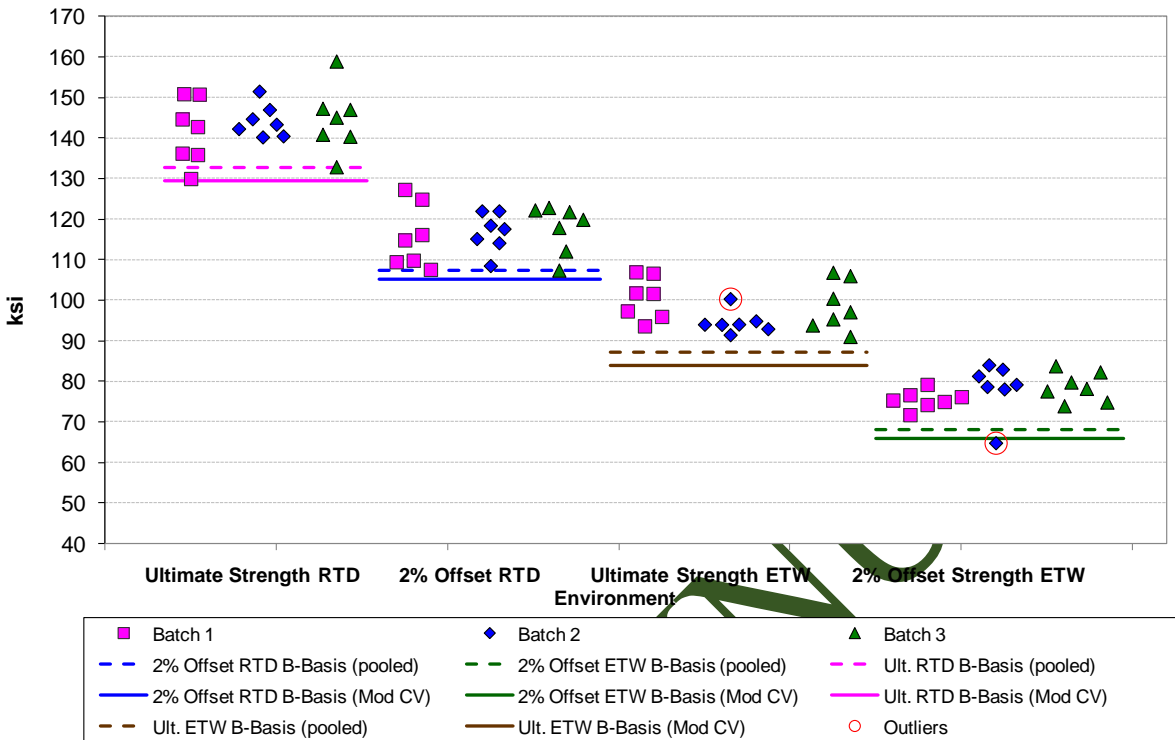


Figure 4-31: Batch plot for SSB3 strength normalized

Single Shear Bearing (SSB3) Strength Basis Values and Statistics								
Env	2% Offset Strength				Ultimate Strength			
	Normalized		As measured		Normalized		As measured	
	RTD	ETW	RTD	ETW	RTD	ETW	RTD	ETW
Mean	116.79	77.54	118.45	79.29	143.52	97.94	145.60	100.11
Stdev	5.98	4.48	5.42	5.49	6.71	5.28	6.92	5.84
CV	5.12	5.77	4.57	6.92	4.67	5.39	4.75	5.83
Modified CV	6.56	6.89	6.29	7.46	6.34	6.70	6.37	6.91
Min	107.42	64.84	109.09	66.34	129.99	91.06	134.33	92.01
Max	127.31	84.06	125.36	89.22	158.97	106.97	161.39	113.78
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	21	21	21	21	21	21	21	21
Basis Values and Estimates								
B-basis Value	107.42	68.17	108.13		132.81	87.24	134.25	88.76
B-estimate				56.06				
A-estimate	100.98	61.73	100.77	39.48	125.45	79.87	126.45	80.96
Method	pooled	pooled	Normal	ANOVA	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates								
B-basis Value	105.08	65.83	104.26		129.46	83.88	131.08	85.59
B-estimate				68.02				
A-estimate	97.03	57.78	94.15	60.00	119.79	74.21	121.10	75.61
Method	pooled	pooled	Normal	Normal	pooled	pooled	pooled	pooled

Table 4-44: Statistics and Basis Values for SSB3 Strength data

4.31 Interlaminar Tension and Curved Beam Strength (ILT and CBS)

The ILT and CBS data is not normalized. Only one batch of data was tested. Basis values are not computed for these properties. There was one outlier. The lowest value of the CBS data in the ETW condition was an outlier. The outlier was retained for this analysis. However the summary statistics are presented in Table 4-45 and the data are displayed graphically in Figure 4-32.

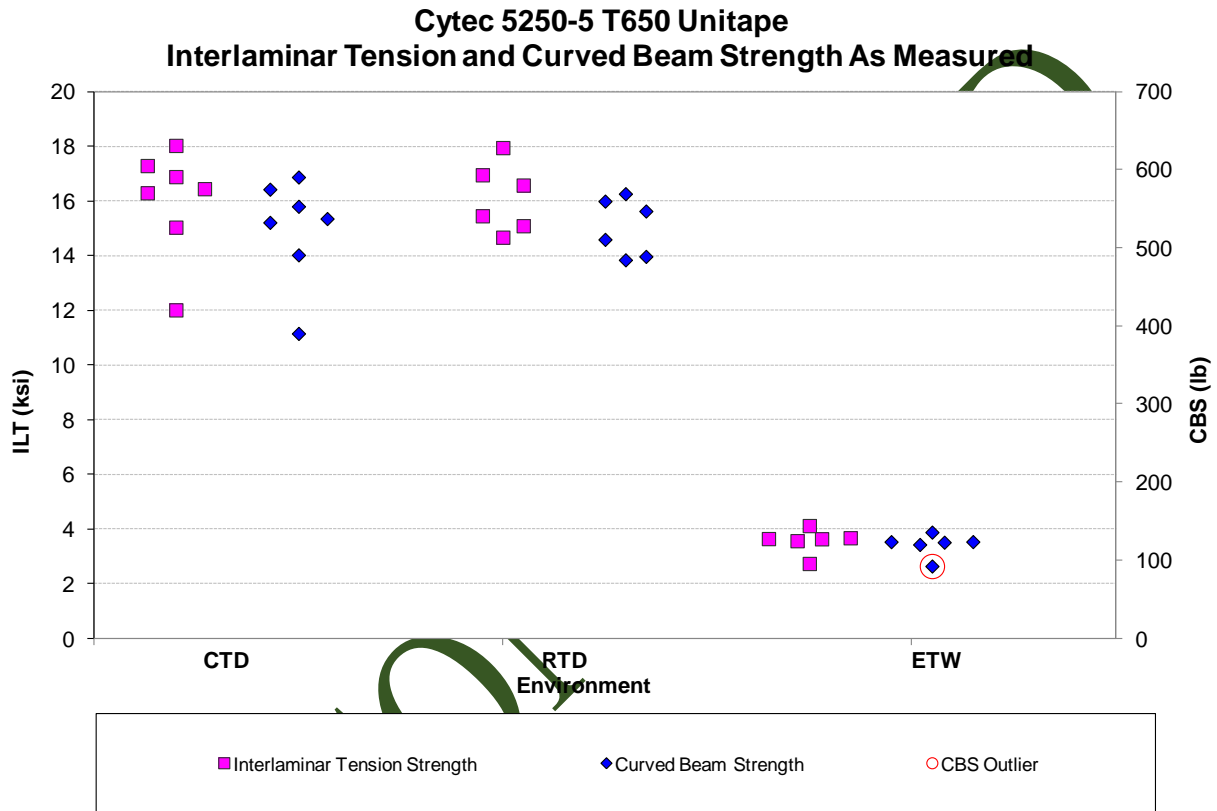


Figure 4-32: Plot for ILT and CBS as measured

Property	Interlaminar Strength (ksi)			Curved Beam Strength (lb)			
	Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean		16.00	16.11	3.56	524.13	526.59	119.61
Stdev		1.99	1.25	0.45	67.21	36.81	14.47
CV		12.42	7.78	12.71	12.82	6.99	12.10
Mod CV		12.42	7.89	12.71	12.82	7.49	12.10
Min		12.01	14.67	2.73	390.16	484.43	92.26
Max		18.03	17.95	4.12	590.47	569.12	135.71
No. Batches		1	1	1	1	1	1
No. Spec.		7	6	6	7	6	6

Table 4-45: Statistics for ILT and CBS data

4.32 Compression After Impact (CAI)

The CAI data was normalized so both normalized and as measured statistics are provided. Only one batch of data was tested. Basis values are not computed for these properties. However the summary statistics are presented in Table 4-46 and the data are displayed graphically in Figure 4-33.

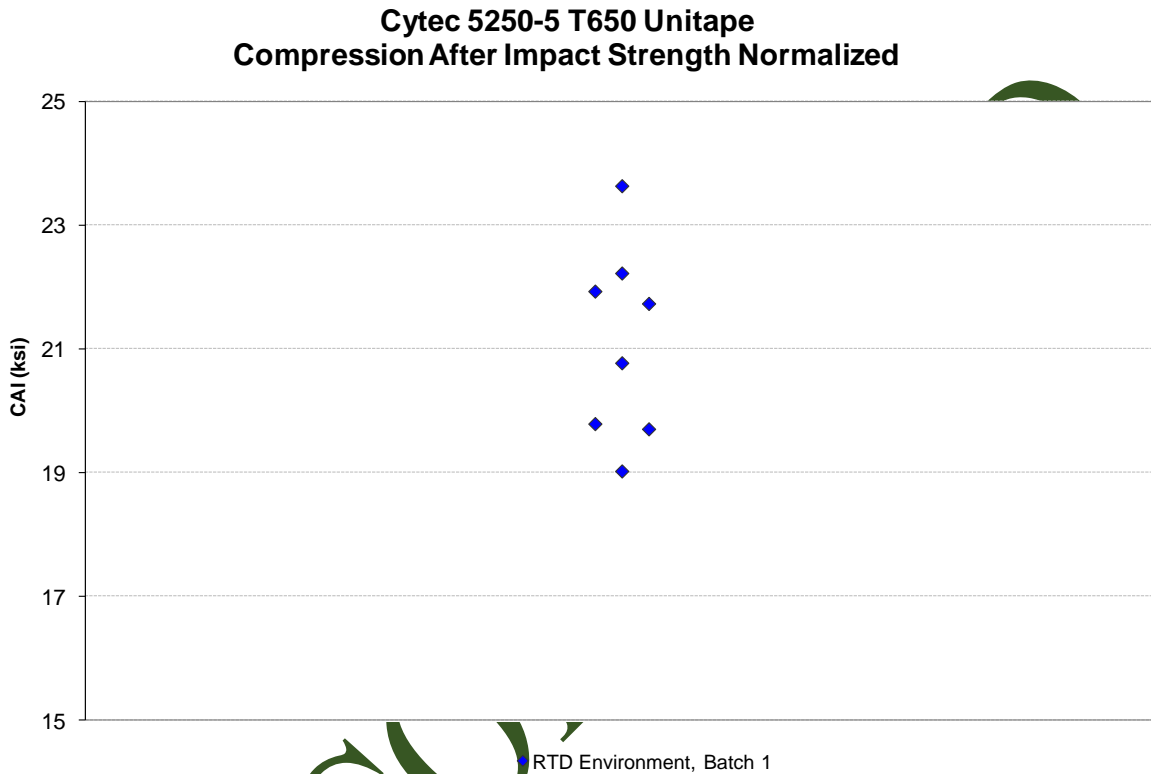


Figure 4-33: Plot for Compression After Impact strength normalized

Compression After Impact Strength (ksi)		
	Normalized	As Measured
Env	RTD	RTD
Mean	21.10	20.74
Stdev	1.55	1.43
CV	7.35	6.91
Modified CV	7.68	7.45
Min	19.02	18.97
Max	23.63	23.03
No. Batches	1	1
No. Spec.	8	8

Table 4-46: Statistics for Compression After Impact Strength data

5. Outliers

Outliers were identified according to the standards documented in section 2.1.5, which are in accordance with the guidelines developed in section 8.3.3 of CMH-17 Rev G. An outlier may be an outlier in the normalized data, the as measured data, or both. A specimen may be an outlier for the batch only (before pooling the three batches within a condition together) or for the condition (after pooling the three batches within a condition together) or both.

Approximately 5 out of 100 specimens will be identified as outliers due to the expected random variation of the data. This test is used only to identify specimens to be investigated for a cause of the extreme observation. Outliers that have an identifiable cause are removed from the dataset as they inject bias into the computation of statistics and basis values. Specimens that are outliers for the condition and in both the normalized and as measured data are typically more extreme and more likely to have a specific cause and be removed from the dataset than other outliers. Specimens that are outliers only for the batch, but not the condition and specimens that are identified as outliers only for the normalized data or the as measured data but not both, are typical of normal random variation.

All outliers identified were investigated to determine if a cause could be found. Outliers with causes were removed from the dataset and the remaining specimens were analyzed for this report. Information about specimens that were removed from the dataset along with the cause for removal is documented in the material property data report, NCAMP Test Report CAM-RP-2010-079 Rev C.

Outliers for which no causes could be identified are listed in Table 5-1. These outliers were included in the analysis for their respective test properties.

Test	Condition	Batch	Specimen Number	Normalized Strength	Strength As Measured	High/Low	Batch Outlier	Condition Outlier
LC	ETD	1	CNARA11BK	233.66	Not an outlier	H	N	Y
UNCO				88.13				
LT	ETW	2	CNAJB11BJ	270.92	276.47	L	Y	Y
SBS	CTD	1	CNAQA216B	NA	16.78	L	Y	N
SBS	RTD	2	CNAQB211A	NA	16.61	H	Y	N
SBS	ETD	1	CNAQA11BK	NA	8.83	H	Y	Y
SBS	ETW	2	CNAQB21EJ	NA	6.48	H	Y	Y
IPS 0.2% Offset	ETW	1	CNANA21AJ	NA	2.23	H	Y	N
IPS 5% Strain	ETW	1	CNANA21AJ	NA	4.45	H	Y	N
IPS 5% Strain	ETW	3	CNANC21BJ	NA	4.52	H	Y	N
UNT1	CTD	1	CNAAA218B	Not an outlier	94.94	L	Y	N
UNT1	CTD	3	CNAAC119B	Not an outlier	104.86	H	Y	N
UNT2	CTD	3	CNABC118B	67.03	Not an outlier	L	Y	N
UNT2	RTD	3	CNABC112A	70.88	Not an outlier	H	N	Y
UNT2	ETW	2	CNABB11BJ	Not an outlier	47.69	L	Y	N
UNC1	ETW	2	CNAWB11BJ	Not an outlier	62.09	H	Y	N
UNC2	RTD	1	CNAXA114A	63.79	64.62	L	As meas - Y Norm - N	Y
OHT3	RTD	2	CNAFB213A	73.43	74.31	L	N	Y
OHC1	RTD	2	CNAGB112A	Not an outlier	48.31	L	Y	N
OHC1	RTD	1	CNAGA111A	48.35	Not an outlier	L	Y	N
OHC1	RTD	3	CNAGC213A	52.12	Not an outlier	H	Y	Y
OHC1	ETW	1	CNAGA11BJ	37.64	Not an outlier	H	Y	N
OHC2	ETW	1	CNAHA215J	Not an outlier	24.07	L	Y	N
OHC3	RTD	2	CNAIB111A	Not an outlier	66.49	H	Y	N
FHC3	RTD	2	CNA9B212A	79.21	Not an outlier	L	Y	N
FHT2	ETW	2	CNA5B11AJ	57.46	Not an outlier	H	Y	N
SSB1 - Ult. Str.	RTD	2	CNA1B113A	154.27	153.77	H	Y	N
SSB1 - Ult. Str.	ETW	3	CNA1C117J	106.83	108.79	H	Y	N
SSB2 - Ult. Str.	ETW	2	CNA2B118J	105.88	Not an outlier	H	Y	N
SSB2 - Ult. Str.	RTD	2	CNA2B212A	160.65	Not an outlier	H	Y	N
SSB3 - Ult. Str.	RTD	2	CNA3B215A	Not an outlier	158.71	H	Y	N
SSB3 - Ult. Str.	ETW	2	CNA3B119J	100.37	102.69	H	Y	N
SSB3 - 2% Offset				64.84	66.34	L	Y	As meas -N Norm - Y
CBS	ETW	1	CNAMA217J	NA	92.26	L	Y	NA

Table 5-1: List of outliers

6. References

1. Snedecor, G.W. and Cochran, W.G., *Statistical Methods*, 7th ed., The Iowa State University Press, 1980, pp. 252-253.
2. Stefansky, W., "Rejecting Outliers in Factorial Designs," *Technometrics*, Vol. 14, 1972, pp. 469-479.
3. Scholz, F.W. and Stephens, M.A., "K-Sample Anderson-Darling Tests of Fit," *Journal of the American Statistical Association*, Vol. 82, 1987, pp. 918-924.
4. Lehmann, E.L., *Testing Statistical Hypotheses*, John Wiley & Sons, 1959, pp. 274-275.
5. Levene, H., "Robust Tests for Equality of Variances," in *Contributions to Probability and Statistics*, ed. I. Olkin, Palo, Alto, CA: Stanford University Press, 1960.
6. Lawless, J.F., *Statistical Models and Methods for Lifetime Data*, John Wiley & Sons, 1982, pp. 150, 452-460.
7. *Metallic Materials and Elements for Aerospace Vehicle Structures*, MIL-HDBK-5E, Naval Publications and Forms Center, Philadelphia, Pennsylvania, 1 June 1987, pp. 9-166,9-167.
8. Hanson, D.L. and Koopmans, L.H., "Tolerance Limits for the Class of Distribution with Increasing Hazard Rates," *Annals of Math. Stat.*, Vol 35, 1964, pp. 1561-1570.
9. Vangel, M.G., "One-Sided Nonparametric Tolerance Limits," *Communications in Statistics: Simulation and Computation*, Vol. 23, 1994, p. 1137.
10. Vangel, M.G., "New Methods for One-Sided Tolerance Limits for a One-Way Balanced Random Effects ANOVA Model," *Technometrics*, Vol 34, 1992, pp. 176-185.
11. Odeh, R.E. and Owen, D.B., *Tables of Normal Tolerance Limits, Sampling Plans and Screening*, Marcel Dekker, 1980.
12. Tomblin, John and Senviratne, Waruna, *Laminate Statistical Allowable Generation for Fiber-Reinforced Composites Material: Lamina Variability Method*, U.S. Department of Transportation, Federal Aviation Administration, May 2006.
13. Tomblin, John, Ng, Yeow and Raju, K. Suresh, *Material Qualification and Equivalency for Polymer Matrix Composite Material Systems: Updated Procedure*, U.S. Department of Transportation, Federal Aviation Administration, September 2003.
14. CMH-17 Rev G, Volume 1, 2012. SAE International, 400 Commonwealth Drive, Warrendale, PA 15096